

Influence of surface coverage on the formation of 4,4'- bipyridinium (viologen) single molecular junctions

Henry M. Osorio,^{a,b,f} Santiago Martín,^{a,c*} David C. Milan,^d Alejandro González-Orive,^b Josef B. G. Gluyas,^e Simon J. Higgins,^d Paul J. Low,^{e*} Richard J. Nichols,^{d*}
and Pilar Cea^{a,b*}

- ^a Departamento de Química Física, Facultad de Ciencias, Universidad de Zaragoza, 50009, Spain.
- ^b Instituto de Nanociencia de Aragón (INA) and Laboratorio de Microscopias Avanzadas (LMA) C/ Mariano Esquilor s/n Campus Rio Ebro, 50018, Zaragoza, Spain.
- ^c Instituto de Ciencia de Materiales de Aragón (ICMA), Universidad de Zaragoza-CSIC, 50009 Zaragoza, Spain.
- ^d Department of Chemistry, University of Liverpool, Crown Street, Liverpool, L69 7ZD, United Kingdom.
- ^e School of Molecular Science, University of Western Australia, 35 Stirling Highway, Crawley, Perth, 6009, Australia.
- ^f Departamento de Física, Escuela Politécnica Nacional, Av. Ladrón de Guevara, E11-253, 170525 Quito, Ecuador.

Abstract

Single-molecule conductance experiments using the STM-based $I(s)$ method and samples of N,N' -di(4-(trimethylsilylethynyl)benzyl)-4,4'-bipyridinium bis(tetrafluoroborate) ($[1](BF_4)_2$) prepared on gold substrates with low-surface coverage of $[1](BF_4)_2$ ($\Gamma = 1.25 \cdot 10^{-11} \text{ mol} \cdot \text{cm}^{-2}$) give rise to molecular junctions with two distinct conductance values. From the associated break-off distances and comparison experiments with related compounds the higher conductance junctions are attributed to molecular contacts between the molecule and the electrodes via the N,N' -dibenzyl-4,4'-bipyridinium (viologen) moiety and one trimethylsilylethynyl (TMSE) group ($G = (5.4 \pm 0.95) \times 10^{-5} G_0$, break-off distance $(1.56 \pm 0.09) \text{ nm}$). The second, lower conductance junction ($G = (0.84 \pm 0.09) \times 10^{-5} G_0$) is consistent with an extended molecular conformation between the substrate and tip contacted through the two TMSE groups giving rise to a break-off distance $(1.95 \pm 0.12) \text{ nm}$ that compares well with the Si...Si distance (2.0 nm) in the extended molecule. Langmuir monolayers of $[1](BF_4)_2$ formed at the air-water interface can be transferred onto a gold-on-glass substrate by the Langmuir-Blodgett (LB) technique to give well-ordered, compact films with surface coverage $\Gamma = 2.0 \cdot 10^{-10} \text{ mol} \cdot \text{cm}^{-2}$. Single-molecule conductance experiments using the STM-based $I(s)$ method reveal only the higher conductance junctions ($G = (5.4 \pm 0.95) \times 10^{-5} G_0$, break-off distance $(1.56 \pm 0.09) \text{ nm}$) due to the restricted range of molecular conformations in the tightly packed, well-ordered LB film.

Introduction

Molecular electronics is an emergent technology in which organic, inorganic or organometallic molecules are connected between two (or three) electrodes, and their electrical properties are harnessed to perform some useful function that can translate to enhanced or novel performance in an electronic device.¹ Recent developments in methods of contacting single molecules or portions of monolayer films by electrodes formed from a wide variety of materials, and measuring the electrical characteristics of these ‘molecular junctions’, have driven significant progress in the area. Nevertheless, many difficult challenges must be overcome before molecular junctions

suitable for developing the science of molecular electronics can be translated to true device structures and considered as a viable technology capable of reaching the market.² However, commercial molecular electronics devices are starting to emerge with the innovation of molecular electronic components for audio processing.³

Many studies have been undertaken to measure and optimize the electrical characteristics of molecular junctions, with an ultimate goal of establishing design rules for the construction of a molecular electronic device. It is now well-established that charge transfer through molecular junctions is dependent on many different factors, including the structure and conformation of the molecular backbone, the number of molecules in the junction, solvent environment and external electrochemical potential, the electrode material, surface structure and the nature of the electrode-molecule contact.⁴⁻⁷ The study of single molecule junctions has greatly contributed to the understanding of these parameters, and their influence on charge and heat transport phenomena at the molecular scale.⁸⁻¹⁶ Although single molecule measurements may appear to represent the ultimate low coverage phase (i.e. a single molecule), depending on the measurement conditions, such measurements may also be performed on single molecules within a densely packed monolayer phase. In turn, studies of larger area metal–molecular monolayer–metal junctions in which molecular components are assembled into a well-defined, high surface coverage and usually well-characterized monolayer film within the junction play a further crucial role in understanding the effect of intermolecular interactions, such as van der Waals interactions and polarization effects, on the electronic transport properties of the molecular film.¹⁷⁻²⁰ In addition, whilst single molecule junctions are excellent vehicles through which to study transport phenomena, planar-sandwiched monolayer structures are more closely aligned with practical electronic applications.

Whether assembled from a single-molecule or monolayer-film, the ability to manipulate the electrical response of a molecular junction beyond the simple non-resonant tunneling behavior of many candidate molecular wires is also an area of intense contemporary activity. For example, mechanical compression or elongation of single-molecule junctions has been shown to facilitate the manipulation of the structure of the molecule within the junction and details of how molecules bind to the electrodes, resulting in mechanical gating of the junction.^{21,22} However, despite

establishing that molecular orientation and junction geometry can play a significant role on the electrical response of a junction, it is not yet clear how, or if, the changes in molecular geometry and orientation that can be expected to occur upon increasing surface coverage of molecular components from truly isolated single molecules to more densely packed and ordered films can influence the electrical response of a junction.

The capacity of various N,N' -disubstituted-4,4'-bipyridinium, or viologen, derivatives to assemble into well-ordered mono- and multi-layered Langmuir films has been established.²³⁻²⁵ In these structures, the doubly-charged viologen group is anchored at the aqueous surface and the (typically hydrophobic) N,N' -substituents are aligned outwards from the surface of the aqueous sub-phase.^{23,26} These Langmuir films are readily transferred onto hydrophilic substrates by means of the vertical dipping method,^{23,26,27} preserving the orientation of the viologen units in the Langmuir films in the resulting substrate-supported Langmuir-Blodgett film in terms to study the electrochemical properties of these films but the electrical properties of these well-ordered films have not yet been studied in detail.

Viologen-based molecular components have also been studied within single molecule junctions, with the reversibility of their redox reactions at modest potentials and the high chemical stability of their various redox states leading to efficient molecular wires based on charge hopping mechanisms, and also allowing electrochemical switching and development of nascent transistor-like devices.^{11,28-30} However, a comparative study of viologen-containing molecules within both single molecule junctions and well-ordered films offers additional challenges and avenues for exploration that have not been explored to date.

In this contribution, single-molecule junctions of the viologen derivative, N,N' -di(4-(trimethylsilylethynyl)benzy)-4,4'-bipyridinium as its bis(tetrafluoroborate) salt ($[I](BF_4)_2$) (Figure 1) have been formed from both dilute solution, leading to low surface coverage, and well-ordered and tightly-packed monolayer LB films. The surface coverage dependence of the formation of single molecular junctions and the resulting electrical conductance is evaluated. The electrical properties and break-off distances from the single molecule junctions formed from isolated molecules of

[1](BF₄)₂ on the surface and well-ordered films reveal two distinct conductance values. By comparison with junctions formed from the related compounds [2](BF₄)₂ and **3** (Figure 1) these different conductance values can be attributed to different molecular configurations and contacts within the junction: (1) a lower conductance junction formed from electrode contact to the two terminal trimethylsilylethynyl (TMSE) groups with the molecule adopting an extended conformation between the electrodes; and (2) a higher conductance junction arising from a more compact molecular conformation with contact to the electrodes formed between the viologen moiety and one TMSE group. Both types of molecular contact are observed from for junctions formed from the isolated molecules, but in the case of the LB film-based junctions, only the more compact, viologen-contacted junction has been observed.

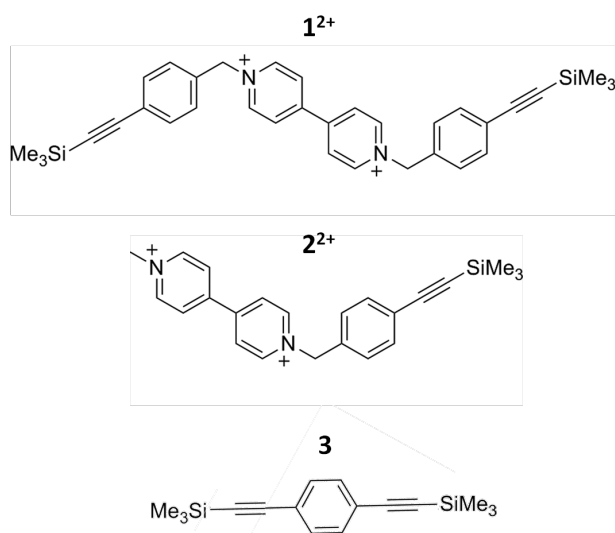


Figure 1. Molecular structures of the compounds used in this study.

Results and discussions

The low surface deposition of [1](BF₄)₂ on a flame-annealed gold substrate was achieved by placing a gold electrode for just 60 s into a 5×10^{-4} M solution of [1](BF₄)₂ in ethanol. The surface coverage was quantified by measuring the frequency change (Δf) of a quartz crystal resonator for incubation at different times in the adsorption solution until the frequency remained constant (see Supplementary Information, SI, for further details). Using the Sauerbrey equation,³¹ frequency changes for the different adsorption times were converted to coverage and the

resulting isotherm is shown in Figure 2. As can be observed, at 60 s a surface coverage of $1.25 \cdot 10^{-11} \text{ mol} \cdot \text{cm}^{-2}$ was obtained.

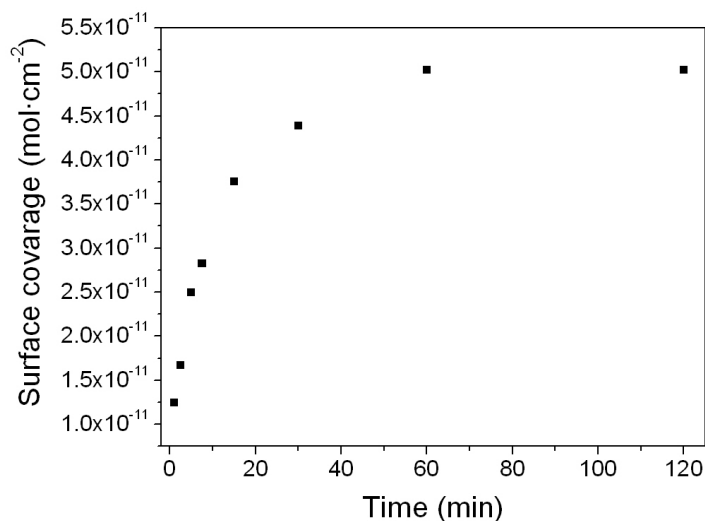


Figure 2. Determination of the surface coverage of $[1](\text{BF}_4)_2$ adsorbed onto a gold-coated quartz resonator during the incubation process.

A higher surface coverage of $[1](\text{BF}_4)_2$ was obtained by transferring a homogenous monolayer, formed and characterized at the air-water interface, onto a gold substrate to produce a compact LB film. This was achieved by the vertical dipping method with the hydrophilic substrates initially immersed in the water subphase at the optimum surface pressure of $10 \text{ mN} \cdot \text{m}^{-1}$ (see SI for further details of the LB film fabrication and characterization). At this surface pressure the surface coverage was determined with a quartz crystal microbalance (QCM) by measuring the frequency change (Δf) for a quartz resonator before and after the deposition process. A surface coverage, Γ , of $2.0 \cdot 10^{-10} \text{ mol} \cdot \text{cm}^{-2}$ was then obtained using the Sauerbrey equation (see SI). Therefore, from these two different methods of sample preparation, a surface coverage difference amounting to a factor of 16 between the low and high coverage is obtained, allowing us to study how these two markedly different surface arrangements of 1^{2+} influence the formation of molecular junctions using an STM probe.

Conductance measurements of molecular junctions formed from either low surface coverage phases ($\Gamma = 1.25 \cdot 10^{-11} \text{ mol} \cdot \text{cm}^{-2}$) or LB films (high surface coverage, $\Gamma =$

$2.0 \cdot 10^{-10} \text{ mol} \cdot \text{cm}^{-2}$) of $[\mathbf{1}](\text{BF}_4)_2$ were carried out using a scanning tunneling microscope (STM) and the $I(s)$ method.^{11,32} The $I(s)$ method has been widely used to determine the conductance both of single molecules^{14,33-35} and molecules assembled into monolayers.³⁶⁻³⁹ In the $I(s)$ technique, an STM tip is first moved into close proximity of the surface, as determined by the STM set point conditions, but in contrast to an STM break-junction metallic contact between tip and surface is avoided. The feedback loop is then disabled and the STM tip is rapidly retracted and the junction tunneling current recorded. If molecule(s) bridge between the STM tip and substrate an enhanced junction current is obtained and many such molecular junction formation and cleavage cycles are recorded and statistically analyzed to obtain the molecular junction conductance. Further details of the measurements are given in the Supplementary Information.

The $I(s)$ curves obtained from substrates with low surface coverage of $[\mathbf{1}](\text{BF}_4)_2$ feature a set of plateaus arising from formation of single-molecule junctions, with a relative high conductance (HC) value at $(5.3 \pm 0.85) \times 10^{-5} G_0$ (Figure 3a), with a break-off distance of $(1.6 \pm 0.11) \text{ nm}$, estimated from the corresponding 2-D histogram (Figure 4a), which is somewhat shorter than the Si...Si distance estimated for the extended molecular conformation (2.0 nm). A detailed analysis closer to the noise level of the current amplifier in the $I(s)$ scans of these conductance-distance traces shows another set of plateaus that are clustered around a low conductance (LC) value of $(8.4 \pm 0.9) \times 10^{-6} G_0$, almost an order of magnitude lower than the HC feature, with a much longer break-off distance of $1.95 \pm 0.12 \text{ nm}$ (Figure 4c). The plateaus corresponding to the LC feature and the corresponding conductance histogram are illustrated in the insets to Figure 3a. Some of the sample conductance traces were found to have plateaus corresponding to both conductance values, suggesting that the conduction pathway in the high state (HC) is not only shorter than that in the low state (LC), but that the HC junctions can evolve into the LC junctions as the tip is retracted.

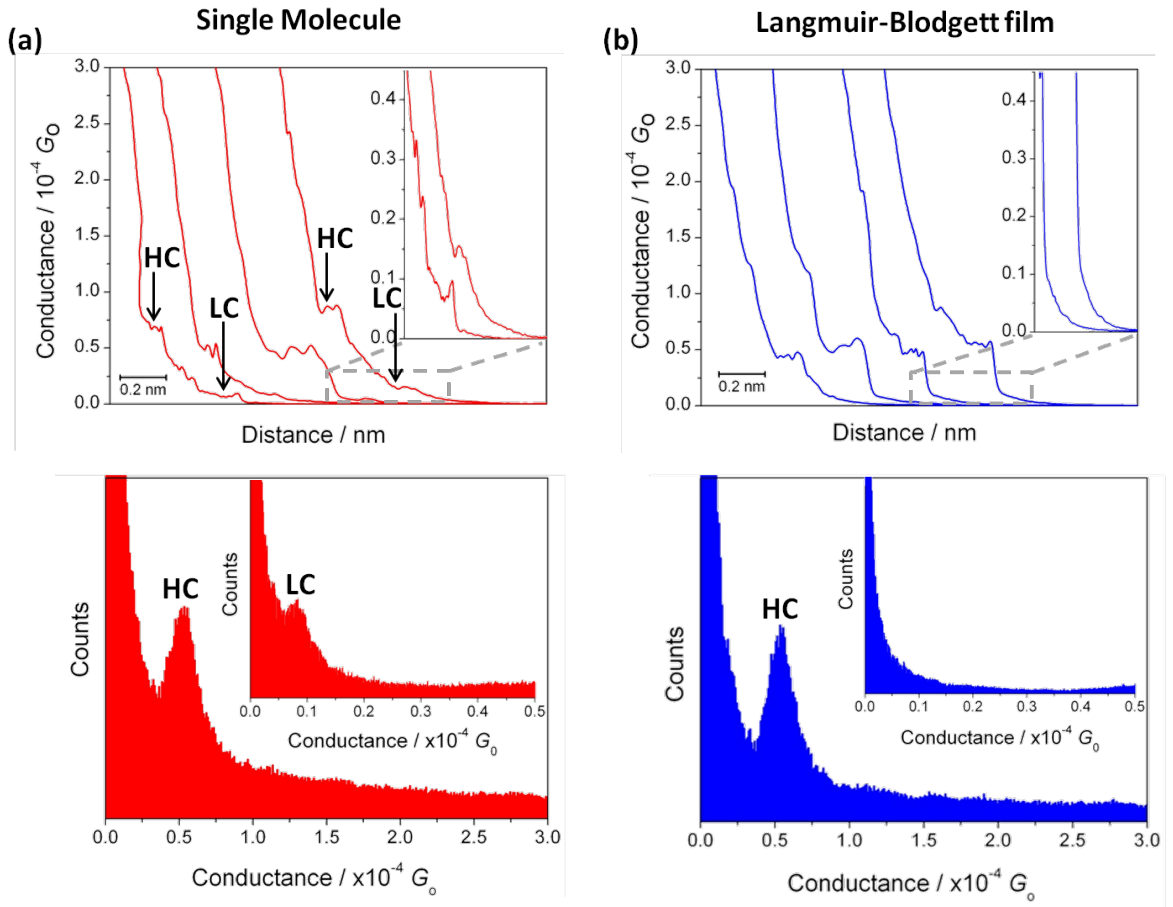
1^{2+} 

Figure 3. (a) Representative $I(s)$ traces for single molecule junctions of 1^{2+} and conductance histogram built from summation of conductance traces (ca. 500) that show discernible plateaus. (b) Representative $I(s)$ traces for molecular junctions formed from a LB film of 1^{2+} and conductance histogram built from summation of conductance traces (ca. 500) that shows discernible plateaus. $U_t = 0.6$ V where U_t is the “tip bias”.

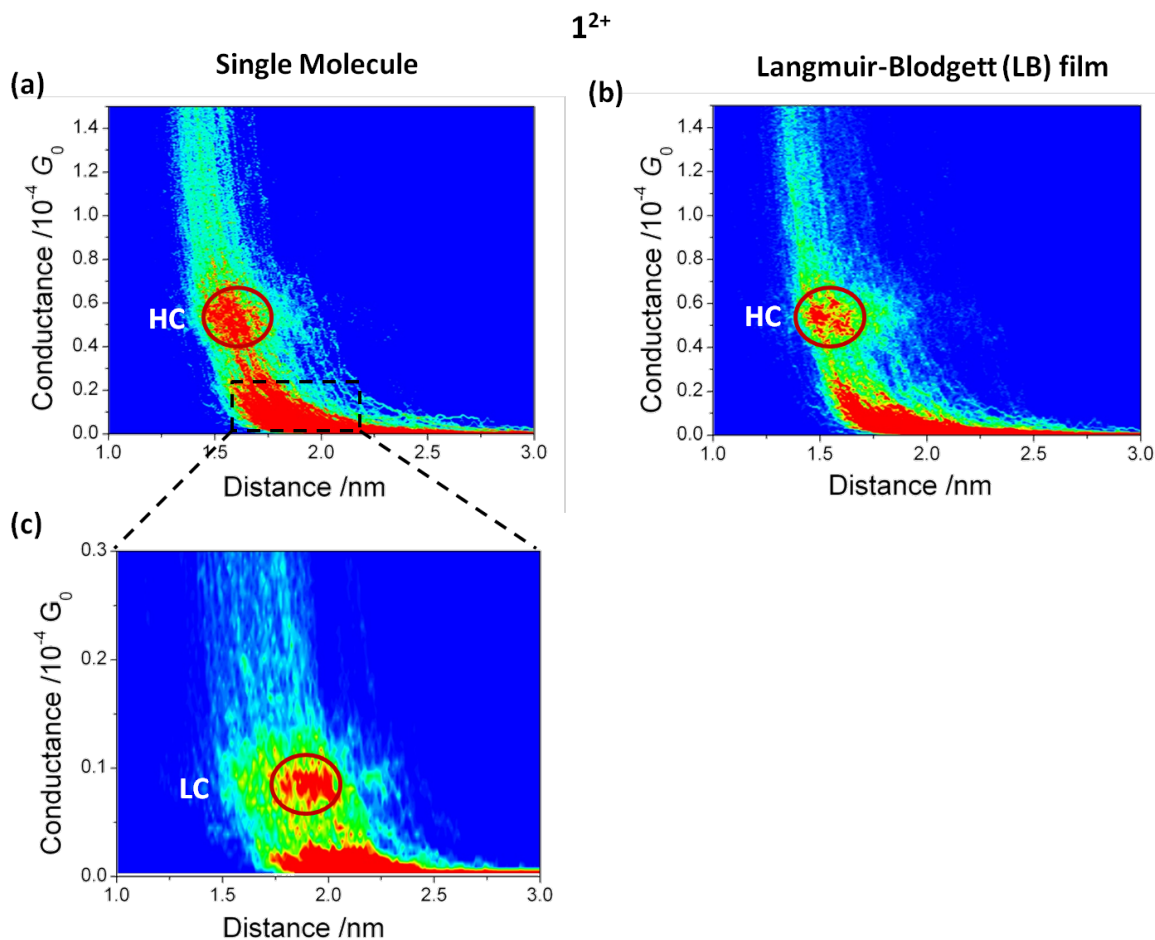


Figure 4. 2D conductance histograms for (a) a low coverage phase, single molecule, and (b) for molecular junctions formed from a LB film of $[1](BF_4)_2$ (c) 2D-histogram constructed by using only the $I(s)$ curves which present the plateau corresponding to the low conductance (LC) value observed for single-molecule junctions of 1^{2+} in Figure 2a.

The conductance value determined from this LC group is also in excellent agreement with the single molecule conductance reported for $[1](BF_4)_2$ in an ionic liquid (1-butyl-3-methylimidazolium triflate (BMIM-OTf)), $\sim 0.8 \times 10^{-5} G_0$.³⁰ Similarly, a viologen derivative with alkyl chains as N,N' -substituents and using thiols as anchoring groups (N,N' -di-(6-(thioacetyl)hexyl)-4,4'-bipyridinium dibromide) which features a S...S distance of 2.4 nm, conductance values of $\sim 0.75 \times 10^{-5} G_0$ and $\sim 0.7 \times 10^{-5} G_0$ were recorded in BMIM-OTf³⁰ and in air,¹¹ respectively, with break-off distances of ~ 2 nm.¹¹ These results suggest that the LC group arises from molecular junctions in which 1^{2+} is contacted through the TMSE groups in an extended molecular geometry (Figure 5b).

The $I(s)$ curves from molecular junctions formed from the more densely packed LB films of $[1](BF_4)_2$ (Figure 3b) and the conductance histogram, constructed from 500 $I(s)$ curves, (Figure 3b bottom) also present a set of HC plateaus at $(5.4 \pm 0.95) \times 10^{-5} G_0$ with associated break-off distance of (1.56 ± 0.09) nm, Figure 4b. In contrast to junctions formed from the low surface coverage substrates featuring more isolated molecules, single-molecule junctions formed from the LB film do not show any other set of plateaus (insets in Figure 3b). The observation of a unique set of plateaus for junctions formed from LB films of $[1](BF_4)_2$ indicates a more uniform and less mobile molecular conformation within the junction, which is likely to be a consequence of the tight packing and high surface coverage in the film. It should be noted here that this method of measurement is likely to be locally destructive for the monolayer structure, since the initial distance between the tip and the substrate is less than the LB film thickness; in other words, the tip penetrates into monolayer. As a consequence the molecule (or molecules) initially trapped within the junction must presumably tilt toward the horizontal in order to compensate for the vertical approach of the tip. Then, during measurement, the molecule is “lifted” by the retracting STM tip, until the molecule bridge breaks.

The similarity between the high conductance, HC, values and break-off distances for the junctions formed from both single-molecule ($(5.3 \pm 0.85) \times 10^{-5} G_0$; 1.60 ± 0.11 nm) and the LB film ($(5.4 \pm 0.95) \times 10^{-5} G_0$; 1.56 ± 0.09 nm) indicate that 1^{2+} is found in the same configuration in both cases. In seeking to better define the molecular geometry in the junctions, the thickness of a LB film of $[1](BF_4)_2$ was determined to be (1.40 ± 0.20) nm by scratching the film with the AFM tip (see SI for more details).⁴⁰ The film thickness obtained using this method (Figure S7) is in good agreement with the break-off distances for the HC plateaus, if one considers that during junction extension only one leg of the molecule is “lifted” until the molecular bridge breaks as in Figure 5a. The film thickness and break-off distances are both considerably shorter than the Si...Si distance (2.0 nm) calculated for 1^{2+} , but entirely consistent with the configuration shown in Figure 5a in which the viologen fragment is linked to one of the electrodes and one of the TMSE end groups is in contact with the top contact electrode. The HC contact in both single-molecule and LB film junctions is therefore

attributed to this conformation. A similar orientation of viologen derivatives was described previously in other LB films containing this moiety.^{24,25}

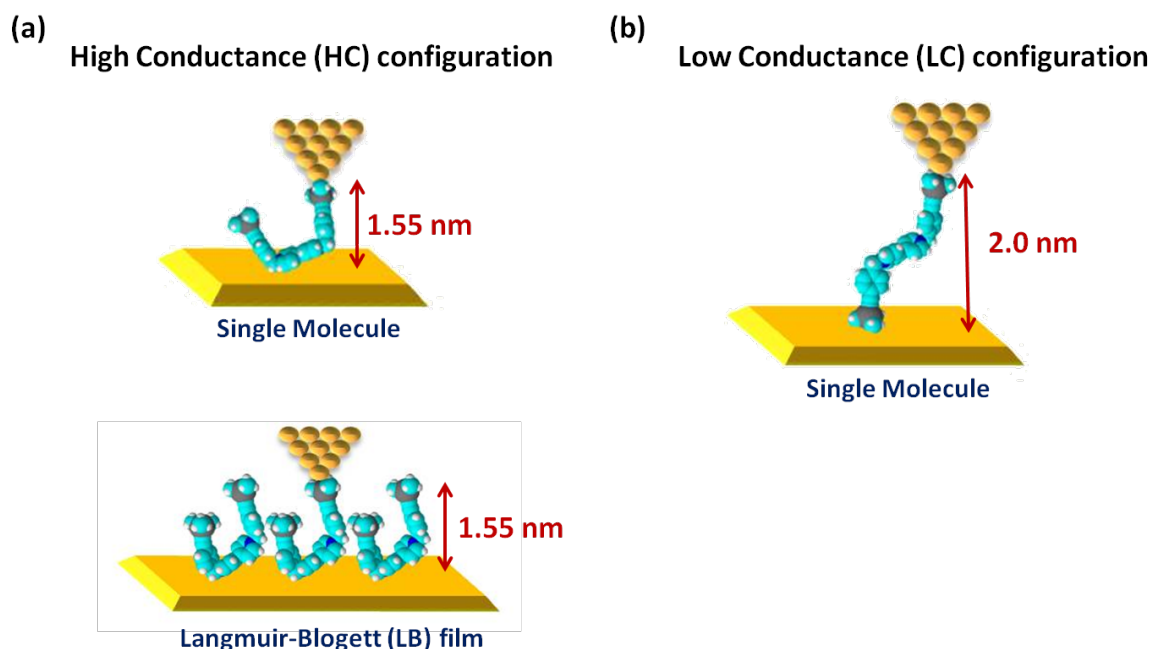


Figure 5. The proposed configuration of 1^{2+} for (a) the high conductance (HC) pathway and (b) the low conductance (LC) pathway from Spartan[®]08V 1.0.0 molecular models.

To corroborate all these results, single-molecule conductance measurements were carried out for compound 2^{2+} (also as the bis(tetrafluoroborate) salt), which features the viologen fragment, but only one benzyl-supported trimethylsilylethynyl moiety (Figure 1). Figure 6a shows the 2D conductance histogram built from summation of conductance traces (ca. 500) that shown discernible plateaus as described in the Supplementary Information. A conductance peak at $(5.3 \pm 0.70) \times 10^{-5} G_0$ and a break-off distance of (1.52 ± 0.07) nm were obtained. Both the conductance value and the break-off distance are in excellent agreement with the HC value recorded for 1^{2+} in single-molecule and LB film-based junctions, supporting the proposed configuration shown in Figure 5a as being responsible for the HC pathway.

The efficacy of the viologen contact can be appreciated by comparison with the conductance data obtained from the linearly conjugated wire-like molecule **3**, which

features the TMSE surface binding groups in a similar Si...Si distance as that proposed for the HC junctions from $\mathbf{1}^{2+}$. A 2D conductance histogram constructed from data collected from single molecule junctions of 1,4-bis(trimethylsilylethynyl) benzene ($\mathbf{3}$) under identical conditions shows a single conductance peak at $(1.25 \pm 0.50) \times 10^{-5} G_0$, some 4 – 5 times lower than the viologen/TMSE contacted compounds $\mathbf{1}^{2+}$ (HC) and $\mathbf{2}^{2+}$, despite the comparable break-off distance (1.41 ± 0.12) nm (Figure 6b).

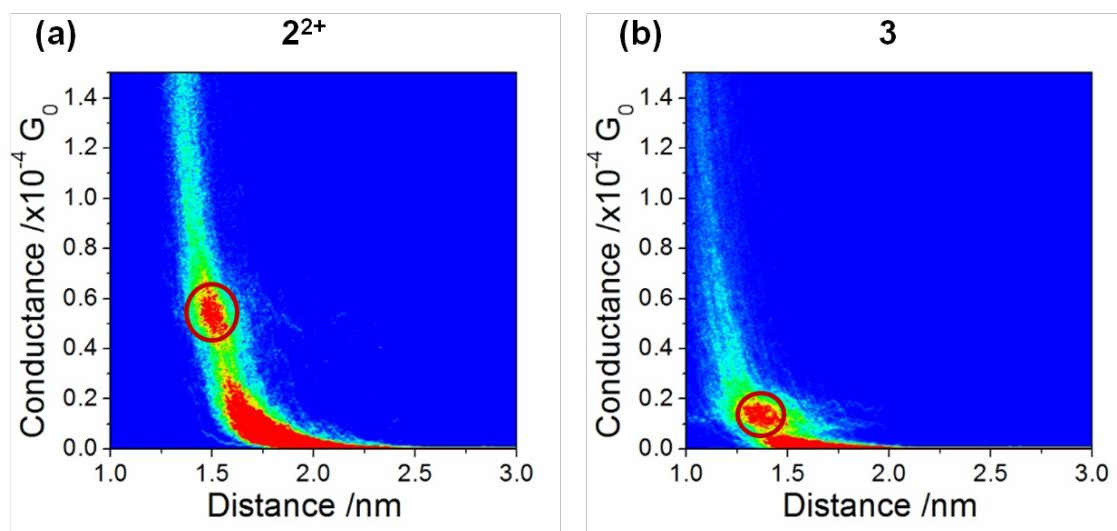


Figure 6. 2D conductance histograms for (a) a single molecule of $\mathbf{2}^{2+}$ and (b) a single molecule of $\mathbf{3}$.

Conclusions

The electrical properties of single-molecule junctions prepared from substrates with low surface coverage of $[\mathbf{1}](\text{BF}_4)_2$ ($\Gamma = 1.25 \cdot 10^{-11} \text{ mol} \cdot \text{cm}^{-2}$) and LB films with considerably higher surface coverage ($\Gamma = 2.0 \cdot 10^{-10} \text{ mol} \cdot \text{cm}^{-2}$) have been examined by the scanning tunneling microscope-based $I(s)$ technique. From junctions prepared from isolated molecules, two conductance values were observed. The low conductance (LC) junction has been associated to the conventional ‘end-to-end’ contacted molecule, with the two trimethylsilylethynyl (TMSE) groups linked to the electrodes giving rise to an extended molecular conformation within the junction. The high conductance (HC) junction has been associated with a conformation which viologen fragment contacts to one of the electrodes and a TMSE group to the other one. From junctions formed from single molecules constrained into LB films only a

single high conductance (HC) junction has been observed. Therefore, surface coverage and molecular packing density can be used to control the geometry of molecules within molecular junctions, leading to a degree of control over the resulting electrical properties.

Experimental Methods.

Compound **[1]**(BF₄)₂ and **3** were synthesized by the literature methods.^{30,41} Compound **[2]**(BF₄)₂ was prepared by minor variation of the routes described elsewhere.⁴²

LB films of **[1]**(BF₄)₂ were prepared using a Nima Teflon trough with dimensions (720×100) mm², which was housed in a constant temperature (20 ± 1 °C) clean room. A Wilhelmy paper plate pressure sensor was used to measure the surface pressure (π) of the monolayers. The subphase was pure water (Millipore Milli-Q, resistivity 18.2 M Ω ·cm). A 7.5×10⁻⁶ M solution of **[1]**(BF₄)₂ in HPLC grade CHCl₃:EtOH (3:1) was spread onto the water surface. The spreading solvent was allowed to completely evaporate from the aqueous surface over a period of at least 20 min before compression of the monolayer commenced at a constant sweeping speed of 0.015 nm²·molecule⁻¹·min⁻¹. Under these experimental conditions, the isotherms were highly reproducible. The monolayers were deposited by the vertical dipping method onto a gold substrate at a constant surface pressure of 10 mN·m⁻¹ and a speed of 3 mm·min⁻¹.

The STM based $I(s)$ method described in the literature,^{11,32} and in further detail in the Supplementary Information has been used here to obtain conductance values of molecular junctions formed from either a LB film of **[1]**(BF₄)₂ or low coverage phases of compounds **[1]**(BF₄)₂, **[2]**(BF₄)₂ and **3**. In brief, in this method (I = current and s = distance) a gold STM tip is brought to a fixed distance above the gold surface, but avoiding metallic contact between tip and surface, so that the target molecule can bind between the gold tip and the substrate. The current is then recorded as the STM tip is retracted from a surface until the molecule bridge(s) break, resulting in a current plateau followed by a step. Hundreds of such junctions are analyzed statistically in histograms to yield the conductance. To avoid ambiguity caused by the inclusion of retraction traces in the absence of molecular bridge formation, conductance

histograms were constructed from retraction traces displaying plateaus and steps, which are synonymous with molecular junction formation. The STM- $I(s)$ measurements were performed with flame-annealed Au substrates in order to obtain atomically flat Au(111) surfaces.⁴³ Molecular adsorption for single-molecule studies was achieved by immersing the gold electrode for 60 s in a 5×10^{-4} M ethanolic solution. The relatively short immersion times and low concentrations are aimed at promoting low coverage on the gold slide which in turn favors single-molecule events. After adsorption, the sample was rinsed in ethanol and gently blown dry in a stream of nitrogen gas. Gold STM tips were fabricated from 0.25 mm Au wire (99.99%) which was freshly electrochemically etched for each experiment at +2.4 V in a mixture of ethanol (50%) and HCl (50%).

Supporting Information

Fabrication and Characterization of Langmuir and Langmuir-Blodgett (LB) films, single molecule and LB films conductance measurements, details of the tip to substrate calibration in the $I(s)$ technique, and determination of the thickness of the LB films.

Acknowledgements

S.M. and P.C. are grateful for financial assistance from Ministerio de Economía y Competitividad from Spain and fondos FEDER in the framework of projects MAT2016-78257-R. S.M. and P.C. also acknowledge DGA/fondos FEDER (construyendo Europa desde Aragón) for funding the research group Platón (E-54). S.M. acknowledges funding from the University of Zaragoza (grant number JIUZ02016-CIE-04). R.J.N, S.J.G and D.C.M are grateful for financial assistance from the EPSRC (grant EP/M029522/1). P.J.L. and J.B.G.G. gratefully acknowledge support from the Australian Research Council (FT120100073; DP140100855).

References

- (1) Editorial *Nat Nanotechnol* **2013**, 8, 377
- (2) Xiang, D.; Wang, X. L.; Jia, C. C.; Lee, T.; Guo, X. F. Molecular-Scale Electronics: From Concept to Function. *Chem Rev* **2016**, 116 (7), 4318-4440
- (3) Bergren, A. J.; Zeer-Wanklyn, L.; Semple, M.; Pekas, N.; Szeto, B.; McCreery, R. L. Musical molecules: the molecular junction as an active component in audio distortion circuits. *J Phys-Condens Mat* **2016**, 28 (9), 094011

- (4) Jia, C. C.; Guo, X. F. Molecule-electrode interfaces in molecular electronic devices. *Chem Soc Rev* **2013**, *42* (13), 5642-5660
- (5) Karthaus, S. Control of molecule-based transport for future molecular devices. *J Phys-Condens Mat* **2011**, *23* (1), 013001
- (6) Sun, L.; Diaz-Fernandez, Y. A.; Gschneidner, T. A.; Westerlund, F.; Lara-Avila, S.; Moth-Poulsen, K. Single-molecule electronics: from chemical design to functional devices. *Chem Soc Rev* **2014**, *43* (21), 7378-7411
- (7) Leary, E.; La Rosa, A.; Gonzalez, M. T.; Rubio-Bollinger, G.; Agrait, N.; Martin, N. Incorporating single molecules into electrical circuits. The role of the chemical anchoring group. *Chem Soc Rev* **2015**, *44* (4), 920-942
- (8) Cui, X. D.; Primak, A.; Zarate, X.; Tomfohr, J.; Sankey, O. F.; Moore, A. L.; Moore, T. A.; Gust, D.; Harris, G.; Lindsay, S. M. Reproducible measurement of single-molecule conductivity. *Science* **2001**, *294* (5542), 571-574
- (9) Smit, R. H. M.; Noat, Y.; Untiedt, C.; Lang, N. D.; van Hemert, M. C.; van Ruitenbeek, J. M. Measurement of the conductance of a hydrogen molecule. *Nature* **2002**, *419* (6910), 906-909
- (10) Xu, B. Q.; Tao, N. J. J. Measurement of single-molecule resistance by repeated formation of molecular junctions. *Science* **2003**, *301* (5637), 1221-1223
- (11) Haiss, W.; van Zalinge, H.; Higgins, S. J.; Bethell, D.; Hobenreich, H.; Schiffrin, D. J.; Nichols, R. J. Redox state dependence of single molecule conductivity. *J Am Chem Soc* **2003**, *125* (50), 15294-15295
- (12) Haiss, W.; Wang, C. S.; Grace, I.; Batsanov, A. S.; Schiffrin, D. J.; Higgins, S. J.; Bryce, M. R.; Lambert, C. J.; Nichols, R. J. Precision control of single-molecule electrical junctions. *Nat Mater* **2006**, *5* (12), 995-1002
- (13) Lafferentz, L. Conductance of a single conjugated polymer as a continuous function of its length *Science* **2009**, *325* (5937), 148-148
- (14) Sedghi, G.; Garcia-Suarez, V. M.; Esdaile, L. J.; Anderson, H. L.; Lambert, C. J.; Martin, S.; Bethell, D.; Higgins, S. J.; Elliott, M.; Bennett, N.; Macdonald, J. E.; Nichols, R. J. Long-range electron tunnelling in oligo-porphyrin molecular wires. *Nat Nanotechnol* **2011**, *6* (8), 517-523
- (15) Aradhya, S. V.; Venkataraman, L. Single-molecule junctions beyond electronic transport. *Nat Nanotechnol* **2013**, *8* (6), 399-410
- (16) Perrin, M. L.; Verzijl, C. J. O.; Martin, C. A.; Shaikh, A. J.; Eelkema, R.; van Esch, J. H.; van Ruitenbeek, J. M.; Thijssen, J. M.; van der Zant, H. S. J.; Dulic, D. Large tunable image-charge effects in single-molecule junctions. *Nat Nanotechnol* **2013**, *8* (4), 282-287
- (17) Karthaus, S. Control of molecule-based transport for future molecular devices. *J Phys-Condens Mat* **2011**, *23* (1), 013001
- (18) Pera, G.; Martin, S.; Ballesteros, L. M.; Hope, A. J.; Low, P. J.; Nichols, R. J.; Cea, P. Metal-Molecule-Metal Junctions in Langmuir-Blodgett Films Using a New Linker: Trimethylsilane. *Chem-Eur J* **2010**, *16* (45), 13398-13405
- (19) Ballesteros, L. M.; Martin, S.; Cortes, J.; Marques-Gonzalez, S.; Higgins, S. J.; Nichols, R. J.; Low, P. J.; Cea, P. Controlling the Structural and Electrical Properties of Diacid Oligo(Phenylene Ethynylene) Langmuir-Blodgett Films. *Chem-Eur J* **2013**, *19* (17), 5352-5363
- (20) Osorio, H. M.; Martin, S.; Lopez, M. C.; Marques-Gonzalez, S.; Higgins, S. J.; Nichols, R. J.; Low, P. J.; Cea, P. Electrical characterization of single molecule and Langmuir-Blodgett monomolecular films of a pyridine-terminated oligo(phenylene-ethynylene) derivative. *Beilstein J Nanotech* **2015**, *6*, 1145-1157

- (21) Inatomi, J.; Fujii, S.; Marques-Gonzalez, S.; Masai, H.; Tsuji, Y.; Terao, J.; Kiguchi, M. Effect of Mechanical Strain on Electric Conductance of Molecular Junctions. *J Phys Chem C* **2015**, *119* (33), 19452-19457
- (22) Quek, S. Y.; Kamenetska, M.; Steigerwald, M. L.; Choi, H. J.; Louie, S. G.; Hybertsen, M. S.; Neaton, J. B.; Venkataraman, L. Mechanically controlled binary conductance switching of a single-molecule junction. *Nat Nanotechnol* **2009**, *4* (4), 230-234
- (23) Cea, P.; Lafuente, C.; Urieta, J. S.; Lopez, M. C.; Royo, F. M. Langmuir and Langmuir-Blodgett films of a viologen derivative. *Langmuir* **1998**, *14* (25), 7306-7312
- (24) Martin, S.; Villares, A.; Haro, M.; Lopez, M. C.; Cea, P. Electrochemical investigation on hybrid viologen tetracyanoquinodimethanide LB films. *J Electroanal Chem* **2005**, *578* (2), 203-211
- (25) Cea, P.; Martin, S.; Villares, A.; Mobius, D.; Lopez, M. C. Use of UV-vis reflection spectroscopy for determining the organization of viologen and viologen tetracyanoquinodimethanide monolayers. *J Phys Chem B* **2006**, *110* (2), 963-970
- (26) Qian, D. J.; Nakamura, C.; Miyake, J. Mixed monolayers of phospholipids with a viologen and the electrochemical properties in Langmuir-Blodgett films. *Colloid Surface A* **2000**, *175* (1-2), 93-98
- (27) Qian, D. J.; Nakamura, C.; Zorin, N.; Miyake, J. Hydrogenase-poly(viologen) complex monolayers and electrochemical properties in Langmuir-Blodgett films. *Colloid Surface A* **2002**, *198*, 663-669
- (28) Raymo, F. M.; Alvarado, R. J. Electron transport in bipyridinium films. *Chem Rec* **2004**, *4* (3), 204-218
- (29) Leary, E.; Higgins, S. J.; van Zalinge, H.; Haiss, W.; Nichols, R. J.; Nygaard, S.; Jeppesen, J. O.; Ulstrup, J. Structure-property relationships in redox-gated single molecule junctions - A comparison of pyrrolo-tetrathiafulvalene and viologen redox groups. *J Am Chem Soc* **2008**, *130* (37), 12204-12205
- (30) Osorio, H. M.; Catarelli, S.; Cea, P.; Gluyas, J. B. G.; Hartl, F.; Higgins, S. J.; Leary, E.; Low, P. J.; Martin, S.; Nichols, R. J.; Tory, J.; Ulstrup, J.; Vezzoli, A.; Milan, D. C.; Zeng, Q. Electrochemical Single-Molecule Transistors with Optimized Gate Coupling. *J Am Chem Soc* **2015**, *137* (45), 14319-14328
- (31) Sauerbrey, G. Verwendung Von Schwingquarzen Zur Wagung Dunner Schichten Und Zur Mikrowagung. *Z Phys* **1959**, *155* (2), 206-222
- (32) Nichols, R. J.; Haiss, W.; Higgins, S. J.; Leary, E.; Martin, S.; Bethell, D. The experimental determination of the conductance of single molecules. *Phys Chem Chem Phys* **2010**, *12* (12), 2801-2815
- (33) Martin, S.; Grace, I.; Bryce, M. R.; Wang, C. S.; Jitchati, R.; Batsanov, A. S.; Higgins, S. J.; Lambert, C. J.; Nichols, R. J. Identifying Diversity in Nanoscale Electrical Break Junctions. *J Am Chem Soc* **2010**, *132* (26), 9157-9164
- (34) Haiss, W.; Martin, S.; Leary, E.; van Zalinge, H.; Higgins, S. J.; Bouffier, L.; Nichols, R. J. Impact of Junction Formation Method and Surface Roughness on Single Molecule Conductance. *J Phys Chem C* **2009**, *113* (14), 5823-5833
- (35) Sedghi, G.; Esdaile, L. J.; Anderson, H. L.; Martin, S.; Bethell, D.; Higgins, S. J.; Nichols, R. J. Comparison of the Conductance of Three Types of Porphyrin-Based Molecular Wires: beta,meso,beta-Fused Tapes, meso-

Butadiyne-Linked and Twisted meso-meso Linked Oligomers. *Adv Mater* **2012**, 24 (5), 653-657

(36) Sek, S.; Misicka, A.; Swiatek, K.; Maicka, E. Conductance of alpha-helical peptides trapped within molecular junctions. *J Phys Chem B* **2006**, 110 (39), 19671-19677

(37) Sek, S. Two metal-molecule binding modes for peptide molecular junctions. *J Phys Chem C* **2007**, 111 (34), 12860-12865

(38) Sek, S.; Tolak, A.; Misicka, A.; Palys, B.; Bilewicz, R. Asymmetry of electron transmission through monolayers of helical polyalanine adsorbed on gold surfaces. *J Phys Chem B* **2005**, 109 (39), 18433-18438

(39) Ballesteros, L. M.; Martin, S.; Pera, G.; Schauer, P. A.; Kay, N. J.; Lopez, M. C.; Low, P. J.; Nichols, R. J.; Cea, P. Directionally Oriented LB Films of an OPE Derivative: Assembly, Characterization, and Electrical Properties. *Langmuir* **2011**, 27 (7), 3600-3610

(40) Ranganathan, S.; McCreery, R. L. Electroanalytical performance of carbon films with near-atomic flatness. *Anal Chem* **2001**, 73 (5), 893-900

(41) Takahashi, S.; Kuroyama, Y.; Sonogashira, K.; Hagihara, N. A Convenient Synthesis of Ethynylarenes and Diethynylarenes. *Synthesis* **1980**, (8), 627-630

(42) Janecek, E. R.; Rauwald, U.; del Barrio, J.; Cziferszky, M.; Scherman, O. A. A Facile Route to Viologen Functional Macromolecules through Azide-Alkyne [3+2] Cycloaddition. *Macromol Rapid Comm* **2013**, 34 (19), 1547-1553

(43) Haiss, W.; Lackey, D.; Sass, J. K. Atomic resolution scanning tunneling microscopy images of Au(111) surfaces in air and polar organic-solvents. *J. Chem. Phys.* **1991**, 95, 2193-2196