

Recent progress in bio-inspired biofilm-resistant polymeric surfaces

Cristina Cattò¹, Federica Villa¹ and Francesca Cappitelli^{1*}

¹*Department of Food Environmental and Nutritional Sciences, Università degli Studi di Milano, Milano, Italy*

*Corresponding author: e-mail: francesca.cappitelli@unimi.it

Any surface of human interest can serve as a substrate for biofilm growth, sometimes with detrimental effects. The social and economic consequences of biofilm-mediated damage to surfaces are significant, the financial impact being estimated to be billions of dollars every year. After describing traditional biocide-based approaches for the remediation of biofilm-affected surfaces, this review deals with more recent developments in material science, focusing on non-toxic, eco-sustainable nature-inspired biomaterials with anti-biofilm properties superior to the conventional biocide-based approaches in terms of addressing the biofilm problem.

Keywords: anti-biofilm, bio-hybrid materials, coatings, natural molecules, polymers

Introduction

Any surface of human interest can serve as a starting ground for biofilm development, limiting material application and increasing health risks and costs. The inclination of microorganisms to become surface bound is ubiquitous, suggesting that surface dwellers have a strong survival and/or selective advantage tendency greater than their free-floating counterparts, i.e. a certain degree of shelter and homeostasis that helps them persist in the environment (Dunne, 2002).

On the global scale, biofilm-related costs incur the spending of billions of dollars in different sectors of the economy including all clinical and industrial settings associated with surfaces (Plyuta et al. 2013). Most likely, the worst biofilm reputation belongs to biofilm associated with the medical and healthcare sectors, because they are responsible for more than 60% of all microbial infections in humans (Sadekuzzaman et al. 2015). Indeed, implantable medical devices applied to critically ill patients often become potential surfaces for biofilm formation, with devastating medical implications in terms of patient morbidity, mortality, prolonged hospitalization and increased healthcare costs (Hall-Stoodley et al. 2004; Darouiche 2007; Lo et al. 2014; Percival et al. 2015; Tenke et al. 2017).

The detrimental effects of biofilm can also be felt across numerous industries, including water treatment and distribution, food processing and marine-based industries. The result is a decrease in industrial productivity as well as the physical deterioration of industrial systems such as pipe plugging and corrosion (Stowe et al. 2011). In food-processing environments, biofilms are of special importance as they have the potential to act as a persistent source of microbial contamination, which can lead to the threatening of the microbiological quality and safety of food products, resulting in food-borne disease (Cappitelli et al. 2014). Approximately 95% of bacterial cells that grow in drinking water networks are attached to pipe walls, while less than 5% has been found in the water phase (Flemming 2002; Douterelo et al. 2016). Detrimental effects include microbe-induced corrosion, disinfectant depletion, color, odor and taste degradation and the microbiological deterioration of drinking water (Farkas et al. 2013).

Biofilm also affects the surface of buildings and monuments, both historic and modern (Polo et al. 2012; Villa et al. 2016; Vázquez-Nion et al. 2018). As a consequence of complex interactions within the microbial community and its substrate biodeterioration processes occur (Giacomucci et al. 2011; Cappitelli et al. 2012). The consequences are aesthetic and structural damage.

Historically, most strategies that attempt to mitigate the effects of biofilm focus on treatments aimed at killing the microbial cells in biofilm already present on solid surfaces. However, such strategies have limited efficacy owing to bacterial persistence and resistance in pre-formed biofilm (Feng et al. 2015). Indeed, sessile bacteria exploit features that make them up to 1,000-fold more resistant to antibiotic and biocide treatments than their corresponding planktonic counterparts (Stewart 2002). *In vitro* experiments have shown that young, less dense biofilm is more easily cleared away by antibiotic treatment than mature thicker biofilm (Stewart 2015). However, early diagnosis of biofilm infection is currently difficult, and most biofilm infections are caused by matured biofilm, thus making it difficult to eradicate them with antibiotic treatments (Wu et al. 2015). Additionally, biofilm treatment is hindered by the dramatic increase in antibiotic resistance among pathogens, reducing the possibility of treating infections effectively and increasing the risk of complications and a fatal outcome.

No less important are chemical treatments that often involve considerable amounts of potentially dangerous substances. Sooner or later biocides and antibiotics are released into the environment and, if they do not break down into safer constituent

parts, they persist intact over prolonged periods of time, raising severe environmental and human risks (Young et al. 2008; Schultz et al. 2011; Sousa et al. 2014). This is readily seen in the growing number of policies, directives, technical reports, strategies, recommendations and regulatory decisions designed to reduce the consumption of antimicrobial agents, ensuring their prudent use, and protect human and animal health and wellbeing (Directive 98/8/EC; Council Recommendation 2002/77/EC; SCENIHR report 2009; EFSA Summary Report 2012).

With regard to the severe adverse impact of biofilm on many human activities, this review provides an overview of current and advanced strategies employed to control and prevent unwanted biofilm on polymeric surfaces in recent years. Materials and coatings with antibacterial activity, as well as more recent biofilm resistant solutions based on non-toxic natural molecules, including advantages and disadvantages with respect to potential applications, are discussed (Tables 1 and 2). Finally, methods for assessing anti-biofilm performance of innovative polymeric surfaces are presented.

Surface modification

The resistance of biofilm cells to traditionally used antimicrobial agents has prompted researchers to focus on preventive strategies rather than on attempts that remove or kill microorganisms. The development of materials that can resist or prevent bacterial adhesion constitutes the most promising and emerging approach to deal with material-associated biofilm infection problems (Alves and Pereira 2016). These approaches aim at altering the polymer surface by using passive or active strategies that discourage microbial adhesion and thus biofilm formation (Coenye et al. 2011).

Passive surfaces

In passive strategies, the physiochemical properties of an existing material, such as composition, charge, hydrophobicity, roughness and porosity, are modified so as to minimize microbial adhesion upon contact, without releasing biocidal agents into the surrounding environment (Gbejuade et al. 2015; Romanò et al. 2015). These coatings are called passive, because their effect is not attributed to antimicrobially active functional groups.

Surface chemistry modifications

In the past, poly(-ethylene oxide) (Johnston et al. 1997; Roosjen et al. 2003; Roosjen et al. 2005), poly(ethylene glycol) (Holmberg et al. 1993; Park et al. 1998; Kingshott et al. 2003; Tedjo et al. 2007; Saldarriaga Fernández et al. 2007) and hydrophilic polyurethanes (Jansen et al. 1993; Nagel et al. 1996) were used extensively as passive coatings to increase surface protection against biofilm formation. Indeed, these anti-adhesive coatings reduce the adhesion force between the bacteria and the solid surface, enabling easy removal of bacteria before the formation of surface biofilm (Adhart et al. 2018).

These strategies are relatively simple and economic ways to counteract microbial colonization. However, despite their popularity in the academic literature, few commercially marketed biomedical coatings are available, perhaps due to the difficulties in creating surface-bound thin films amenable at industrial scale (Sjollema et al. 2018).

Additionally, these passive coatings have been shown to reduce the adhesion of bacteria and yeast *in vitro*, but after exposure to physiological fluids *in vitro* or *in vivo*, the reduction in microbial adhesion is usually small or soon lost (Roosjen et al. 2005; Saldarriaga Fernández et al. 2007). The anti-biofilm properties of the coating are quickly masked by an adsorbed conditioning film of bacteria-produced proteins that diminishes its effectiveness (Hetrick and Schoenfisch 2006) whereas coating degradation can also occur (e.g. hydrolysis, chain cleavage, surface removal) (Saldarriaga Fernández et al. 2007). Furthermore, surfaces that are non-adhesive to bacteria are often non-adhesive to tissue cells as well, making them less suitable for biomaterial implants and devices requiring tissue integration (Sjollema et al. 2018). Finally, the introduction of additional chemical species decreases biocompatibility (Dickson et al. 2015).

Surface topography modifications

Modification of surface topography with micro- and nanoscale features that minimize bacterial attachment is another passive strategy for preventing biofilm formation on abiotic surfaces. Indeed, surfaces with topographic features of dimensions much smaller than microbial cells, in the sub-micrometer or nanometer range, have been reported to inhibit attachment by reducing the contact area between bacteria and the surface (Hsu et al. 2013).

An interesting development in this area is the recognition that nature has developed numerous surfaces with highly optimized nanoscale topography able to minimize microbial attachment. Therefore, many studies have attempted to mimic the peculiar surfaces found in nature. Carman et al. (2006) developed engineered microscale surface design inspired by the topography of shark skin (with features 2 μm wide, 3 μm in height) able to disrupt biofilm formation on patterned poly(dimethylsiloxane) elastomer without the use of biocidal agents. Regularly spaced nanopillar structures, similar to those found on the bactericidal cicada wings, were reproduced on a black silicon surface by Ivanova et al. (2013) with optimal bactericidal effect against both Gram-positive and Gram-negative bacteria. A superhydrophobic and biocompatible micro/nano structure gecko skin-like surface with low adhesion, anti-wetting, self-cleaning and antibacterial properties has been developed by Watson et al. (2015) and Li et al. (2016). Other examples of bio-inspired surfaces with effective anti-adherence nanoscale feature include those resembling rose petals, lotus leaves, taro leaves, rice leaves and legs of water striders (Claudia et al. 2016; Barthlott et al. 2017).

According to these researchers, bacterial cells are killed through the mechanical rupture of their cell wall when they are in contact with the nanostructures (Tripathy et al. 2017). Therefore, recruitment of additional cells and biofilm build up are both prevented and resistance to the nanofeatures cannot evolve (Dickson et al. 2015).

Unfortunately, these discoveries have not been translated to technologically scalable processes yet. Indeed, most of nanostructuring methods available today require cleanroom technologies and are prohibitively expensive, slow and cumbersome for large-scale applications (Feng et al. 2015; Hasan et al. 2018). Additionally, although most studies have shown that biofilms are sensitive to nanoscale topographical details, no universal rules of attachment have been determined yet and some researchers have reported a greater level of attachment on some nanoscale surfaces compared to those with conventional topographies (Park et al. 2008; Hsu et al. 2013).

Active antimicrobial surfaces

In active approaches, the abatement of biofilm growth has been achieved by spreading a number of antimicrobials and disinfectants onto the surfaces or by incorporating them into synthetic polymer-based products, directly or by means of a

carrier. The anti-biofilm activity is the result of functional groups that interact with microbes in the surrounding area (Lichter et al. 2009).

Antimicrobial-releasing surfaces

In the antimicrobial-releasing surfaces, the biocidal agent is actively eluted from the surface when in contact with an aqueous environment (Coenye et al. 2011; Chen et al. 2013; Lo et al. 2014; Zanini et al. 2015). Such approaches are those most used to obtain devices with different antimicrobial spectra and duration. Indeed, a number of materials with entrapped antibiotics and disinfectants are commercially available, and are already used in clinical applications, especially for mitigating implant-associated infections (Antoci et al. 2008; Hockenhull et al. 2009; Francolini and Donelli 2010; Swartjes et al. 2015; Ashbaugh et al. 2016). Examples of active polymers for antimicrobial applications are reported in Gao et al. (2011), Chen et al. (2013) and Huang et al. (2016).

Release of antibiotics by coating degradation is also possible by using degradable polymers, such as poly(D,L-lactide), poly(ϵ -caprolactone) or poly(trimethylene carbonate) (Strobel et al. 2011; Guillaume et al. 2012). Shukla et al. (2012) found that application of vancomycin containing layer-by-layer assembled films increased drug loading by up to approximately 9 times the control. It is interesting to note that the approach enables the incorporation of different drug types in each layer, giving potential to engineered delivery system for drugs with a multitude release profile (Hammond 2012).

However, despite the considerable effort made, over the past 30 years there has been little progress, few products have become available on the market, and reviews are not unanimous about their benefits (Johanson et al. 2006; Nowatzky et al. 2012; Sjollem et al. 2018). The prerequisite for the good performance of such coatings is the continuous and constant elution of antimicrobial molecules from the surface, with a release rate sufficient to deter or slow down microbial attachment to ensure the long service life of the coating (Barrios et al. 2005). Unfortunately, such active coatings have been designed to release high initial fluxes of antimicrobial agents during the critical short term post-implantation period (several hours) so as to inhibit initial microbial adhesion through a biocidal mechanism. However, continued release beyond this short-term period (weeks to months) is not realized, making these systems less desirable for

long-term and extended applications (Hetrick and Schoenfisch 2006; Knetsch and Koole 2011; Gao et al. 2011).

Antimicrobial responsive surfaces

Several materials from which the antimicrobial substance release is triggered by the microorganisms approaching the surface have been proposed. Indeed, in such responsive approaches, both enzymes and acids excreted by the bacteria themselves have been used as triggers for antimicrobial release to combat their adhesion.

Komnatnyy et al. (2014) introduced an enzyme-sensitive link into a poly(ethylene glycol) material. The bioactive compounds, i.e. quorum sensing signals and antimicrobial drugs, were only released in presence of the microorganisms that secrete the specific enzymes that cleave the sensitive linkage in the construction. Pavlukhina et al. (2014) constructed a pH/bacteria-responsive material providing a novel hydrogel-like montmorillonite/polyacrylic acid film able to keep gentamicin safely sequestered for months under physiologic conditions. When challenged with bacteria, the coating released gentamicin because microorganisms locally acidify the environment, e.g. by secreting lactic or acetic acid. Similarly, Wang et al. (2017) developed a new multilayer film with a high loading capacity for triclosan. In this system, the permeability of the films is altered in response to pH changes in the environment caused by bacteria providing the release of the antibiotic.

These responsive materials are supposed to provide new antimicrobial approaches with the following advantages: i) they exhibit the antibacterial activity only when and where needed; ii) they extend the useful life time of coatings, decreasing the premature depletion of the drug reservoir; and iii) they minimize side-effects related to continuous and uncontrolled molecule release, e.g. its accumulation in vital tissues.

Though these materials are interesting, they are seldom used as antibacterial coatings. The main challenges are: i) to achieve release of meaningful doses over multiple cycles; ii) to minimize non-triggered background leaching from surfaces; iii) the limited effect against multiple microbial infections; and iv) the altered efficacy of many antimicrobials due to changes in pH during microbial growth (Cloutier et al. 2015; Alvarez-Lorenzo et al. 2016).

Immobilization of antimicrobials

Important achievements have also been made to covalently immobilize antimicrobials on surfaces to completely overcome the problem of constant release (Antoci et al. 2008; Gharbi et al. 2015; Gerits et al. 2016; Peng et al. 2017). These so-called contact-killing surfaces are not intended to release antimicrobials into the surroundings, but to kill bacteria upon contact.

The active molecule, covalently bound to the polymeric chain, reaches the site of action on the bacterial envelope or inside the bacterium, e.g. by penetrating its cell wall. Therefore, the bond with the surface is generally performed by using flexible spacers that allow a certain degree of freedom of the bound antibacterial agents (Nie et al. 2016). Indeed, chain length and chain density are important parameters for polymer brush anchors (Adhart et al. 2018). Jose et al. (2005) used a double aminoethoxyethoxyacetate linker combined with a 3-aminopropyltriethoxysilane-modified titanium surface to provide vancomycin with a distance of about 4 nm from the polymer surface.

In contrast to the release coatings, surface binding technology of antibiotic agents creates a high local concentration, minimizing the risk of exposing bacteria to sub-inhibitory concentrations and thereby reducing the likelihood of resistance development (Nie et al. 2016). Little is known about the possible development of bacterial resistance against these materials and it remains to be seen whether or not this occurs upon their increasing usage. Certainly, it has been well documented that the constant use of antimicrobial agents inevitably leads to the development of antibiotic resistant strains and could even promote biofilm formation (Hoffman et al. 2005; Andersson and Hughes 2010). Moreover, the effectiveness of such material is most likely limited to infections caused by bacteria that are sensitive to the specific antibiotic (Hetrick and Schoenfisch 2006). No less important: the application of such surface-active systems is restricted to some surfaces for safety reasons, e.g. their use is less suitable for specific food contact materials as the carrying over of antimicrobials into food products might occur (Simões et al. 2010; Lucera et al. 2012; Cappitelli et al. 2014).

Metal-based antimicrobial materials

Metal coatings

Heavy metals have been used as an anti-biofilm agent, the metal being deposited on biomaterial surfaces by means of a coating technology (Stobie et al. 2008; Gallo et al. 2014).

Among the metals, the one that has long been the center of attention is silver (Knetsch and Koole 2011). There are indications that the antimicrobial activity of silver is dependent on the silver cation Ag^+ , which reacts with, and disrupts, the function of bacterial cell membranes, DNA molecules, crucial metabolic proteins and enzymes, and ultimately leads to cell death (Feng et al. 2000; Jung et al. 2008; Randall et al. 2013). Indeed, silver has been coated onto medical implants (Darouiche 1999; Devasconcellos et al. 2012), wound dressings (Heggens et al. 2005; Ip et al. 2006) and textiles (Sataev et al. 2014). However, such silver coating has its faults, including poor silver adhesion and lack of coating uniformity; it also requires special processing conditions (Kumar and Munstedt 2005). Furthermore, the incorporation of silver into polymers does not always result in efficient antimicrobial activity because of the poor solubility of most silver salts in polymeric materials (Knetsch and Koole 2011).

Metal-nanoparticles based materials

Over the last decade a great deal of interest has been shown in metal nanoparticles. This is because of the superior and unique features that make them particularly attractive for new and emerging nanoparticle-based anti-biofilm materials (Polo et al. 2011; Ahire et al. 2016; Mu et al. 2016; Qayyum and Khan 2016; Ramasamy and Lee 2016; Gambino et al. 2017). Among others, silver nanoparticle-based materials have been successfully proposed to limit biofilm formation on both medical and industrial applications, e.g. medical implants (Roe et al. 2008), air and water treatment filters (Mpenyana-Monyatsi et al. 2012; Gehrke et al. 2015), clothing (Zhang et al. 2009; Zhang et al. 2014), food processing surfaces (Araujo et al. 2013) and food packaging materials (Bumbudsanpharoke et al. 2015; Souza and Fernando 2016). Although it seems that bacteria are less prone to develop resistance against silver than they do against conventional antibiotics, concerns associated with the overuse of silver and the consequent emergence of bacterial resistance have been raised (Hobman and

Crossman 2015; Ebrahiminezhad et al. 2016). Moreover, these nanotechnology-based emerging novel anti-biofilm strategies are still in the nascent phase and more research is needed to clarify a number of safety, environmental, ethical, policy and regulatory issues (Fabrega et al. 2011; Gottschalk et al. 2013; Sajid et al. 2015; Gambino et al. 2015; Reed et al. 2016; Garuglieri et al. 2016; Hoseinnejad et al. 2017; Garuglieri et al. 2018).

Preventive green biocide-free surfaces

Numerous concerns have put pressure on the scientific community to develop alternative, more effective strategies; strategies perceived by the public as safe, and as posing negligible risk to human health and the environment.

Indeed, efforts are being directed towards developing innovative anti-biofilm materials with functional features targeting molecular determinants of biofilm genesis, instead of fighting biofilm with antimicrobial materials and coatings (Chen et al. 2013; Villa et al. 2013). In these approaches microorganisms are deprived of their virulent properties but their existence remains unaffected. Thus, selection pressure decreases, with the promising perspective of restoring the efficacy of traditional antimicrobial agents (Rasko and Sperandio 2010).

On considering the process of biofilm formation, different key steps can be identified as promising targets for the development of innovative anti-biofilm products. The first is to avoid surface microbial adhesion: this can be done by interacting with the surface sensing process in order to keep the pioneering cells in a planktonic form. Another good point of attack that has emerged is the disruption of mature biofilm. Indeed, interference with cell-to-cell communication processes inevitably results in biofilm matrix damage, leading to the destabilization of biofilm physical integrity. Finally, the promotion of biofilm dispersal by forcing the planktonic state is another interesting target (Kaplan 2010; Kostakioti et al. 2013).

Needless to say, the above strategies do not presume to be the solution to preventing biofilm development, but they could be used in combination with other conventional treatments to maximize the anti-biofilm performance of polymeric materials. Indeed, these strategies could be a step forward in applications where it would be advantageous to slow down contamination. Indeed, in many industrial and clinical activities, surface treatments that retard adhesion, and consequently biofilm

formation, could greatly enhance the efficiency of daily cleaning and disinfection procedures, because, once dispersed from the biofilm, free-floating microbes are more susceptible to detergents and biocides than those in the biofilm itself (Davey and O'Toole 2000; Dell'Orto et al. 2017). The synergic combination of antimicrobial and anti-biofilm agents is even recommended by the Infectious Diseases Society of America guidelines for the treatment of selected biofilm-associated infection (Pappas et al. 2004; Cui et al. 2015).

Already, to date, a number of natural and synthetic compounds based on this innovative biocide-free anti-biofilm strategy have been proposed. The latter includes a broad range of molecules, free in solution as well as coated or immobilized on a surface, that interfere with quorum sensing cell-to-cell communications and promote biofilm dispersal (Ding et al. 2011; Wu et al. 2015; Alexander et al. 2015; Brackman and Coenye 2015; Abraham 2016; Chen et al. 2016), as well as matrix-targeting enzymes able to effectively destroy biofilm architecture (Pavluhina et al. 2012; Villa et al. 2015; Spadoni Andreani et al. 2016; Sadekuzzaman et al. 2015; Meireles et al. 2016; Spadoni Andreani et al. 2017; Snarr et al. 2017).

Surface modification with natural anti-biofilm compounds

Present day awareness of ecological problems, together with the increased number of safety laws, has prompted the scientific community to address the development of more eco-sustainable anti-biofilm materials with non-toxic and biodegradable properties. Thus, there is great demand for new approaches based on molecules displaying suitable environmental-fate parameters such as high water solubility, low partition coefficient, low bioaccumulation in biological systems, and no ecotoxicity; such molecules used in anti-biofilm materials would give them great potential as safe anti-biofilm agents (Qian et al. 2010). To date, a multitude of compounds found in nature have revealed promising anti-biofilm properties suitable for the development of improved effective eco-friendly, bio-inspired anti-biofilm materials able to replace, or integrate with, current dominating biocide-based strategies (Villa et al. 2013; Sadekuzzaman et al. 2015; Qian et al. 2015; Almeida et al. 2017). However, compared to the great amount of work devoted to the discovery of potent natural biofilm inhibitors, relatively little research has dealt with the design of anti-infective

bio-hybrid surfaces based on natural products and, of these, only a few materials display anti-biofilm properties without biocidal activity.

Passive and active natural molecule-based strategies

Barrios and coauthors (2005) and Newby and colleagues (2006) incorporated zosteric acid into silicone coatings, developing different strategies to achieve its slow release into the surrounding area. Bryers and collaborators (2006) and Rosenberg and colleagues (2008) proposed salicylic acid-releasing poly(anhydride-ester) polymers able to inhibit *Pseudomonas aeruginosa* and *Salmonella enterica* biofilms respectively. In a further study, Nowatsky and coauthors (2012) developed a new salicylic acid-releasing polyurethane acrylate polymer. Under aqueous environments, the polymer hydrolyzed and released salicylic acid, leaving the backbone intact and reducing biofilm formation of *Staphylococcus epidermidis*, *Bacillus subtilis*, *Escherichia coli*, *P. aeruginosa*, and *S. aureus*. Others examples are reported in Table 2.

Unfortunately, in most cases, these materials exhibited a discontinuous release, this release being initially high but soon followed by an exponential decrease. In addition, a very large number of molecules appeared close to the surface, reaching concentrations lethal for the microorganisms. The amount of released substance and its rate is influenced by factors like processing parameters, loading dose, applied technique, molecular size of the molecule and the physic-chemical properties of the polymeric material, all of which makes it arduous to carry out a strict monitoring of the anti-biofilm rate from the surface. Indeed, the problem of release rate in an aqueous medium can be attributed to the fact that most polymeric matrices and anti-biofilm compounds have incompatible physical characteristics. Most of the coating matrices are hydrophobic polymers, while some anti-biofilm compounds are hydrophilic, making their miscibility with the coating matrices difficult. The result is a non-uniform molecule distribution within the material, which increases the tendency of the surfaces to absorb and diffuse water through the polymer matrix; this allows the anti-biofilm molecules to diffuse out (Barrios et al. 2005; Newby et al. 2006; Nowatzki et al. 2012). To solve the problem, Barrios and coauthors (2005) investigated various techniques for incorporating zosteric acid into a model silicone material. When the zosteric acid distribution within the polymer was uniform, with small aggregates or even individual molecules, leaching took place at a reasonable rate, extending the material working

time. However, the optimal, and desired, constant rate was never reached as, at the beginning, the rate was quite high, reaching an almost constant value only later.

Covalent immobilization of natural molecules

The binding of natural molecules to surfaces could easily side-step the problem of constant release, guaranteeing the material long life as the molecules become permanently attached and integrated into the scaffold structure of the polymers. Indeed, grafting active compounds to polymers is preferred to covalent incorporation as biofilm development is a process that occurs at the surface and not in the bulk. This kind of approach requires very good knowledge of the exact functional groups required by molecules to exert anti-biofilm activity, identifying the molecular structure's binding site needed for the group's immobilization on the surface, without destroying the biological activity of the material. However, in most cases this information is not available. Hume et al. (2004) proposed two different methods for the covalent immobilization of the furanone 3-(1'-bromohexyl)-5-dibromomethylene-2(5H) on biomaterials: a furanone co-polymerization with a styrene polymer and a plasma-1-ethyl-3-(dimethylaminopropyl) carbodiimide reaction to produce furanone-grafted catheters. Biofilm formation by *S. epidermidis in vitro* was inhibited by 80% whereas in an *in vivo* sheep model immobilized furanones were found effective at controlling infection for up to 65 days. A study by Cattò et al. (2015) concerning the relationship between zosteric acid structure and anti-biofilm activity clarified that the carboxylic acid moiety conjugated to the double bond in trans configuration is necessary in the molecule to guarantee good anti-biofilm performance, while deletion of the sulphate ester group does not compromise molecule anti-biofilm activity. In addition, Cattò et al. (2017) showed that the para-position of the phenyl ring in the salicylic acid structure proved suitable for its immobilization on a N-hydroxysuccinimide polymeric matrix. On the basis of these two studies, Dell'Orto et al. (2017) covalently grafted modified cinnamic and salicylic acid on a low density polyethylene surface, previously activated by oxygen plasma treatment and using 2-hydroxymethylmetacrylate as linker. Both functionalized polymers displayed optimal anti-biofilm performance against *E. coli*, reducing biofilm surface coverage, thickness and cellular biovolume by more than 80%. Cattò et al. (2018) later confirmed that the reduction of biofilm biomass was achieved in both functionalized surfaces by a mechanism that did not affect bacterial viability,

which is an important factor in the challenge to limit the risk of developing resistant microbial strains. Additionally, the authors demonstrated that the functionalized surfaces strongly reduced polysaccharides in the biofilm matrix, maximizing the biofilm sensitivity to conventional antimicrobial agents. Noteworthy, the new polymers preserved their anti-biofilm activity over time.

Although anti-biofilm mechanisms are still poorly understood, current findings document that, in most cases, anti-biofilm materials affect microbial settlement by acting as an environmental cue that leads bacteria to global stress, providing conditions by which the best microbial strategy is to escape from the adverse environment rather than activate drug resistant sessile mechanisms. This response is often mediated by reactive oxygen species, used by cells as signals in adapting to changing environments (Gambino and Cappitelli 2016). For example, both zosteric acid and salicylic acid affect the bacterial oxidative balance by interacting with NADH: quinone reductase (WrbA), an enzyme belonging to a family of flavoprotein quinone reductases widespread in both bacteria and fungi (Cattò et al. 2015; Cattò et al. 2017). The outcome of this oxidative imbalance is the production of signal molecules that discourage the firm adhesion of bacteria on surfaces (Villa et al. 2012; Cattò et al. 2015).

Methods for evaluating the anti-biofilm performance of new bio-inspired polymeric surfaces

After the design and creation of bio-inspired polymeric surfaces, the validation of the new materials' anti-biofilm performance becomes a critical step for field applications. However, the *in vivo* testing of new anti-biofilm materials remains a difficult task due to the poor control over experiments and justified ethical concerns (Sjollema et al. 2018). Therefore, simplified *in vitro* systems have been developed to mimic different conditions encountered *in vivo* (Gomes et al. 2017).

While a number of industrial standard tests are available to assess the antimicrobial efficacy of medical and non-medical products, no accepted standard methods exist to properly evaluate the anti-biofilm activity of new surfaces with a mechanism of action that is different from simple killing or growth inhibition. Indeed, available surface evaluation standard tests are mostly intended to assess the efficacy of surface by testing the material ability to decrease microbial viability without considering differences in the mechanism of action (Sjollema et al. 2018). Therefore,

the only way to test is by adapting the standard lab-scale devices and procedures to reproduce the biofilms on the functionalized biocide-free materials.

Lab-scale systems for growing biofilms on anti-biofilm surfaces

The simplest experimental system relies on the use of microtiter well plates, a static assay particularly useful for examining early events in biofilm formation (Merritt et al. 2005). Microtiter plates allow surfaces to be modified or, alternatively, new bio-functionalized polymers can be further inserted into the wells. The general protocol allows for the inoculation of microtiter wells with a cell suspension for a desired period of time, after which the attached biomass is analyzed.

While microtiter tray based techniques are inexpensive and appropriate for large scale screening purposes, the static nature of these systems leaves them prone to nutrient exhaustion, thus limiting the generation of mature biofilm (Azeredo et al. 2017). As a consequence, the full effect of new tested materials on biofilm growth and dispersion cannot be evaluated with this system.

The dynamic solution lies in continuous-flow systems to produce mature biofilms on surfaces. Indeed, continuously pumping high shear and nutrients into the reactor provides stress conditions that promote biofilm development on the polymer surfaces (Goeres et al. 2005). Standardized protocols employing the Center for Disease Control biofilm reactor (CDC reactor), the rotating disk reactor (RD reactor) and the drip flow reactor (DF reactor), have been approved by the American Society for Testing and Materials (ASTM E2562-12 2012; ASTM E2196-02 2012; ASTM E2871-13 2013; ASTM E2647-13 2013).

The CDC reactor allowed Cai et al. (2012) to prove that diazeniumdiolate-doped poly(lactic-co-glycolic acid)-based nitric oxide releasing films applied in indwelling biomedical devices exhibit considerable anti-biofilm properties against gram-positive *S. aureus* and gram-negative *E. coli*. In another experiment, the CDC reactor was used to challenge dentin-composite and hydroxyapatite disks with multi-species oral biofilms, mimicking acidogenic meals and snacks (Li et al. 2014). Dell'Orto and colleagues (2017) tested a new anti-biofilm material obtained by the covalent grafting of *p*-aminocinnamic or *p*-aminosalicylic acids on low density polyethylene coupons against *E. coli* biofilm grown in the CDC reactor. Sawant and colleagues (2013) tested the anti-biofilm properties of silver nanocomposites against *E. coli* biofilm by the use of a DF

reactor. With the same device, Pérez-Díaz et al. (2016) evaluated the anti-biofilm capacity of chitosan gel formulations loaded with silver nanoparticles on strains of clinical isolates under conditions that mimic the flow of nutrients in the human skin.

All the described continuous-flow systems offer the advantages of the simultaneous use of different surface materials, the possibility of analyzing samples noninvasively, and standardized protocols, making it possible to compare different materials within one laboratory alone and among different laboratories (Gomes et al. 2017). Additionally, bioreactors allow to sample the materials aseptically at different time points during the sessile growth, without compromising the whole experiment.

Methods for quantification and structural assessment of biofilm on anti-biofilm surfaces

Once grown on a surface, the most widely used technique to estimate biofilm is the determination of viable cells by plate counting on agar media (Azeredo et al. 2017). Alternatively, flow cytometry, is a fast and precise way to count live and dead cells in a biofilm (Kerstens et al. 2015; Sgier et al. 2016). Quantification can be also achieved through colorimetric methods by staining biofilms and measuring the amount of desorbed dye by spectrophotometric measurement (Honraet et al. 2005; Welch et al. 2012; Larimer et al. 2016; Sabatini et al. 2018). Depending on the stain, this method enables quantification of the total biofilm biomass (e.g., crystal violet), the biofilm matrix (e.g. dimethyl methylene blue), or the metabolic activity of the biofilm cells (e.g. XTT 2,3-bis-(2-methoxy-4-nitro-5-sulfophenyl)-2H-tetrazolium-5-carboxanilide inner salt and resazurin). Furthermore, quantitative polymerase chain reaction (qPCR) could be used to account for the uncultivable portion of the biofilm microbial community (Dalwai et al. 2007).

Microscopy is one of the most powerful tools to assess the biofilm architecture on material surfaces. In particular, confocal Laser Scanning Microscopy (CLSM) allows the representation of the 3D architecture of the biofilm, and the acquisition of quantitative structural parameters such as biofilm bio-volume, thickness and roughness (Bridier and Briandet 2014) (Figure 1).

The amount of biomass retrieved on the surface is not the only indication of the anti-biofilm properties of a new material. In fact, functionalized materials might act by destabilizing biofilm organization and its physical integrity, compromising its structure

rather than decreasing the biomass on a surface (Villa et al. 2015). This mode of action might render the biofilm more prone to detachment and/or more susceptible to traditional antimicrobial agents. By using micro-bead force spectroscopy, it is possible to quantify biofilm adhesion and viscoelasticity at the micro-meter scale (Lau et al. 2009; Angeloni et al. 2016). Additionally, Atomic Force Microscopy was used to determine the adhesion forces between bacteria and goethite (Huang et al. 2015), and between biofilms and different plastics (vinyl chloride, silicone resin, Nylon 66, polycarbonate, polypropylene, polyethylene and polymethylmethacrylate) (Harapanahalli et al. 2015; Hirai et al. 2015).

The susceptibility of biofilms grown on functionalized materials to traditional antimicrobials is an important aspect to consider. In this respect, CLSM has been shown to be a powerful tool to analyze antimicrobial actions by a time course (minutes-to-hours scale) visualization of live and dead cells through the biofilm structure during a biocidal treatment (Rani et al. 2005; Daddi Oubekka et al. 2012; Singh et al. 2016). The general protocol consists in staining biofilm grown on the coupon with specific fluorochromes in order to detect live and dead cells (e.g. LIVE/DEAD BacLight bacterial viability kit) or enzymatic activities (e.g. esterase activity marker CalceinAM). The biofilm is then exposed to the antimicrobial treatment, and any changes over time in fluorescent intensity due to cell inactivation are recorded under CLSM (Figure 2 and Video S1).

Concluding remarks

The use of surfaces that prevent or limit microbial adhesion and biofilm formation by depriving microorganisms of their biofilm-specific traits, without affecting their existence, has been proved instrumental in combating surface-associated biofilm. The integration of such innovative strategies with conventional approaches also appear to be a good strategy as, once the biofilm is destabilized, microorganisms are more sensitive to biocide treatments. Now, the hard part is to translate these ideas into commercial reality: although the value of the previously described research is indisputable, it is equally true that a number of issues have yet to be solved. In contrast to the currently used solvent-based approaches, the design and synthesis of such surface materials needs to be focused on chemical approaches based on solvent-free, non-toxic reactions, adhering to the principles of green chemistry (Sheldon, 2016). In addition, the

diffusion of a natural-based surface commercially requires large amounts of natural materials, as, unfortunately, not all compounds are suitable candidates for commercial total synthesis due to their structural complexity (Dias et al. 2012). Advances in chemoinformatics have partially filled previous gaps: high throughput screening has shortened times whereas structure-activity studies have permitted a drastic reduction in the size and chirality of bioactive natural products. However, these approaches are often limited by the general lack of information concerning the mechanism of action, the cellular receptors and the active chemical scaffold of many bioactive natural products. This understanding is also necessary to achieve more efficient and better targeted anti-biofilm surfaces (Chen and Qian 2017).

Acknowledgements

This work was supported by the Fondazione Cariplo under grant number 2011-0277.

Disclosure of interest

The authors report no conflicts of interest.

References

- Abraham WR. 2016. Going beyond the control of quorum-sensing to combat biofilm infections. *Antibiotics*. 5(1):3.
- Adlhart, Verran J, Azevedo NF, Olmez H, Keinänen-Toivola MM, Gouveia I, Melo LF, Crijns F. 2018. Surface modifications for antimicrobial effects in the healthcare setting: a critical overview. *J Hosp Infect*. [accessed 2018 Feb 2]. [DOI: 10.1016/j.jhin.2018.01.018].
- Ahire JJ, Hattingh M, Neveling DP, Dicks LMT. 2016. Copper-containing anti-biofilm nanofiber scaffolds as a wound dressing material. *PloS One*. 11(3): e0152755.
- Alexander SA, Kyi C, Schiesser CH. 2015. Nitroxides as anti-biofilm compounds for the treatment of *Pseudomonas aeruginosa* and mixed-culture biofilms. *Org Biomol Chem* 13(16):4751–4759.
- Almeida JR, Correia-da-Silva M, Sousa E, Antunes J, Pinto M, Vasconcelos V, Cunha I. 2017. Antifouling potential of nature-inspired sulfated compounds. *Sci Rep*. 7: 42424.

- Alvarez-Lorenzo C, Garcia-Gonzalez CA, Bucio E, Concheiro A. 2016. Stimuli-responsive polymers for antimicrobial therapy: drug targeting, contact-killing surfaces and competitive release. *Expert Opin Drug Deliv.* 13(8):1109–1119.
- Alves D, Pereira MO. 2016. Bio-inspired coating strategies for the immobilization of polymyxins to generate contact-killing surfaces. *Macromol Biosci.* 16(10):1450–1460.
- [ASTM] American Society for Testing and Materials. 2012. E2562-12 - Standard test method for quantification of *Pseudomonas aeruginosa* biofilm grown with high shear and continuous flow using CDC biofilm reactor.
- [ASTM] American Society for Testing and Materials. 2012. E2196-02 - Standard test method for quantification of a *Pseudomonas aeruginosa* biofilm grown with shear and continuous flow using a rotating disc reactor.
- [ASTM] American Society for Testing and Materials. 2013. E2871-13 - Standard test method for evaluating disinfectant efficacy against *Pseudomonas aeruginosa* biofilm grown in the CDC biofilm reactor using the single tube method.
- [ASTM] American Society for Testing and Materials. 2013. E2647-13 - Standard test method for quantification of *Pseudomonas aeruginosa* biofilm grown using drip flow biofilm reactor with low shear and continuous flow; 2013.
- Andersson DI, Hughes D. 2010. Antibiotic resistance and its cost: is it possible to reverse resistance? *Nat Rev Microbiol.* 8(4):260–271.
- Angeloni L, Passeri D, Reggente M, Pantanella F, Mantovani D, Rossi M. 2016. Microbial cells force spectroscopy by atomic force microscopy: a review. *Nanosci Nanometr.* 2(1):30–40.
- Antoci V, Adams CS, Parvizi J, Davidson HM, Composto RJ, Freeman TA, Wickstrom E, Ducheyne P, Jungkind D, Shapiro IM, et al. 2008. The inhibition of *Staphylococcus epidermidis* biofilm formation by vancomycin-modified titanium alloy and implications for the treatment of periprosthetic infection. *Biomaterials.* 29(35):4684–4690.
- Araujo EA, de Andrade NJ, da Silva LHM, Bernardes PC, Teixeira A, Fialho JFQ, de Sa JPN, Fernandes PE. 2013. Modification of stainless steel surface hydrophobicity by silver nanoparticles: strategies to prevent bacterial adhesion in the food processing. *J Adhes Sci Technol.* 27(24):2686–2695.

- Ashbaugh AG, Jiang XS, Zheng J, Tsai AS, Kim WS, Thompson JM, Miller RJ, Shahbazian JH, Wang Y, Dillen CA, et al. 2016. Polymeric nanofiber coating with tunable combinatorial antibiotic delivery prevents biofilm-associated infection *in vivo*. *Proc Natl Acad Sci U S A*. 113(45):E6919–E6928.
- Azeredo J, Azevedo NF, Briandet R, Cerca N, Coenye T, Costa AR, Desvaux M, Di Bonaventura G, Hebraud M, Jaglic Z, et al. 2017. Critical review on biofilm methods. *Crit Rev Microbiol*. 43(3):313–351.
- Barrios CA, Xu Q, Cutright T, Newby BM. 2005. Incorporating zosteric acid into silicone coatings to achieve its slow release while reducing fresh water bacterial attachment. *Colloids Surf., B*. 41(2–3):83–93.
- Barthlott W, Mail M, Bhushan B, Koch K. 2017. Plant surfaces: structures and functions for biomimetic innovations. *Nano-Micro Lett*. 9(2):23.
- Brackman G, Coenye T. 2015. Quorum sensing inhibitors as anti-biofilm agents. *Curr Pharm Des*. 21(1):5–11.
- Bridier A, Briandet R. 2014. Contribution of confocal laser scanning microscopy in deciphering biofilm tridimensional structure and reactivity. *Methods Mol Biol*. 1147:255–266.
- Bryers JD, Jarvis RA, Lebo J, Prudencio A, Kyriakides TR, Uhrich K. 2006. Biodegradation of poly(anhydride-esters) into non-steroidal anti-inflammatory drugs and their effect on *Pseudomonas aeruginosa* biofilms *in vitro* and on the foreign-body response *in vivo*. *Biomaterials*. 27(29):5039–5048.
- Bumbudsanpharoke N, Choi J, Ko S. 2015. Applications of nanomaterials in food packaging. *J Nanosci Nanotechnol*. 15(9):6357–6372.
- Cai WY, Wu JF, Xi CW, Meyerhoff ME. 2012. Diazoniumdiolate-doped poly(lactic-co-glycolic acid)-based nitric oxide releasing films as antibiofilm coatings. *Biomaterials*. 33(32):7933–7944.
- Cappitelli F, Polo A, Villa F. 2014. Biofilm formation in food processing environments is still poorly understood and controlled. *Food Eng Rev*. 6(1–2):29–42.
- Cappitelli F, Salvadori O, Albanese D, Villa F, Sorlini C. 2012. Cyanobacteria cause black staining of the National Museum of the American Indian Building, Washington,

DC, USA. *Biofouling*. 28(3):257–266.

Carman ML, Estes TG, Feinberg AW, Schumacher JF, Wilkerson W, Wilson LH, Callow ME, Callow JA, Brennan AB. 2006. Engineered antifouling microtopographies - correlating wettability with cell attachment. *Biofouling*. 22(1–2):11–21.

Cattò C, Dell'Orto S, Villa F, Villa S, Gelain A, Vitali A, Marzano V, Baroni S, Forlani F, Cappitelli F. 2015. Unravelling the structural and molecular basis responsible for the anti-biofilm activity of zosteric acid. *PLoS One*. 10(7):e0131519.

Cattò C, Grazioso G, Dell'Orto S, Gelain A, Villa S, Marzano V, Vitali A, Villa F, Cappitelli F, Forlani F. 2017. The response of *Escherichia coli* biofilm to salicylic acid. *Biofouling*. 33(3):235–251.

Cattò C, James G, Villa F, Villa S, Cappitelli F. 2018. Zosteric acid and salicylic acid bound to a low density polyethylene surface successfully control bacterial biofilm formation. *Biofouling*. [DOI: 0.1080/08927014.2018.1462342].

Chen L, Qian PY. 2017. Review on molecular mechanisms of antifouling compounds: an update since 2012. *Mar Drugs*. 15(9).

Chen LH, Bu QQ, Xu H, Liu Y, She PF, Tan RC, Wu Y. 2016. The effect of berberine hydrochloride on *Enterococcus faecalis* biofilm formation and dispersion *in vitro*. *Microbiol Res*. 186:44–51.

Chen M, Yu QS, Sun HM. 2013. Novel strategies for the prevention and treatment of biofilm related infections. *Int J Mol Sci*. 14(9):18488–18501.

Chifiriuc C, Grumezescu V, Grumezescu AM, Saviuc C, Lazăr V, Andronescu E. 2012. Hybrid magnetite nanoparticles/*Rosmarinus officinalis* essential oil nanobiosystem with antibiofilm activity. *Nanoscale Res Lett*. 7:209.

Claudia Z, Isabelle CRDS, Matthias M, Maryna NK, Wilhelm B, Hendrik H. 2016. Micro-structures of superhydrophobic plant leaves - inspiration for efficient oil spill clean-up materials. *Bioinspir Biomim*. 11(5):056003.

Cloutier M, Mantovani D, Rosei F. 2015. Antibacterial coatings: challenges, perspectives, and opportunities. *Trends Biotechnol*. 33(11):637–652.

Coenye T, De Prijck K, Nailis H, Nelis HJ. 2011. Prevention of *Candida albicans* biofilm formation. *Open Mycol J*. 5:9–20.

Council Recommendation 2002/77/EC (2001) Prudent use of antimicrobial agents in human medicine (2002/77/EC).

http://antibiotic.ecdc.europa.eu/PDFs/l_03420020205en00130016.pdf.

Cui JH, Ren B, Tong YJ, Dai HQ, Zhang LX. 2015. Synergistic combinations of antifungals and anti-virulence agents to fight against *Candida albicans*. *Virulence*. 6(4):362–371.

Daddi Oubekka S, Briandet R, Fontaine-Aupart MP, Steenkeste K. 2012. Correlative time-resolved fluorescence microscopy to assess antibiotic diffusion-reaction in biofilms. *Antimicrob Agents Chemother*. 56(6):3349–3358.

Dalwai F, Spratt DA, Pratten J. 2007. Use of quantitative PCR and culture methods to characterize ecological flux in bacterial biofilms. *J Clin Microbiol*. 45(9):3072–3076.

Darouiche RO. 1999. Anti-infective efficacy of silver-coated medical prostheses. *Clin Infect Dis*. 29(6):1371–1377.

Darouiche RO. 2007. Antimicrobial coating of devices for prevention of infection: principles and protection. *Int J Artif Organs*. 30(9):820–827.

Davey ME, O'Toole G A. 2000. Microbial biofilms: from ecology to molecular genetics. *Microbiol Mol Biol Rev*. 64(4):847–867.

Dell'Orto S, Cattò C, Villa F, Forlani F, Vassallo E, Morra M, Cappitelli F, Villa S, Gelain A. 2017. Low density polyethylene functionalized with antibiofilm compounds inhibits *Escherichia coli* cell adhesion. *J Biomed Mater Res A*. 105A:3251–3261.

Devasconcellos P, Bose S, Beyenal H, Bandyopadhyay A, Zirkle LG. 2012. Antimicrobial particulate silver coatings on stainless steel implants for fracture management. *Mater Sci Eng C Mater Biol Appl*. 32(5):1112–1120.

Dias DA, Urban S, Roessner U. 2012. A historical overview of natural products in drug discovery. *Metabolites*. 2(2):303–336.

Dickson MN, Liang EI, Rodriguez LA, Vollereaux N, Yee AF. 2015. Nanopatterned polymer surfaces with bactericidal properties. *Biointerphases*. 10(2): 021010.

Ding X, Yin B, Qian L, Zeng ZR, Yang ZL, Li HX, Lu YJ, Zhou SN. 2011. Screening for novel quorum-sensing inhibitors to interfere with the formation of *Pseudomonas aeruginosa* biofilm. *J Med Microbiol*. 60(12):1827–1834.

Directive 98/8/EC of the European Parliament and of the Council of 16 February 1998 concerning the placing of biocidal products on the market.

<http://eurlex.europa.eu/LexUriServ/site/en/consleg/1998/L/01998L000820070119-en.pdf>.

Douterelo I, Jackson M, Solomon C, Boxall J. 2016. Microbial analysis of in situ biofilm formation in drinking water distribution systems: implications for monitoring and control of drinking water quality. *Appl Microbiol Biotechnol.* 100(7):3301–3311.

Dunne WM. 2002. Bacterial adhesion: seen any good biofilms lately? *Clin Microbiol Rev.* 15(2):155–166.

Ebrahimezhad A, Raei MJ, Manafi Z, Jahromi AS, Ghasemi Y. 2016. Ancient and novel forms of silver in medicine and biomedicine. *JAMSAT.* 2(1):122–128.

[EFSA] European Food Safety Authority. 2012. Summary report.

<https://www.efsa.europa.eu/en/topics/topic/nanotechnology>.

Fabrega J, Luoma SN, Tyler CR, Galloway TS, Lead JR. 2011. Silver nanoparticles: behaviour and effects in the aquatic environment. *Environ Int.* 37(2):517–531.

Farkas A, Dragan-Bularda M, Muntean V, Ciataras D, Tigan S. 2013. Microbial activity in drinking water-associated biofilms. *Cent Eur J Biol.* 8(2):201–214.

Feng G, Cheng Y, Wang SY, Borca-Tasciuc DA, Worobo RW, Moraru CI. 2015. Bacterial attachment and biofilm formation on surfaces are reduced by small-diameter nanoscale pores: how small is small enough? *NPJ Biofilms Microbiomes.* 1:15022.

Feng QL, Wu J, Chen GQ, Cui FZ, Kim TN, Kim JO. 2000. A mechanistic study of the antibacterial effect of silver ions on *Escherichia coli* and *Staphylococcus aureus*. *J Biomed Mater Res.* 52(4):662–668.

Flemming HC. 2002. Biofouling in water systems - cases, causes and countermeasures. *Appl Microbiol Biotechnol.* 59(6):629–640.

Francolini I, Donelli G. 2010. Prevention and control of biofilm-based medical-device-related infections. *FEMS Immunol Med Microbiol.* 59(3):227–238.

Gallo J, Holinka M, Moucha CS. 2014. Antibacterial surface treatment for orthopaedic implants. *Int J Mol Sci.* 15(8):13849–13880.

- Gambino M, Ahmed M, Villa F, Cappitelli F. 2017. Zinc oxide nanoparticles hinder fungal biofilm development in an ancient Egyptian tomb. *Int Biodeterior Biodegradation*. 122:92–99.
- Gambino M, Cappitelli F. 2016. Mini-review: biofilm responses to oxidative stress. *Biofouling*. 32(2):167–178.
- Gambino M, Marzano V, Villa F, Vitali A, Vannini C, Landini P, Cappitelli F. 2015. Effects of sublethal doses of silver nanoparticles on *Bacillus subtilis* planktonic and sessile cells. *J Appl Microbiol*. 118(5):1103–1115.
- Gao P, Nie X, Zou MJ, Shi YJ, Cheng G. 2011. Recent advances in materials for extended-release antibiotic delivery system. *J Antibiot*. 64(9):625–634.
- Garuglieri E, Cattò C, Villa F, Zanchi R, Cappitelli F. 2016. Effects of sublethal concentrations of silver nanoparticles on *Escherichia coli* and *Bacillus subtilis* under aerobic and anaerobic conditions. *Biointerphases*. 11(4):04B308.
- Garuglieri E, Meroni E, Cattò C, Villa F, Cappitelli F, Erba D. 2018. Effects of sublethal concentrations of silver nanoparticles on a simulated intestinal prokaryotic-eukaryotic interface. *Front Microbiol*. 8:2698.
- Gbejuade HO, Lovering AM, Webb JC. 2015. The role of microbial biofilms in prosthetic joint infections. *Acta Orthop*. 86(2):147–158.
- Gehrke I, Geiser A, Somborn-Schulz A. 2015. Innovations in nanotechnology for water treatment. *Nanotechnol Sci Appl*. 8:1–17.
- Geiger T, Delavy P, Hany R, Schleuniger J, Zinn M. 2004. Encapsulated zosteric acid embedded in poly 3-hydroxyalkanoate coatings - Protection against biofouling. *Polymer Bulletin*. 52(1):65–72.
- Gerits E, Kucharikova S, Van Dijck P, Erdtmann M, Krona A, Lovenklev M, Frohlich M, Dovgan B, Impellizzeri F, Braem A, et al. 2016. Antibacterial activity of a new broad-spectrum antibiotic covalently bound to titanium surfaces. *J Orthop Res*. 34(12):2191–2198.
- Gharbi A, Legigan T, Humblot V, Papot S, Berjeaud JM. 2015. Surface functionalization by covalent immobilization of an innovative carvacrol derivative to avoid fungal biofilm formation. *Amb Express*. 5:9.

- Giacomucci L, Bertocello R, Salvadori O, Martini I, Favaro M, Villa F, Sorlini C, Cappitelli F. 2011. Microbial deterioration of artistic tiles from the facade of the Grande Albergo Ausonia & Hungaria (Venice, Italy). *Microb Ecol.* 62(2):287–298.
- Goeres DM, Loetterle LR, Hamilton MA, Murga R, Kirby DW, Donlan RM. 2005. Statistical assessment of a laboratory method for growing biofilms. *Microbiology.* 151:757–762.
- Gomes IB, Meireles A, Gonçalves AL, Goeres DM, Sjollem J, Simões LC, Simões M. 2017. Standardized reactors for the study of medical biofilms: a review of the principles and latest modifications. *Crit Rev Biotechnol.* 1–14.
- Gottschalk F, Sun TY, Nowack B. 2013. Environmental concentrations of engineered nanomaterials: Review of modeling and analytical studies. *Environ Pollut.* 181:287–300.
- Guinta RA, Carbone LA, Rosenberg EL, Uhrich EK, Tabak M, Chikindas LM. 2009. Slow release of salicylic acid from degrading poly(anhydride ester) polymer disrupts bimodal pH and prevents biofilm formation in *Salmonella typhimurium* MAE52. In: Bailey WC, editor. *Biofilms: formation, development and properties*. New York (NY): Nova Science Publishers; p. 649–658.
- Guillaume O, Garric X, Lavigne JP, Van Den Berghe H, Coudane J. 2012. Multilayer, degradable coating as a carrier for the sustained release of antibiotics: preparation and antimicrobial efficacy *in vitro*. *J Control Release.* 162(3):492–501.
- Hall-Stoodley L, Costerton JW, Stoodley P. 2004. Bacterial biofilms: from the natural environment to infectious diseases. *Nat Rev Microbiol.* 2(2):95–108.
- Hammond PT. 2012. Building biomedical materials layer-by-layer. *Mater Today.* 15:5.
- Hany R, Böhlen C, Geiger T, Schmid M, Zinn M. 2004. Toward non-toxic antifouling: synthesis of hydroxy-, cinnamic acid-, sulfate-, and zosteric acid-labeled poly[3-hydroxyalkanoates]. *Biomacromolecules.* 5(4):1452-1456.
- Harapanahalli AK, Chen Y, Li J, Busscher HJ, van der Mei corresponding HC. 2015. Influence of adhesion force on *icaA* and *cidA* gene expression and production of matrix components in *Staphylococcus aureus* biofilms. *Appl Environ Microbiol.* 81(10): 3369–

3378.

Hasan J, Jain S, Padmarajan R, Purighalla S, Sambandamurthy VK, Chatterjee K. 2018. Multi-scale surface topography to minimize adherence and viability of nosocomial drug-resistant bacteria. *Mater Des.* 140:332-344.

Heggors J, Goodheart RE, Washington J, McCoy L, Carino E, Dang T, Edgar P, Maness C, Chinkes D. 2005. Therapeutic efficacy of three silver dressings in an infected animal model. *J Burn Care Rehabil.* 26(1):53–56.

Hetrick EM, Schoenfisch MH. 2006. Reducing implant-related infections: active release strategies. *Chem Soc Rev.* 35(9):780–789.

Hirai N, Mun MK, Masuda T, Itoh H, Kanematsu H. 2015. Atomic force microscopy analysis of biofilms formed on different plastics. *Mater Technol.* 30(5):B57-B60.

Hobman JL, Crossman LC. 2015. Bacterial antimicrobial metal ion resistance. *J Med Microbiol.* 64(5):471–497.

Hockenhull JC, Dwan KM, Smith GW, Gamble CL, Boland A, Walley TJ, Dickson RC. 2009. The clinical effectiveness of central venous catheters treated with anti-infective agents in preventing catheter-related bloodstream infections: a systematic review. *Crit Care Med.* 37(2):702–712.

Hoffman LR, D'Argenio DA, MacCoss MJ, Zhang ZY, Jones RA, Miller SI. 2005. Aminoglycoside antibiotics induce bacterial biofilm formation. *Nature.* 436(7054):1171–1175.

Holmberg K, Bergstrom K, Brink C, Osterberg E, Tiberg F, Harris JM. 1993. Effects on protein adsorption, bacterial adhesion and contact-angle of grafting peg chains to polystyrene. *J Adhes Sci Technol.* 7(6):503–517.

Honraet K, Goetghebeur E, Nelis HJ. 2005. Comparison of three assays for the quantification of *Candida* biomass in suspension and CDC reactor grown biofilms. *J Microbiol Methods.* 63(3):287–295.

Hoseinnejad M, Jafari SM, Katouzian I. 2017. Inorganic and metal nanoparticles and their antimicrobial activity in food packaging applications. *Crit Rev Microbiol.* 1–21.

Hsu LC, Fang J, Borca-Tasciuc DA, Worobo RW, Moraru CA. 2013. Effect of micro- and nanoscale topography on the adhesion of bacterial cells to solid surfaces. *Appl*

- Environ Microbiol. 79(8): 2703–2712.
- Huang KS, Yang CH, Huang SL, Chen CY, Lu YY, Lin YS. 2016. Recent advances in antimicrobial polymers: a mini-review. *Int J Mol Sci.* 17(9).
- Huang QY, Wu HY, Cai P, Fein JB, Chen WL. 2015. Atomic force microscopy measurements of bacterial adhesion and biofilm formation onto clay-sized particles. *Sci Rep.* 5:16857.
- Hume EBH, Baveja J, Muir BW, Schubert TL, Kumar N, Kjelleberg S, Griesser HJ, Thissen H, Read R, Poole-Warren LA, et al. 2004. The control of *Staphylococcus epidermidis* biofilm formation and *in vivo* infection rates by covalently bound furanones. *Biomaterials.* 25(20):5023–5030.
- Ip M, Lui SL, Poon VKM, Lung I, Burd A. 2006. Antimicrobial activities of silver dressings: an *in vitro* comparison. *J Med Microbiol.* 55(1):59–63.
- Ivanova EP, Hasan J, Webb HK, Gervinskas G, Juodkazis S, Truong VK, Wu AHF, Lamb RN, Baulin VA, Watson GS, et al. 2013. Bactericidal activity of black silicon. *Nat Commun.* 4: 2838.
- Jansen B, Goodman LP, Ruiten D. 1993. Bacterial adherence to hydrophilic polymer-coated polyurethane stents. *Gastrointest Endosc.* 39(5):670–673.
- Johnson JR, Kuskowski MA, Wilt TJ. 2006. Systematic review: antimicrobial urinary catheters to prevent catheter-associated urinary tract infection in hospitalized patients. *Ann Intern Med.* 144(2):116–126.
- Johnston EE, Bryers JD, Ratner BD. 1997. Interactions between *Pseudomonas aeruginosa* and plasma-deposited PEO-like thin films during initial attachment and growth. *Polym Prepr.* 38(1):1016–1017.
- Jose B, Antoci V, Zeiger AR, Wickstrom E, Hickok NJ. 2005. Vancomycin covalently bonded to titanium beads kills *Staphylococcus aureus*. *Chem Biol.* 12(9):1041–1048.
- Jung WK, Koo HC, Kim KW, Shin S, Kim SH, Park YH. 2008. Antibacterial activity and mechanism of action of the silver ion in *Staphylococcus aureus* and *Escherichia coli*. *Appl Environ Microb.* 74(7):2171–2178.
- Kaplan JB. 2010. Biofilm dispersal: mechanisms, clinical implications, and potential therapeutic uses. *J Dent Res.* 89(3):205–218.

- Kerstens M, Boulet G, Van Kerckhoven M, Clais S, Lanckacker E, Delputte P, Maes L, Cos P. 2015. A flow cytometric approach to quantify biofilms. *Folia Microbiol.* 60(4):335–42.
- Kim YG, Lee JH, Gwon G, Kim SI, Park JG, Lee J. 2016. Essential oils and eugenols inhibit biofilm formation and the virulence of *Escherichia coli* O157:H7. *Sci Rep.* 6:36377.
- Kingshott P, Wei J, Bagge-Ravn D, Gadegaard N, Gram L. 2003. Covalent attachment of poly(ethylene glycol) to surfaces, critical for reducing bacterial adhesion. *Langmuir.* 19(17):6912–6921.
- Knetsch MLW, Koole LH. 2011. New strategies in the development of antimicrobial coatings: the example of increasing usage of silver and silver nanoparticles. *Polymers.* 3(1):340–366.
- Komnatny VV, Chiang WC, Tolker-Nielsen T, Givskov M, Nielsen TE. 2014. Bacteria-triggered release of antimicrobial agents. *Angew Chem Int Ed Engl.* 53(2):439–441.
- Kostakioti M, Hadjifrangiskou M, Hultgren SJ. 2013. Bacterial biofilms: development, dispersal, and therapeutic strategies in the dawn of the postantibiotic era. *Cold Spring Harb Perspect Med.* 3(4): a010306.
- Kumar R, Munstedt H. 2005. Silver ion release from antimicrobial polyamide/silver composites. *Biomaterials.* 26(14):2081–2088.
- Larimer C, Winder E, Jeters R, Prowant M, Nettleship I, Addleman RS, Bonheyo GT. 2016. A method for rapid quantitative assessment of biofilms with biomolecular staining and image analysis. *Anal Bioanal Chem.* 408(3):999–1008.
- Lau PCY, Dutcher JR, Beveridge TJ, Lam JS. 2009. Absolute quantitation of bacterial biofilm adhesion and viscoelasticity by microbead force spectroscopy. *Biophys J.* 96(7):2935–2948.
- Le Norcy T, Niemann H, Proksch P, Linossier I, Vallee-Rehel K, Hellio C, Fay F. 2017. Anti-biofilm effect of biodegradable coatings based on hemibastadin derivative in marine environment. *Int J Mol Sci.* 18(7).
- Li X, Cheung GS, Watson GS, Watson JA, Lin S, Schwarzkopf L, Green DW. 2016.

- The nanotipped hairs of gecko skin and biotemplated replicas impair and/or kill pathogenic bacteria with high efficiency. *Nanoscale*. 8(45):18860–18869.
- Li Y, Carrera C, Chen R, Li J, Lenton P, Rudney JD, Jones RS, Aparicio C, Fok A. 2014. Degradation in the dentin-composite interface subjected to multi-species biofilm challenges. *Acta Biomater*. 10(1):375–383.
- Lichter JA, Van Vliet KJ, Rubner MF. 2009. Design of antibacterial surfaces and interfaces: polyelectrolyte multilayers as a multifunctional platform. *Macromolecules*. 42(22):8573–8586.
- Lo J, Lange D, Chew BH. 2014. Ureteral stents and foley catheters-associated urinary tract infections: the role of coatings and materials in infection prevention. *Antibiotics*. 3(1):87–97.
- Lucera A, Costa C, Conte A, Del Nobile MA. 2012. Food applications of natural antimicrobial compounds. *Front Microbiol*. 3:287.
- Meireles A, Borges A, Giaouris E, Simoes M. 2016. The current knowledge on the application of anti-biofilm enzymes in the food industry. *Food Res Int*. 86:140–146.
- Melander C, Moeller PDR, Ballard TE, Richards JJ, Huigens RW, Cavanagh J. 2009. Evaluation of dihydrooroidin as an antifouling additive in marine paint. *International Biodeterioration Association*. 63(4):529–532.
- Merritt JH, Kadouri DE, O'Toole GA. 2005. Growing and analyzing static biofilms. *Curr Protoc Microbiol*. 1:1B.1.
- Mpenyana-Monyatsi L, Mthombeni NH, Onyango MS, Momba MNB. 2012. Cost-effective filter materials coated with silver nanoparticles for the removal of pathogenic bacteria in groundwater. *Int J Environ Res Public Health*. 9(1):244–271.
- Mu HB, Tang JJ, Liu QJ, Sun CL, Wang TT, Duan JY. 2016. Potent antibacterial nanoparticles against biofilm and intracellular bacteria. *Sci Rep*. 6: 18877.
- Nagel JA, Dickinson RB, Cooper SL. 1996. Bacterial adhesion to polyurethane surfaces in the presence of pre-adsorbed high molecular weight kininogen. *J Biomater Sci Polym Ed*. 7(9):769–780.
- Newby BMZ, Cutright T, Barrios CA, Xu QW. 2006. Zosteric acid - An effective antifoulant for reducing fresh water bacterial attachment on coatings. *Jct Research*.

3(1):69–76.

Nie B, Long T, Ao H, Zhou J, Tang T, Yue B. 2016. Covalent immobilization of enoxacin onto titanium implant surfaces for inhibiting multiple bacterial species infection and *in vivo* methicillin-resistant *Staphylococcus aureus* infection prophylaxis. *Antimicrob Agents Chemother.* 61(1): e01766–16.

Nowatzki PJ, Koepsel RR, Stoodley P, Min K, Harper A, Murata H, Donfack J, Hortelano ER, Ehrlich GD, Russell AJ. 2012. Salicylic acid-releasing polyurethane acrylate polymers as anti-biofilm urological catheter coatings. *Acta Biomater.* 8(5):1869–1880.

Pappas PG, Rex JH, Sobel JD, Filler SG, Dismukes WE, Walsh TJ, Edwards JE. 2004. Guidelines for treatment of candidiasis. *Clin Infect Dis.* 38(2):161–189.

Park KD, Kim YS, Han DK, Kim YH, Lee EHB, Suh H, Choi KS. 1998. Bacterial adhesion on PEG modified polyurethane surfaces. *Biomaterials.* 19(7–9):851–859.

Park MR, Banks MK, Applegate B, Webster TJ. 2008. Influence of nanophase titania topography on bacterial attachment and metabolism. *Int J Nanomedicine.* 3(4):497–504.

Pavluhina SV, Kaplan JB, Xu L, Chang W, Yu XJ, Madhyastha S, Yakandawala N, Mentbayeva A, Khan B, Sukhishvili SA. 2012. Noneluting enzymatic antibiofilm coatings. *ACS Appl Mater Interfaces.* 4(9):4708–4716.

Pavluhina S, Zhuk I, Mentbayeva A, Rautenberg E, Chang W, Yu X, van de Belt-Gritter B, Busscher HJ, van der Mei HC, Sukhishvili SA. 2014. Small-molecule-hosting nanocomposite films with multiple bacteria-triggered responses. *NPG Asia Mater.* 6:e121.

Peng KM, Zou T, Ding W, Wang RN, Guo JS, Round JJ, Tu WP, Liu C, Hu JQ. 2017. Development of contact-killing non-leaching antimicrobial guanidyl-functionalized polymers via click chemistry. *Rsc Advances.* 7(40):24903–24913.

Percival SL, Suleman L, Vuotto C, Donelli G. 2015. Healthcare-associated infections, medical devices and biofilms: risk, tolerance and control. *J Med Microbiol.* 64:323–334.

Pérez-Díaz M, Alvarado-Gomez E, Magana-Aquino M, Sanchez-Sanchez R, Velasquillo C, Gonzalez C, Ganem-Rondero A, Martinez-Castanon G, Zavala-Alonso

- N, Martinez-Gutierrez F. 2016. Anti-biofilm activity of chitosan gels formulated with silver nanoparticles and their cytotoxic effect on human fibroblasts. *Mater Sci Eng C Mater Biol Appl.* 60:317–323.
- Plyuta VA, Lipasova VA, Kuznetsov AE, Khmel IA. 2013. Effect of salicylic, indole-3-acetic, gibberellic, and abscisic acids on biofilm formation by *Agrobacterium tumefaciens* C58 and *Pseudomonas aeruginosa* PAO1. *Appl Biochem Biotechnol.* 49(8):706–710.
- Polo A, Diamanti MV, Bjarnsholt T, Hoiby N, Villa F, Pedferri MP, Cappitelli F. 2011. Effects of photoactivated titanium dioxide nanopowders and coating on planktonic and biofilm growth of *Pseudomonas aeruginosa*. *Photochem Photobiol.* 87(6):1387–1394.
- Polo A, Gulotta D, Santo N, Di Benedetto C, Fascio U, Toniolo L, Villa F, Cappitelli F. 2012. Importance of subaerial biofilms and airborne microflora in the deterioration of stonework: a molecular study. *Biofouling.* 28(10):1093–1106.
- Qayyum S, Khan AU. 2016. Nanoparticles vs. biofilms: a battle against another paradigm of antibiotic resistance. *Med Chem Comm.* 7(8):1479–1498.
- Qian PY, Li ZR, Xu Y, Li YX, Fusetani N. 2015. Mini-review: marine natural products and their synthetic analogs as antifouling compounds: 2009-2014. *Biofouling.* 31(1):101–122.
- Qian PY, Xu Y, Fusetani N. 2010. Natural products as antifouling compounds: recent progress and future perspectives. *Biofouling.* 26(2):223–234.
- Ramasamy M, Lee J. 2016. Recent nanotechnology approaches for prevention and treatment of biofilm-associated infections on medical devices. *Biomed Research International.* 2016:1851242.
- Randall CP, Oyama LB, Bostock JM, Chopra I, Oneill AJ. 2013. The silver cation (Ag): antistaphylococcal activity, mode of action and resistance studies. *J Antimicrob Chemother.* 68(1):131–138.
- Rani SA, Pitts B, Stewart PS. 2005. Rapid diffusion of fluorescent tracers into *Staphylococcus epidermidis* biofilms visualized by time lapse microscopy. *Antimicrob Agents Chemother.* 49(2):728–732.

- Rasko DA, Sperandio V. 2010. Anti-virulence strategies to combat bacteria-mediated disease. *Nat Rev Drug Discov.* 9(2):117–128.
- Reed RB, Zaikova T, Barber A, Simonich M, Lankone R, Marco M, Hristovski K, Herckes P, Passantino L, Fairbrother DH, et al. 2016. Potential environmental impacts and antimicrobial efficacy of silver and nanosilver-containing textiles. *Environ Sci Technol.* 50(7):4018–4026.
- Roe D, Karandikar B, Bonn-Savage N, Gibbins B, Rouillet JB. 2008. Antimicrobial surface functionalization of plastic catheters by silver nanoparticles. *J Antimicrob Chemother.* 61(4):869–876.
- Romanò CL, Scarponi S, Gallazzi E, Romano D, Drago L. 2015. Antibacterial coating of implants in orthopaedics and trauma: a classification proposal in an evolving panorama. *J Orthop Surg Res.* 10:157
- Roosjen A, de Vries J, van der Mei HC, Norde W, Busscher HJ. 2005. Stability and effectiveness against bacterial adhesion of poly(ethylene oxide) coatings in biological fluids. *J Biomed Mater Res B Appl Biomater.* 73B(2):347–354.
- Roosjen A, Kaper HJ, van der Mei HC, Norde W, Busscher HJ. 2003. Inhibition of adhesion of yeasts and bacteria by poly(ethylene oxide)-brushes on glass in a parallel plate flow chamber. *Microbiology.* 149(Pt11):3239–3246.
- Rosenberg LE, Carbone AL, Romling U, Uhrich KE, Chikindas ML. 2008. Salicylic acid-based poly(anhydride esters) for control of biofilm formation in *Salmonella enterica* serovar *Typhimurium*. *Lett Appl Microbiol.* 46(5):593–599.
- Sabatini V, Cattò C, Cappelletti G, Cappitelli F, Antenucci S, Farina H, Ortenzi MA, Camazzola S, Di Silvestro G. 2018. Protective features, durability and biodegradation study of acrylic and methacrylic fluorinated polymer coatings for marble protection. *Prog. Org. Coat.* 114:47–57.
- Sadekuzzaman M, Yang S, Mizan MFR, Ha SD. 2015. Current and recent advanced strategies for combating biofilms. *Compr Rev Food Sci F.* 14(4):491–509.
- Sajid M, Ilyas M, Basheer C, Tariq M, Daud M, Baig N, Shehzad F. 2015. Impact of nanoparticles on human and environment: review of toxicity factors, exposures, control strategies, and future prospects. *Environ Sci Pollut Res.* 22(6):4122–4143.

- Saldarriaga Fernández IC, van der Mei HC, Lochhead MJ, Grainger DW, Busscher HJ. 2007. The inhibition of the adhesion of clinically isolated bacterial strains on multi-component cross-linked poly(ethylene glycol)-based polymer coatings. *Biomaterials*. 28(28):4105–4112.
- Sataev MS, Koshkarbaeva ST, Tleuova AB, Perni S, Aidarova SB, Prokopovich P. 2014. Novel process for coating textile materials with silver to prepare antimicrobial fabrics. *Colloids Surf A Physicochem Eng Asp*. 442:146–151.
- Sawant SN, Selvaraj V, Prabhawathi V, Doble M. 2013. Antibiofilm properties of silver and gold incorporated PU, PCLm, PC and PMMA nanocomposites under two shear conditions. *PloS One*. 8(5):e63311.
- [SCENIHR] Scientific Committee on Emerging and Newly Identified Health Risks 2013 ISSN:1831-4783.
- Schultz MP, Bendick JA, Holm ER, Hertel WM. 2011. Economic impact of biofouling on a naval surface ship. *Biofouling*. 27(1):87–98.
- Sheldon RA. 2016. Engineering a more sustainable world through catalysis and green chemistry. *J Royal Soc Interface*. 13(116).
- Shukla A, Fang JC, Puranam S, Hammond PT. 2012. Release of vancomycin from multilayer coated absorbent gelatin sponges. *J Control Release*. 157(1):64–71.
- Sgier L, Freimann R, Zupanic A, Kroll A. 2016. Flow cytometry combined with viSNE for the analysis of microbial biofilms and detection of microplastics. *Nat Commun*. 7:11587.
- Simões M, Simões LC, Vieira MJ. 2010. A review of current and emergent biofilm control strategies. *LWT - Food Sci. Technol*. 43:573–583.
- Singh R, Sahore S, Kaur P, Rani A, Ray P. 2016. Penetration barrier contributes to bacterial biofilm-associated resistance against only select antibiotics, and exhibits genus-, strain- and antibiotic-specific differences. *Pathog Dis*. 74(6).
- Sjollema J, Zaat SAJ, Fontaine V, Ramstedt M, Luginbuehl R, Thevissen K, Li J, van der Mei HC, Busscher HJ. 2018. *In vitro* methods for the evaluation of antimicrobial surface designs. *Acta Biomater*. 70:12–24.
- Snarr BD, Baker P, Bamford NC, Sato Y, Liu H, Lehoux M, Gravelat FN, Ostapska H,

- Baistrocchi SR, Cerone RP, et al. 2017. Microbial glycoside hydrolases as antibiofilm agents with cross-kingdom activity. *Proc Natl Acad Sci U S A*. 114(27):7124–7129.
- Sousa ACA, Pastorinho MR, Takahashi S, Tanabe S. 2014. History on organotin compounds, from snails to humans. *Environ Chem Lett*. 12(1):117–137.
- Souza VGL, Fernando AL. 2016. Nanoparticles in food packaging: biodegradability and potential migration to food- A review. *Food Packag Shelf Life*. 8:63–70.
- Spadoni Andreani E, Magagnin L, Secundo F. 2016. Preparation and comparison of hydrolase-coated plastics. *ChemistrySelect*. 1(7):1490–1495.
- Spadoni Andreani E, Villa F, Cappitelli F, Krasowska A, Biniarz P, Lukaszewicz M, Secundo F. 2017. Coating polypropylene surfaces with protease weakens the adhesion and increases the dispersion of *Candida albicans* cells. *Biotechnol Lett*. 39(3):423–428.
- Stewart PS. 2002. Mechanisms of antibiotic resistance in bacterial biofilms. *Int J Med Microbiol*. 292(2):107–113.
- Stewart PS. 2015. Antimicrobial Tolerance in Biofilms. *Microbiol Spectr*. 3(3).
- Stobie N, Duffy B, McCormack DE, Colreavy J, Hidalgo M, McHale P, Hinder SJ. 2008. Prevention of *Staphylococcus epidermidis* biofilm formation using a low-temperature processed silver-doped phenyltriethoxysilane sol-gel coating. *Biomaterials*. 29(8):963–969.
- Stowe SD, Richards JJ, Tucker AT, Thompson R, Melander C, Cavanagh J. 2011. Antibiofilm compounds derived from marine sponges. *Mar Drugs*. 9(10):2010–2035.
- Strobel C, Bormann N, Kadow-Romacker A, Schmidmaier G, Wildemann B. 2011. Sequential release kinetics of two (gentamicin and BMP-2) or three (gentamicin, IGF-I and BMP-2) substances from a one-component polymeric coating on implants. *J Control Release*. 156(1):37–45.
- Swartjes J, Sharma PK, van Kooten TG, van der Mei HC, Mahmoudi M, Busscher HJ, Rochford ETJ. 2015. Current developments in antimicrobial surface coatings for biomedical applications. *Curr Med Chem*. 22(18):2116–2129.
- Tedjo C, Neoh KG, Kang ET, Fang N, Chan V. 2007. Bacteria-surface interaction in the presence of proteins and surface attached poly(ethylene glycol) methacrylate chains. *J Biomed Mater Res A*. 82A(2):479–491.

- Tenke P, Mezei T, Bode I, Koves B. 2017. Catheter-associated urinary tract infections. *Eur Urol Suppl.* 16(4):138–143.
- Trentin DS, Silva DB, Frasson AP, Rzhepishevska O, da Silva MV, Pulcini EL, James G, Soares GV, Tasca T, Ramstedt M, et al. 2015. Natural green coating inhibits adhesion of clinically important bacteria. *Sci Rep.* 5:8287.
- Tripathy A, Sen P, Su B, Briscoe WH. 2017. Natural and bioinspired nanostructured bactericidal surfaces. *Adv Colloid Interface Sci.* 248:85–104.
- Villa F, Giacomucci L, Polo A, Principi P, Toniolo L, Levi M, Turri S, Cappitelli F. 2009. N-vanillylnonanamide tested as a non-toxic antifoulant, applied to surfaces in a polyurethane coating. *Biotechnol Lett.* 31(9):1407–1413.
- Villa F, Remelli W, Forlani F, Vitali A, Cappitelli F. 2012. Altered expression level of *Escherichia coli* proteins in response to treatment with the antifouling agent zosteric acid sodium salt. *Environ Microbiol.* 14(7):1753–1761.
- Villa F, Secundo F, Polo A, Cappitelli F. 2015. Immobilized hydrolytic enzymes exhibit antibiofilm activity against *Escherichia coli* at sub-lethal concentrations. *Curr Microbiol.* 71(1):106–114.
- Villa F, Stewart PS, Klapper I, Jacob JM, Cappitelli F. 2016. Subaerial biofilms on outdoor stone monuments: changing the perspective toward an ecological framework. *Bioscience.* 66(4):285–294.
- Villa F, Villa S, Gelain A, Cappitelli F. 2013. Sub-lethal activity of small molecules from natural sources and their synthetic derivatives against biofilm forming nosocomial pathogens. *Curr Top Med Chem.* 13(24):3184–3204.
- Vázquez-Nion D, Silva B, Prieto B. 2018. Influence of the properties of granitic rocks on their bioreceptivity to subaerial phototrophic biofilms. *Sci Total Environ.* 610–611:44–54.
- Wang B, Liu H, Wang Z, Shi S, Nan K, Xu Q, Yea Z, Chen H. 2017. A self-defensive antibacterial coating acting through the bacteria-triggered release of a hydrophobic antibiotic from layer-by-layer films. *J Mater Chem.* 5(7):1498–1506.
- Watson GS, Green DW, Schwarzkopf L, Li X, Cribb BW, Myhra S, Watson JA. 2015. A gecko skin micro/nano structure – a low adhesion, superhydrophobic, anti-wetting,

- self-cleaning, biocompatible, antibacterial surface. *Acta Biomater.* 21:109–122.
- Welch K, Cai Y, Strømme M. 2012. A method for quantitative determination of biofilm viability. *J Funct Biomater.* 3(2):418–431.
- Wu H, Moser C, Wang HZ, Hoiby N, Song ZJ. 2015. Strategies for combating bacterial biofilm infections. *Int J Oral Sci.* 7(1):1–7.
- Young ME, Alakomi HL, Fortune I, Gorbushina AA, Krumbein WE, Maxwell I, McCullagh C, Robertson P, Saarela M, Valero J, et al. 2008. Development of a biocidal treatment regime to inhibit biological growths on cultural heritage: BIODAM. *Environ Geol.* 56(3–4):631–641.
- Zanini S, Polissi A, Maccagni EA, Dell'Orto EC, Liberatore C, Riccardi C. 2015. Development of antibacterial quaternary ammonium silane coatings on polyurethane catheters. *J Colloid Interface Sci.* 451:78–84.
- Zhang F, Wu XL, Chen YY, Lin H. 2009. Application of silver nanoparticles to cotton fabric as an antibacterial textile finish. *Fiber Polym.* 10(4):496–501.
- Zhang GY, Liu Y, Gao XL, Chen YY. 2014. Synthesis of silver nanoparticles and antibacterial property of silk fabrics treated by silver nanoparticles. *Nanoscale Res Lett.* 9(1):216.
- Zodrow KR, Schiffman JD, Elimelech M. 2012. Biodegradable polymer (PLGA) coatings featuring cinnamaldehyde and carvacrol mitigate biofilm formation. *Langmuir.* 28(39):13993–13999.

Table

Table 1. Comparison of various anti-biofilm strategies presented in the paper.

Anti-biofilm strategy	Mechanism	Advantages	Disadvantages
Surface modification			
1. Passive surfaces			
1.1 Surface chemistry modifications	Anti-adhesive coatings to reduce the adhesion force between bacteria and the solid surface.	- Simple and economic.	- Difficulties in creating surface-bound thin films amenable to industrial scale processing; - Anti-biofilm properties quickly masked by bacteria-produced substances; - Surface erosion during application; - Less suitable for long-term applications; - Less biocompatibility with living tissue; - Toxicity concerns.
1.2 Surface topography modifications	Modification of surface topography with micro- and nanoscale features that minimize bacterial attachment.	- No recruitment of additional cells and biofilm buildup; - No resistance against nano-features.	- Nano-structuring methods expensive and not available for large scale production; - Discordant results about the efficacy.
2. Active antimicrobial surfaces			
2.1 Antimicrobial-releasing surfaces	Biocidal agent actively eluted from the surface by contact with an aqueous environment.	- Incorporation of different drugs in separate sets of layers.	- Not controlled elution of antimicrobials from the surface; - Less suitable for long-term applications; - Resistance against antimicrobials. - Limited applications for safety reason.
2.2 Antimicrobial-responsive surfaces	Antimicrobial release triggered by microorganisms when approaching the surface.	- Antimicrobial activity only when and where needed; - Extended material life time by decreased premature depletion of drug reservoir; - Limited accumulation of antimicrobials in vital tissues.	- Not controlled elution of antimicrobials over multiple cycles; - Non-triggered background leaching from the surface; - Limited effect against multiple microbial infections; - Altered environmental condition by bacteria affect the release of antimicrobials. - Resistance against antimicrobials. - Limited applications for safety reason.

2.3 Immobilization of antimicrobials	Antimicrobials covalently immobilized on a surface.	<ul style="list-style-type: none"> - No release of antimicrobials from the surface; -Minimized risk to expose bacteria to sub-inhibitory concentrations; - Reduced likelihood of resistance development; -Long-term activity. 	<ul style="list-style-type: none"> - Efficacy only against specific microorganism; - Limited applications for safety reason.
3. Metal-based antimicrobial materials			
3.1 Metal coatings	Heavy metal with antimicrobial activity, deposited on the surface or incorporated into a polymeric material.	-Broad spectrum of antimicrobial activity.	<ul style="list-style-type: none"> - Poor solubility of metal into polymeric materials; - Poor metal adhesion to the surface; - Lack of coating uniformity; - Resistance against metals.
3.2 Metal-nanoparticles based materials	Metals with antimicrobial activity, grouped onto nanoparticles and then incorporated into a polymeric material or coated or immobilized on a surface.	- Nanosized particles increase the antimicrobial potency	<ul style="list-style-type: none"> - Nano-structuring methods expensive and not available for large scale production; - Safety, environmental, ethical, policy and regulatory issues; - Resistance against metals.
Preventive green biocide-free surfaces			
1. Surface modification with natural anti-biofilm compounds			
1.1 Passive and active natural molecule-based strategies	Natural molecules with anti-biofilm activity coated on or incorporated into a polymeric material or eluted from a surface.	<ul style="list-style-type: none"> -No biocidal activity; -No development of resistance; -Enhanced efficacy of cleaning and disinfection procedures; -No toxicity concerns. 	<ul style="list-style-type: none"> - Discontinuous release of the compounds; - Non-uniform molecule distribution within the material - Incompatible physical characteristics of anti-biofilm compounds and most polymeric matrices; - Mechanisms of action poorly understood.
1.2 Covalent immobilization of natural molecules	Natural molecules with anti-biofilm activity grafted on a surface or covalently incorporated into the polymer.	<ul style="list-style-type: none"> - No biocidal activity; - No release of compounds from the surface; -No development of resistance; - Long-term activity; -No toxicity concerns; -Enhanced efficacy of cleaning and disinfection procedures. 	<ul style="list-style-type: none"> - Knowledge of the molecule functional groups required to exert the anti-biofilm activity; - Mechanisms of action poorly understood.

Table 2. Relevant examples of polymeric surfaces modified with natural anti-biofilm compounds.

	Coating agent	Polymer	Coating method	Target microorganism	Target mechanism	Remarks	Reference
PASSIVE STRATEGY	B-type proanthocyanidins	Permanox plastic slide	Spin coating onto a Permanox slide	<i>Staphylococcus epidermidis</i> , <i>Staphylococcus aureus</i> , <i>Enterococcus faecalis</i>	Bacterial adhesion	Treated biofilm composed by few cell clusters or single attached cells; compatibility with mammalian cells	Trentin et al. 2015
	Cinnamaldehyde, carvacrol	Poly(lactic-co-glycolic acid)	Incorporation in the polymer mixture	<i>E. coli</i> , <i>S. aureus</i> , <i>Pseudomonas aeruginosa</i>	Bacterial adhesion	Efficacy against <i>E. coli</i> and <i>S. aureus</i> biofilm	Zodrow et al. 2012
	Clove essential oil; Eugenol	poly(D,L-lactide-coglycolide)	Incorporation in the polymer mixture	<i>Escherichia coli</i> <i>O157:H7</i> and <i>K-12</i>	Bacterial adhesion, Biofilm maturation	Reduction of biofilm biomass, thickness, and substratum coverage by \geq 90%	Kim et al. 2016
	Dibromohemibastadin-1	Poly(ϵ -caprolactone-co- δ -valerolactone)	Varnish applied on the surface	<i>Paracoccus sp.</i> , <i>Bacillus sp.</i> , <i>Pseudoalteromonas sp.</i>	Bacterial adhesion, Biofilm maturation	39.6% biofilm inhibition for <i>Paracoccus sp.</i> ; no effect on <i>Pseudolateromonas sp.</i> and <i>Bacillus</i>	Le Norcy et al. 2017
	Dihydrooroidin	PVC plastic	Mixed in a generic marine-based paint and applied on the surface	<i>Halomonas pacifica</i>	Bacterial adhesion	Active after 3 weeks in a marine environment	Melander et al. 2009
	N-vanillylnonanamide	Polyurethane	Dissolution in the polymer and sprayed on the surface	<i>Bacillus cereus</i> , <i>Bacillus thuringiensis</i> , <i>Pseudomonas stutzeri</i>	Bacterial adhesion	No anti-adhesion effect	Villa et al. 2009

	<i>Rosmarinus officinalis</i> essential oil	Catheter pieces	Functionalization on magnetite nanoparticles absorbed on the surface	<i>Candida albicans</i> , <i>Candida tropicalis</i>	Fungal adhesion, Biofilm maturation	Important reduction in adhering cells and biofilm development	Chifiriuc et al. 2012
ACTIVE STRATEGY	Salicylic acid	Poly(anhydride-esters)	Releasing of salicylic acid through the hydrolytic degradation of the polymer	<i>P. aeruginosa</i>	Bacterial adhesion, quorum sensing	47% reduction of bacterial adhesion after 3 h; reduction of biofilm formation after 3 days; resistant to cell degradation when implanted subcutaneously for 4 weeks	Bryers et al. 2006
	Salicylic acid	Poly (anhydrideesters)	Dispersion in the polymer	<i>Salmonella enterica</i> serovar <i>Typhimurium</i>	Biofilm maturation	No anti-biofilm effect at the air-liquid interface, no effect on cells attachment	Rosenberg et al. 2008
	Salicylic acid	Poly[1,6-bis(o-carboxyphenoxy)-hexanoate]	Built into the polymer backbone	<i>Salmonella typhimurium</i> MAE52	Bacterial adhesion, Biofilm maturation	Biofilm inhibition without affecting cells viability	Guinta et al. 2009
	Salicylic acid	Polyurethane acrylate	Co-polymerization with an acrylate-bearing urethane resins	<i>E. coli</i> , <i>P. aeruginosa</i>	Biofilm maturation	Reduction of biofilm formation for up to 5 days without affecting cells existence	Nowatzki et al. 2012
	Zosteric acid	Polystyrene poly[3-hydroxyalkanoate-co-3-hydroxyalkanoate]	Dispersion and loading in polystyrene microcapsules	Activated sludge	Bacterial adhesion	Efficacy only in the first 48 h of biofilm formation	Geiger et al. 2004
	Zosteric acid	Polydimethylsiloxane (Sylgard® 184)	Incorporation in the polymer mixture	Microbial consortium isolated from Lake Erie, <i>Pseudomonas putida</i>	Bacterial adhesion	70% reduction of bacterial attachment	Barrios et al. 2005
	Zosteric acid	Sylicon Sylgard® 184; Sylicon RTV11	Incorporation in the polymer mixture	Microbial consortium isolated from Lake Erie, <i>P. putida</i>	Bacterial adhesion	75% reduction of bacterial attachment on Sylgard® 184 and of 55% on RTV11	Newby et al. 2006

COVALENT ATTACHMENT	Furanone 3-(10-bromohexyl)5-dibromomethylene-2(5 H)-	Polystyrene; Silastic Tenckhoff catheters	Co-polymerisation with a styrene polymer; plasma-1-ethyl-3-(dimethylaminopropyl) carbodiimide reaction	<i>S. epidermidis</i>	Bacterial adhesion, Biofilm maturation	Biofilm inhibited up to 89%; effective <i>in vivo</i> sheep model up to 65 days	Hume et al. 2004
	<i>p</i> -aminocinnamic acid; <i>p</i> -aminosalicylic acid	Low-density polyethylene	Covalent grafting on the surface	<i>E. coli</i>	Bacterial adhesion, Biofilm maturation	Reduction of biofilm biomass up to 73 %; active after multiple use	Dell'Orto et al. 2017
	<i>p</i> -aminocinnamic acid; <i>p</i> -aminosalicylic acid	Low-density polyethylene	Covalent grafting on the surface	<i>E. coli</i>	Bacterial adhesion, Biofilm maturation, Antimicrobial susceptibility	Decreasing of biofilm thickness, roughness, substratum coverage, cell and matrix polysaccharide bio-volumes by > 80%; no biocidal activity; biofilm more susceptible to ampicillin and ethanol	Cattò et al. 2018
	Zosteric acid	Poly[3-hydroxyalkanoate-co-3-hydroxyalkenoate]	Covalent incorporation in the polymer backbone	Activated sludge	Bacterial adhesion	No cell attachment	Hany et al. 2004

Figures

Figure 1. 3D-reconstructed CLSM images of *E. coli* biofilm grown on non-functionalized (a) and functionalized with *p*-aminocinnamic acid (b) low density polyethylene surfaces. Biofilm grown on non-functionalized surface (a) shows a complex heterogeneous biofilm, with multi-layers of cells (green) organized in dense macro-colonies inside a well-structured polysaccharide matrix (red). On the contrary, biofilm grown on functionalized surface (b) shows a significant decrease in thickness with a uniform mono-layer of cells (green) and a significant reduction of polysaccharide matrix (red). Scale bar = 20 μm . © Cristina Cattò.


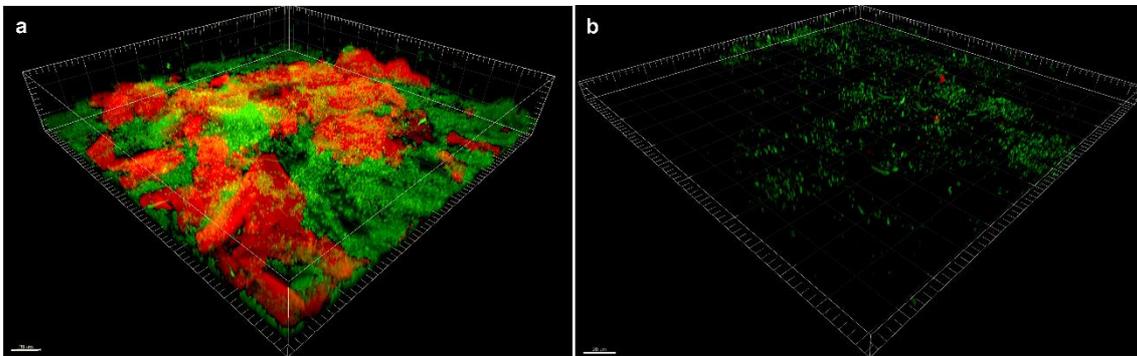


Figure 2. Time lapse CLSM of ethanol action performed on *E. coli* biofilm grown on non-functionalized (a) and functionalized with *p*-aminosalicylic acid (b) low density polyethylene surfaces. The fluorescence loss from stained *E. coli* cells is used to monitor real-time loss in cell viability during the biocide action. The images show that ethanol treatment did not affect green fluorescence of biofilm grown on the control surface within the 20 min of the experiment (a). On the contrary, ethanol treatment significantly affected the biofilm biomass integrity of biofilm grown on the functionalized surface, with a complete loss in fluorescent intensity in 5 min (b). Scale bar = 20 μ m. © Cristina Cattò.

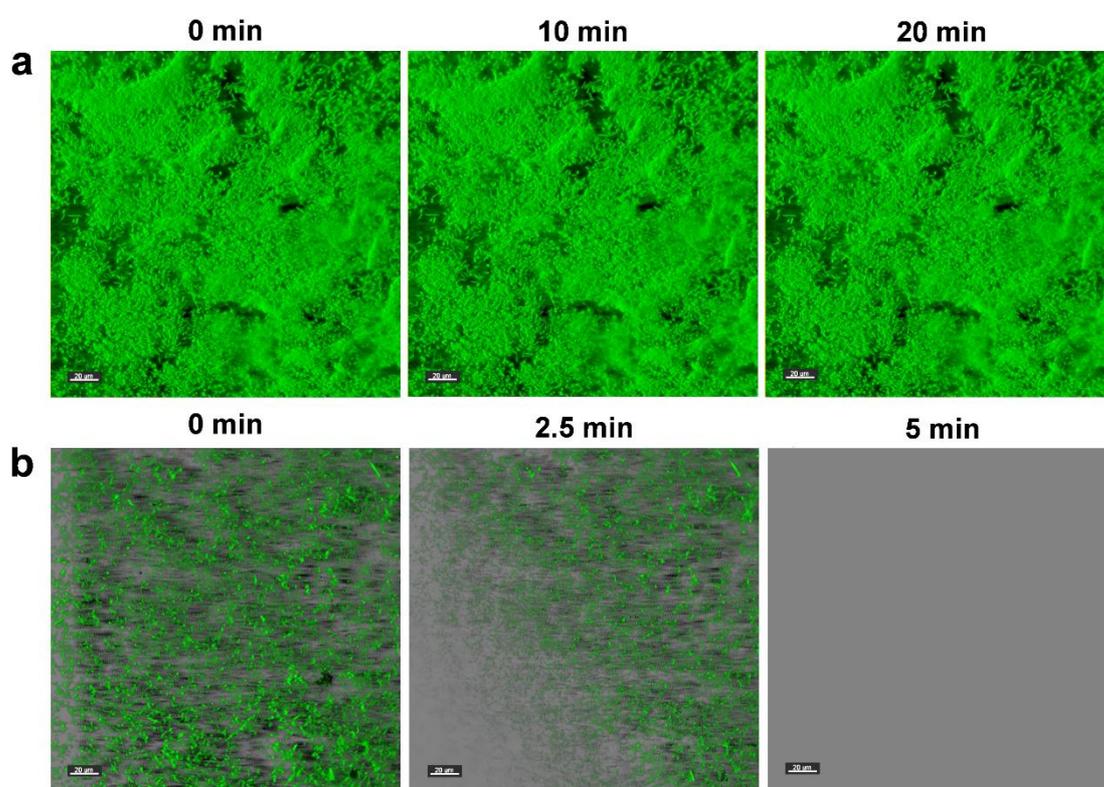

Supplemental material

Video S1. Time lapse CLSM of ethanol action performed on *E. coli* biofilm grown on low density polyethylene surface functionalized with modified cinnamic acid. The technique permits the direct visualization of cell inactivation patterns in biofilm structures during the biocide action. The method is based on the monitoring of fluorescence loss from stained *E. coli* cells, used to monitor real-time loss in cell viability. © Cristina Cattò.