

Investigation of Antibacterial Activity and Cytotoxicity of ZnO Nanoparticles Synthesized by a Novel Biological Method

¹Nada K. Abbas, ^{2,3}Israa Al-Ogaidi, ²Shurooq S. Mahmood and ⁴Hamid N. Obied

¹Department of Physics, College of Science for Women, University of Baghdad, Baghdad, Iraq

²Department of Biotechnology, College of Science, University of Baghdad, Baghdad, Iraq

³Department of Chemistry and biochemistry, Fulbright College of Arts and Sciences,
University of Arkansas, Arkansas, USA

⁴Department of Pharmacology, College of Medical, University of Babylon, Babylon, Iraq

Abstract: This study explains the biosynthesis, characterization, evaluation of the antibacterial activity and cytotoxicity of zinc oxide nanoparticles (ZnO NPs) prepared by a low-cost and simple procedure. Bio-inspired ZnO NPs were synthesized with the aid of a novel, non-toxic, ecofriendly biological material namely; Banana Peels Extract (BPE). Qualitative phytochemical screening of the aqueous fruit peels extract of banana revealed the presence of many phytochemicals in it. The structural, morphological and optical properties of the synthesized nanoparticles have been characterized by using UV-Vis spectrophotometer, XRD, FE-SEM with EDX analysis, AFM and FTIR. The synthesized ZnO NPs were characterized by a peak at 373 nm in the UV-Vis spectrum. The XRD of the sample revealed the hexagonal wurtzite structure with an average grain size 11.98 nm. Particle shapes and sizes were determined by FE-SEM. Surface morphology of the sample was studied by AFM. The FT-IR confirmed the presence of functional groups of both leaf extract and ZnO NPs. The results showed the antibacterial activity of the ZnO NPs against Gram-positive bacteria (*Staphylococcus aureus*) and Gram-negative bacteria (*Pseudomonas aeruginosa* and *Escherichia coli*). The cytotoxicity of ZnO NPs was tested against vero101 normal cell line and skin A431 cancer cell line by Crystal violet (CV) assay. Banana peels mediated ZnO NPs showed no evidence of toxicity against normal cell line, the nanoparticles are biocompatible and are non-toxic and effective cytotoxic effect against cancer cell line. These results clearly support the benefits of using a biological method for synthesizing ZnO NPs with anticancer activities.

Keywords: Zinc oxide NPs, biosynthesis, banana peels extract (BPE), phytochemical, antibacterial, cytotoxicity

INTRODUCTION

In recent years, metal and metal oxide nanoparticles have been intensively studied. The nano-sized materials have been appealed considerable attention because of their peculiar physicochemical properties compared to the bulk materials. Now-a-days, there are plenty of opportunities to fully employ in modern clinical technology the novel concepts and phenomena that have appeared in Nanoparticles research field (Jayaseelan *et al.*, 2012). Transition metal oxides have a wide range of applications as catalysts, sensors, superconductors, antimicrobial agents, etc. Researchers have extensively studied the role of noble metals such as gold and silver nanoparticles as antimicrobial agents (Vayssieres, 2004; Sanpui *et al.*, 2008). Recently, the antimicrobial activity of nano-sized ZnO particles has attracted attention, (Azizi *et al.*, 2013) since the small size (less than 100 nm) and high surface to volume ratio of the

nanoparticles allow for better interaction with bacteria (Saadat *et al.*, 2013). Recent studies have shown that these nanoparticles have selective toxicity to bacteria and exhibit minimal effects on human cells (Nagarajan and Kuppusamy, 2013; Singh *et al.*, 2012). Since, most of the ZnO nanoparticles are produced synthetically; it has certain advantages, compared to silver nanoparticles, such as lower cost and white appearance (Singh *et al.*, 2012).

The ZnO has received more attention due to its unique morphology and dimension dependent properties. ZnO being a wide band gap semiconductor (3.3 eV) has received more attention as it possesses a wide range of useful properties including electrical, chemical, optical and magnetic properties (Patil *et al.*, 2013; Suwanboon *et al.*, 2013). The ZnO has gained much importance as it can be applied in many applications such as for gas sensing, catalyst, for semiconductors, UV-shielding materials, nano generators, an antibacterial

agent, cosmetics as well as medicinal applications (Li *et al.*, 2002; Ann *et al.*, 2014). In recent days controllable synthesis of ZnO nano-materials of desired size and shapes has been the subject of the investigation by researchers because it has been found that the properties of ZnO nanoparticles are size and morphology dependent. Several methods have been developed to synthesize ZnO nanoparticles such as precipitation, hydrothermal, combustion, sol-gel, chemical vapor deposition, spray pyrolysis, sonochemical (Suwanboon, 2008; Podrezova *et al.*, 2013; Zak *et al.*, 2013).

The biosynthesized ZnO nanoparticles are trusted to be friendly with environment, non-toxic, bio-safe and bio-compatible. It is desirable for biomedical application such as drug carriers, cosmetics and filling the medical materials (Lakshmeesha *et al.*, 2014).

Plants and/or their extracts provide a biological synthesis route of several metallic nanoparticles which are more eco-friendly and allow controlling the synthesis with well-defined size and shape (Bar *et al.*, 2009). The enzymes, (Prasad and Jha, 2009) plant leaf extract (Sangeetha *et al.*, 2011) and bacteria (Jayaseelan *et al.*, 2012) plays a vital role in the green synthesis of zinc oxide nanoparticles.

Based on the review of literature, the bio synthesis of ZnO NPs using various plants has been carried out, *Cassia fistula* plant extract (Suresh *et al.*, 2015a) *Trifolium pratense* flower extract, (Dobrucka and Dlugaszewska, 2016) *Aloe barbadensis miller* leaf extract, (Sangeetha *et al.*, 2011) *Candida albicans*, (Mashrai *et al.*, 2017) *Vitex negundo* extract, (Ambika and Sundrarajan, 2015) leaf extract of *Tamarindus indica* (L.), (Elumalai *et al.*, 2015a) *Nephelium lappaceum* L. peel extract (Yuvakkumar *et al.*, 2014) *Solanum nigrum* leaf extract, (Ramesh *et al.*, 2015) *Azadirachta indica*, (Bhuyan *et al.*, 2015) curry leaf *Murraya koenigii*, (Elumalai *et al.*, 2015b) *Borassus flabellifer* fruit extract, (Vimala *et al.*, 2014) *Artocarpus gomezianus* fruits extract, (Suresh *et al.*, 2015b) *Ocimum basilicum* L. var. *purpurascens* Benth.-*Lamiaceae* leaf extract (Salam *et al.*, 2014) *Moringa oleifera* leaf extract (Elumalai *et al.*, 2015c).

Banana is one of the most common crops grown in almost all tropical countries; therefore, it is an abundant and cheap agricultural product. Peels represent about 30-40 g/100 g of fruit weight (Pangnakorn, 2006). The banana peels waste is normally disposed in municipal landfills, which contribute to the existing environmental problems. However, the problem can be recovered by utilizing its high-added value compounds, including the dietary fibre fraction that has great potential in the preparation of functional foods. Dietary fibre has shown beneficial effects in the prevention of several diseases, such as cardiovascular diseases, constipation, irritable

colon, diverticulosis, colon cancer and diabetes (Rodriguez *et al.*, 2006). The crude extract of this peel has anti-infection, anti-parasitic, anti-bacterial, anti-fungal and anti-inflammation activity (Van Beek *et al.*, 1984; Pratchayasakul *et al.*, 2008). Aqueous extract of banana peel has rich phytochemicals such as alkaloids, tannins, Flavonoids, phytosterols, phenols, terpenes and carbohydrates. Flavonoids are known to be synthesized by plants in response to microbial infections (Gopinath *et al.*, 2011).

In this study, distilled water was used to obtain the peels extract of banana. The peels of these plants were qualitatively screened for phytochemicals using standard methods. The aim of the current study is to synthesize ZnO NPs through a green approach with the aid of a novel, non-toxic, eco-friendly biological material namely, abundantly available and as a waste; Banana Peels Extract (BPE) and the nanoparticles have been characterized utilizing UV-Visible spectroscopy, X-Ray diffraction (XRD), Field Emission Scanning Electron Microscopy (FE-SEM) with EDX analysis, Atomic Force Microscopy (AFM) and Fourier Transform Infrared Spectroscopy (FT-IR) analysis.

Besides, an application of these nanoparticles that are biologically synthesized as antibacterial against Gram-positive bacteria (*Staphylococcus aureus*) and Gram-negative bacteria (*Pseudomonas aeruginosa* and *Escherichia coli*) has also been investigated. Minimum inhibitory concentration (MIC) was determined by micro broth dilution technique. The potential toxicity of ZnO NPs against vero101 normal cell line and skin A431 cancer cell line was evaluated in this present work by Crystal violet (CV) assay.

MATERIALS AND METHODS

Preparation of Fresh Banana Peels Extract (BPE):

Banana Peels Extract (BPE) was prepared according to Ibrahim (2015) with slight modification; which includes the use of microwave oven to cut short the time also to preserve the vital resources in the banana peels.

Qualitative phytochemical analysis of the peels extracts of banana:

The qualitative phytochemical analysis of the banana peels extract as an aqueous extraction were done by using different phytochemical screening to distinguish the chemical components existent in the extract in comparison with standard chemical reagents.

Test for flavonoids: A mixture of 1 mL of the peels extract and 1 mL of 5% lead acetate in a test tube was allowed to stand at room temperature (25°C) for 2 min. Formation of white precipitate in the sample indicates that the extract contained flavonoids (Harborne, 1998; Trease and Evans, 1989).

Test for tannins: A solution of 2 mL of peels extract was treated with 10% alcoholic ferric chloride. That observe of the formation of blue or green colour indicate to presence of tannins (Sasikumar *et al.*, 2014).

Test for alkaloids: Mayer's reagent and Dragendorff's reagent were used in crude extract to test the presence of alkaloids. One milliliter of the peels extract was added with 5 mL of 1% hydrochloric acid, filtered and tested with the reagents. The formation of white or creamy precipitates was taken as a positive result for the presence of alkaloids (Harborne, 1998; Trease and Evans, 1989).

Test for saponins: A mixing of 2 mL of the extract and 6 mL of distilled water in a test tube was shaken vigorously and observed formation of persistent foam that indicated the presence of saponins (Trease and Evans, 1989).

Test for glycosides: A few drops of Keed reagent [3-5 dinitrobenzoic acid (0.5 g) dissolved in 25 mL of 95% methanol and a few drops of 1 N NaOH solution was added to 5 mL of peels extract. A change in color of solution to blue indicated the presence of glycosides.

Test for phenols: Five milliliters of the extract was dissolved in distilled water which was added to 3 mL of solution of lead acetate at a concentration of 10%. The formation of a dark green colour indicates the presence of phenolic compounds (Harborne, 1998; Trease and Evans, 1989).

Test for terpenoids: One milliliter of the peels extract was treated with 1 mL of chloroform and 1 mL of concentrated sulphuric acid was added to form a layer. A reddish brown colour indicates the presence of terpenoids.

Test for steroids: One mL of chloroform, few drops of concentrated H_2SO_4 and 1 mL acetic anhydride were added and mixed with 5 mL of the peels extract. The observe of formation of dark red colour which indicates the presence of steroids (Sasikumar *et al.*, 2014).

Synthesis of the ZnO nanoparticles from BPE: Zinc nitrate (99% purity), sodium hydroxide (pellet 0.99%) and ethanol were used as the introductory material was supplied by Sigma-Aldrich chemicals. Zinc oxide nanoparticles were prepared by green synthesis method using zinc nitrate and sodium hydroxide precursors mediated Banana Peels Extract (BPE) as a reducing and capping agent. In this experiment, 0.02 M Zinc nitrate ($Zn(NO_3)_2 \cdot 4H_2O$) was added to 300 mL of distilled water under constant stirring using a magnetic stirrer to completely dissolve the zinc nitrate. Aqueous peel extract of banana was introduced into the above solution after

10min stirring at 6 mL. After 1 h to the same 2.0 M aqueous solution of sodium hydroxide (NaOH) was added to make pH 12 under high speed constant stirring, drop by drop (slowly for 15 min) touching the walls of the vessel resulted in a pale white aqueous solution. The reaction mixture was kept for incubation in a microwave oven (700 W, 2.45 GHz) for 1 min under static conditions. This reaction was then placed in a magnetic stirrer for 2 h. The beaker was sealed at this condition. After the completion of the reaction, the supernatant solution was separated carefully. The remaining solution was centrifuged at 10,000 rpm for 10 min. The pale white precipitate was then taken out and washed 3 times with distilled water followed by ethanol to get free of the impurities and remove the byproducts which were bound with the nanoparticles. Then a pale white powder of ZnO nanoparticles was obtained after drying at $400^\circ C$ in oven for 2 h (Fig. 1). During drying, $Zn(OH)_2$ is completely converted in to ZnO.

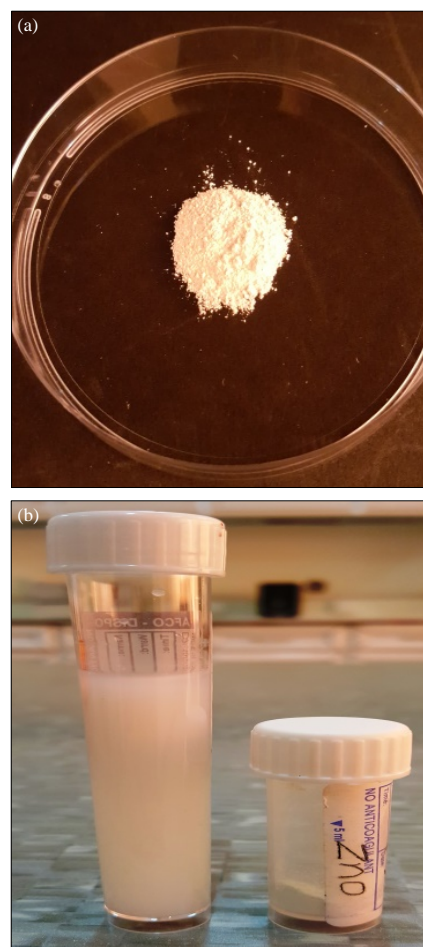


Fig. 1: ZnO nanoparticles and aqueous solution of ZnO nanoparticles

Characterization of the ZnO nanoparticles: In order to study the structural properties of ZnO NPs, the crystalline structure was recorded by X-ray diffractometer (XRD-6000, Shimadzu, Japan), the source of radiation is Cu (k_{α}) with wavelength of ($\lambda = 1.5405\text{\AA}$), voltage 60 kV and current 80 mA, at scanning speed of 5 degrees min^{-1} in 2θ range from 20-80°, these measurements were carried out on dried and finely grounded samples on Nano-Filter paper. The size and shape of the ZnO nanoparticles were determined by FE-SEM with EDX analysis and AFM. The morphology of synthesized ZnO NPs was observed by Field emission scanning electron microscopy (FE-SEM, SIGMA VP-500, ZEISS) and the elemental composition by recorded using (EDX, ZEISS). The surface morphology, particle size distribution and root mean square of roughness of the ZnO NPs were performed by using atomic force microscope AFM (AA3000 Scanning Probe Microscope SPM, tip NSC35/AIBS from Angstrom Advanced Inc., USA). The Ultraviolet–Visible spectra of the bioreduction ZnO NPs were monitored periodically as a function of wavelength within a range from 190-1100 nm by using UV-VIS Spectrophotometer (UV-1800 Shimadzu, Japan). The UV-Vis spectra were monitored for the sample at a resolution of 1 nm at room temperature. In order to determine the functional groups which present in biomolecules in the plant extract surface and their possible involvement in the synthesis of ZnO nanoparticles, Fourier Transform Infrared (FTIR) Spectroscopy measurements was carried out. The test samples were independently dried and blended with KBr to obtain a pellet. The FTIR Spectrometer where detected by used (TENSOR 27, Bruker Optik GmbH, Germany) ranging from 400-4000 cm^{-1} .

Activation and preparation of the bacterial isolates:

The bacterial isolates used in this study were obtained from Department of Biotechnology, College of Science, University of Baghdad, they were Gram-positive bacteria (*Staphylococcus aureus*) and Gram-negative bacteria (*Pseudomonas aeruginosa* and *Escherichia coli*) were used to evaluate the antibacterial activity of prepared ZnO nanoparticles. Bacterial isolates were streaked on brain heart infusion agar and incubated for 18 h at 37. Then single colony was picked up from media plate and inoculated into 5 mL of brain heart infusion broth then incubated for overnight at 37.

Determination of minimum inhibitory concentration and minimum bactericidal concentration (MIC/MBC) as an anti-bacterial activity of ZnO nanoparticle:

The anti-bacterial activities of nano-sized zinc oxide were evaluated against Gram-positive bacteria (*Staphylococcus aureus*) and Gram-negative bacteria (*Pseudomonas aeruginosa* and *Escherichia coli*) by

serial dilution method through the determination of the minimum inhibitory concentration (MIC and MBC) in the culture broth. The method of two fold serial dilutions (28) was used in this study for determination of the minimum inhibitory concentration (MIC) values, 1 mL of media was taken in a test tube, to which, 1 mL of test solution ($200\text{ }\mu\text{g mL}^{-1}$) was added, thereafter, 0.1 mL of the bacterial strains prepared in 0.9% NaCl was added to the test tube containing media and test solution. Serial dilution was done nine times giving concentrations of 200, 100, 50, 25, 12.5, 6.2, 3.1, 1.5 and 0.7 $\mu\text{g mL}^{-1}$ (Fig. 2). Then 1 mL of each serial nanoparticles were added to the set of tubes except for that tubes of control. All tubes which contained tested samples and controls were incubated for 24 h at 37°C with shaking 200 rpm. The MIC values were taken as the lowest concentration required to arrest the growth of the bacteria in the test tube after incubation (showed no turbidity) while the minimum bactericidal concentration (MBC) was determined by sub culturing 50 μL from each test tube showing no apparent growth (clear), if there was no growth this concentration was taken as MBC. A sterile loop was used to inoculate and spread the solutions on Mueller Hinton Agar medium in Petri dishes. The Petri dishes were incubated at 37°C for 24 h at the same conditions. Petri dishes of MBC were compared with control.

Cell culture: Vero101 normal cell lines and skin A431 cancer cell lines were obtained from Cancer Research Lab., Department of Pharmacology, College of Medical, University of Babylon, Babylon, Iraq. It was grown in 25 mL culture flask with growth medium containing 10% FBS and antibiotics, incubated at 37°C.

Cytotoxicity assays: The cytotoxicity assays were applied for determining the effect of ZnO NPs on Vero101 normal cell line and skin A431 cancer cell line culture, according to Freshney (1993). When the growth in the flask became as monolayer before it reached the exponential phase, the cell monolayer was harvested and re-suspended with a growth medium in a concentration of $5 \times 10^5\text{ cell mL}^{-1}$ and seeded in each well of a 96-well microtiter plate and incubated for 24 h at 37°C in the incubator. Since the cell growth reaches 80%, the wells were exposed to serial dilutions of the ZnO NPs. The cells were then exposed to 200 μL of each of the serial dilutions of ZnO nanoparticles 200, 100, 50, 25, 12.5 and 6.2 $\mu\text{g mL}^{-1}$ and incubated for 48 hr under similar conditions. Following incubation, the culture medium was changed and cells were incubated for another 24 h. After the end of the exposure the wells washed with 200 μL of a sterile Phosphate buffered saline (PBS). The effect of the ZnO NPs on the cell lines growth was assessed by Crystal violet (CV) assay.

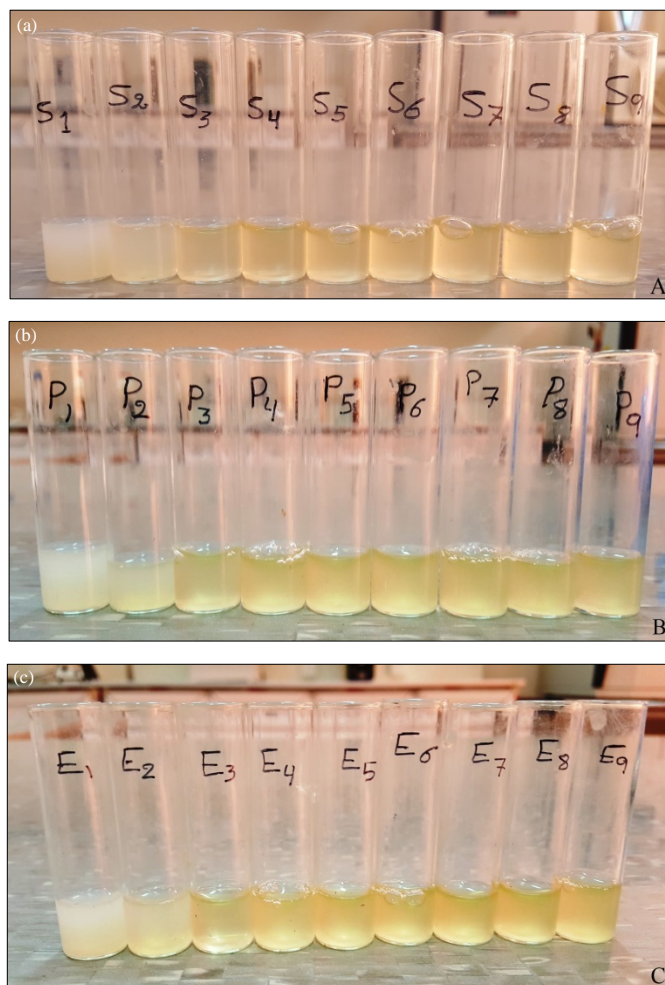


Fig. 2(a-c): Determination of minimum inhibitory concentration and minimum bactericidal concentration (MIC/MBC) as antibacterial activity of ZnO nanoparticle by serial dilution method against (a) *Staphylococcus aureus*, (b) *Pseudomonas aeruginosa* and (c) *Escherichia coli*

Crystal violet (CV) assay: Crystal violet (CV) assay was used to determine the optical density of the cell growth in each well of the microtiter plate, by using plate reader at 570 nm. After the end point of the cytotoxicity assay, the maintenance medium with the test substance was discarded out and the wells washed with 100 μ L of cold PBS by automatic pipette. Then the cell cultures were fixed with 10% buffered formalin for 20 min at room temperature. A fixative solution was discarded and 100 μ L of 0.1% aqueous CV solution was added to each well. The samples were incubated at room temperature for 20 min with gentle shaking. After that the plates were washed by submersion in flowing tap water until there is no diffusion of the crystal violet stain from the wells. The plates were allowed to dry in the air and 0.2% Triton X-100 in water was added to each well and incubated for 30 min at room temperature with gentle shaking to

dissolve the dye. Then, 100 μ L from each well was transferred into a new 96-well microplate and the absorbance was read at 570 nm by a microplate reader (Castro-Garza *et al.*, 2007).

The percentage of inhibition was calculated according to the following equation:

$$\text{Inhibition (\%)} = \frac{\text{Optical density of control wells} - \text{Optical density of test wells}}{\text{Optical density of control wells}} \times 100$$

The percentage of viability was calculated according to the following equation:

$$\text{Viability (\%)} = 100 - \frac{\text{Optical density of control wells} - \text{Optical density of test well}}{\text{Optical density of control wells}} \times 100$$

RESULTS AND DISCUSSION

To the researchers' knowledge, this report has been the first one on the preparation of ZnO NPs by using banana peels to avoid toxicity problems without a probability of cytotoxicity for living tissues after penetrating the target tissues. Conversely, other kinds of chemical reducing agent materials such as ammonia (NH_3) can cause significant toxicity for normal tissues. Interestingly the prepared ZnO NPs has selectivity toxic effect to the cancer cell.

Phytochemical properties of Banana Peels Extract (BPE):

The phytochemicals present in the banana peels were revealed by standard methods before using in ZnO nanoparticles synthesis. The results proved the qualitative presence of alkaloids, flavonoids, Tannins, saponins, glycosides, phenols and terpenoids whereas, Steroids was absence in the extract. These phytochemicals in banana peels served as reducing, stabilizing and capping agents for the microwave assisted synthesis of ZnO nanoparticles from ZnNO_3 . As illustrated in Table 1, the phytochemical screening of banana peels extract exhibited the presence a complex mixture of phytochemical components.

Ultraviolet-visible spectra analysis: Figure 3 exhibits the absorption spectrum of the bio-synthesized ZnO NPs with a strong absorption peak around 373 nm. This result indicating that ZnO NPs displays exciton absorption at 373 nm due to their large exciton binding energy at room temperature. The wavelength of 373 nm absorption peak confirms the occurrence of blue-shifted absorption spectrum with respect to the bulk value (377 nm) of the ZnO NPs, due to the quantum confinement effect, which in a good agreement of the previous report (Elumalai *et al.*, 2015c).

The energy band gap (E_g) value of the sample was calculated using the equation (Bai *et al.*, 2014):

$$E_g = hc/\lambda_m \text{ eV} \quad (1)$$

where, h is the planks constant, c is the speed of light and λ_m is the wavelength corresponding to the maximum wavelength.

The energy band gap (E_g) of ZnO NPs was calculated to be 3.33 eV. The appearance of the sharp excitonic peak indicates the high crystalline quality of the grown nanostructures (Zhou *et al.*, 2002).

X-ray Diffraction (XRD) analysis: The XRD pattern of bio-synthesized ZnO nanoparticles from peels extract banana is shown in Fig. 4. The ZnO NPs diffraction peaks clearly indicate highly crystalline structure. The sharp and narrow diffraction peaks appearing at about 2θ of 31.95, 34.60, 36.42, 47.70, 56.75, 63.02, 66.62, 68.13 and 69.22 (deg) were assigned to 100, 002, 101, 102, 110, 103, 200, 112 and 201 hkl plane values of ZnO nanoparticles. The peak intensity profiles were confirmed the hexagonal wurtzite structure by comparison with the data from JCPDS card No. 89-7102. The XRD pattern obtained is consistent with earlier reports (Parthibana and Sundaramurthy, 2015; Chitra and Annadurai, 2013).

Table 1: Qualitative phytochemical analysis of peels extracts of banana

Phytochemical	Aqueous extract of banana peels
Flavonoids	+
Tannins	+
Alkaloids	+
Saponins	+
Glycosides	+
phenols	+
Steroids	-
Terpenoids	+

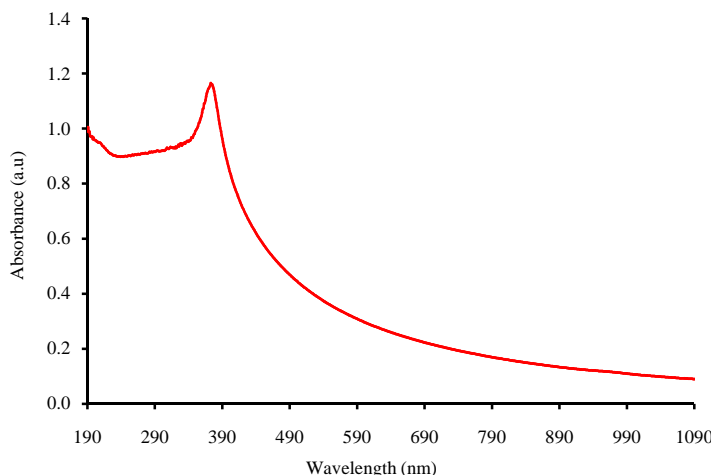


Fig. 3: UV-Vis spectrum of ZnO nanoparticles

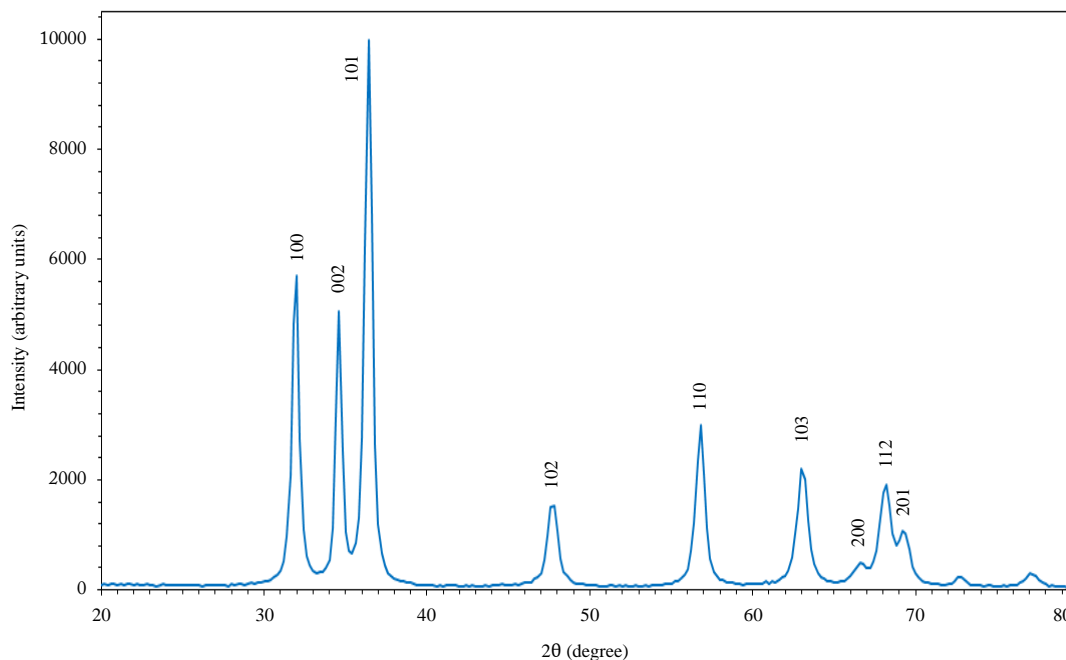


Fig. 4: XRD pattern of ZnO nanoparticles

Table 2: Structure and geometric parameters of ZnO

2θ (°)	d-spacing (Å)	FWHM (β)	Grain size (nm)
31.9537	2.798	0.6320	13.076
34.6051	2.589	0.5900	14.104
36.4245	2.464	0.6288	13.301
47.7053	1.904	0.7890	11.009
56.7595	1.620	0.7132	12.660
63.0208	1.473	0.7724	12.063
66.6222	1.402	1.0000	9.505
68.1318	1.375	0.8911	10.761
69.2215	1.356	0.8466	11.400
Average			11.986

The calculation of average grain size was attained by using Scherer's equation (Cullity, 1967):

$$D = \frac{K\lambda}{\beta \cos \theta} \text{ Å} \quad (2)$$

where, D is the average crystallite size in Å, K is the shape factor, λ is the wavelength of X-ray (1.5406 Å) Cu-Kα radiation, θ is the Bragg angle and β is the corrected line broadening of the nanoparticles. The average powder particle size calculated by Scherer's equation was found to be 11.98 nm. The calculated values are listed in Table 2.

FE-SEM with EDX analysis: After the substantiation of XRD result the sample was proceeded for the further FE-SEM with EDX studies. The size, shape and surface morphology of the ZnO nanoparticles are clearly indicated FE-SEM image as shown in Fig. 5a, the micrograph images of ZnO nanoparticles prove that they

have granular nano-sized range and have a uniform distribution with agglomerated particles of spherical shape (Elumalai *et al.*, 2015c). The particle size ranges from 10-24 nm as shown in Fig. 5a. Energy Dispersive X-ray (EDX) spectrometer analysis is confirmatory presence of elemental zinc and oxygen signals of the ZnO NPs. The vertical axis displays the number of x-ray counts although the horizontal axis displays energy in KeV (Fig. 5b). The weight and the atomic percentage of zinc, oxygen was found to be 77.9 and 22.1 these corresponds, the spectrum without impurities peaks.

Atomic Force Microscopy (AFM) analysis: The AFM images were used to characterize the structure morphology and size of the ZnO NPs. Figure 6 showed lateral and 3D AFM image for the biosynthesis ZnO nanoparticle. From AFM pictures we can see that the size of nanoparticles is bigger. The sizes of nanoparticles obtained from the AFM images appear bigger than the values that we get from XRD and FE-SEM measurements. We interpret those results to several reasons; first explanation relates the ZnO nanoparticles tend to form aggregates on the surface during deposition. Second explanation related to the shape of the tip AFM may cause misleading cross sectional views of the sample (Moosa *et al.*, 2015; Delay *et al.*, 2011). So, the width of the nanoparticle depends on probe shape. The resultant images for ZnO NPs were showed have spherical shape. The particle size of the ZnO NPs was found to be 51 nm and is also used to verify that the ZnO NPs were more or less homogenous in size.

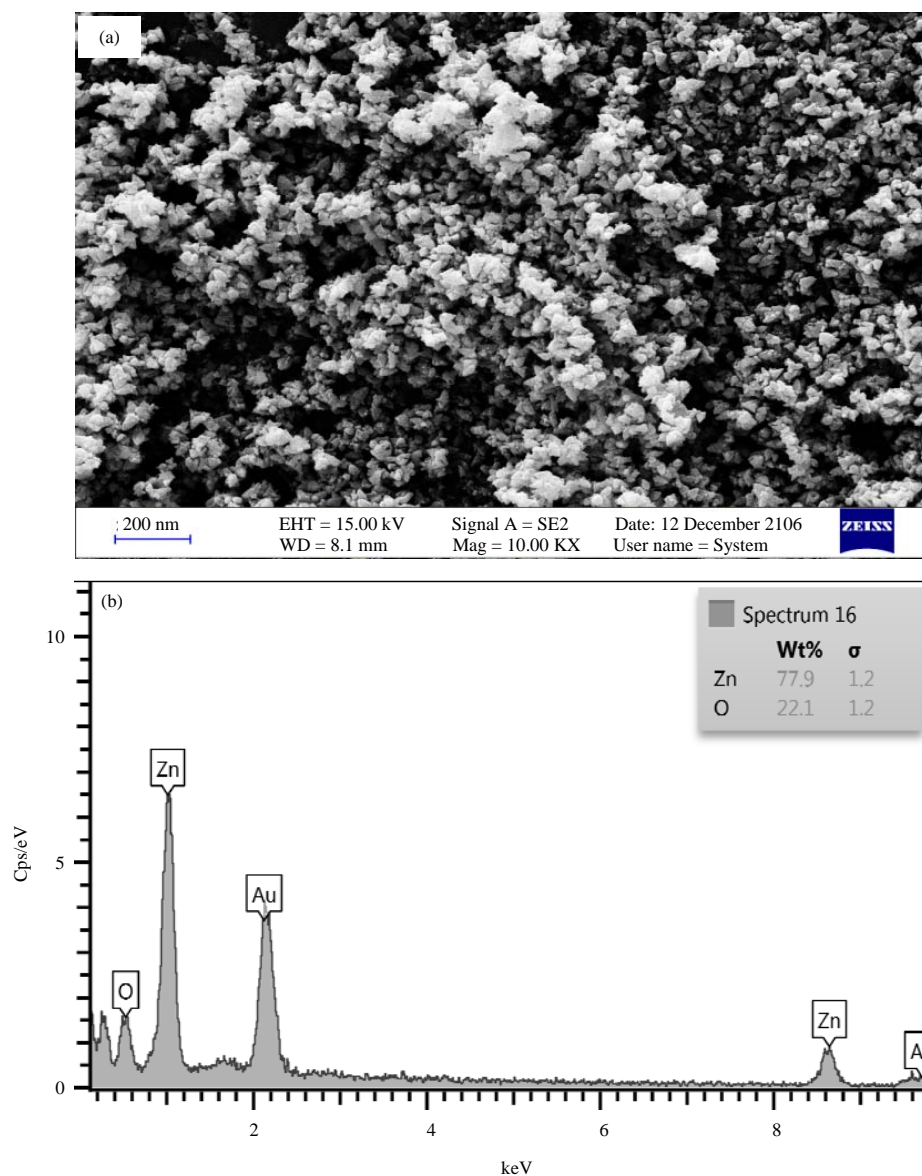


Fig. 5(a-b): (a) FE-SEM image of synthesized ZnO nanoparticles and (b) EDX spectrum

Fourier Transform Infrared Spectroscopy (FTIR):

Figure 7 presents the FTIR spectra of bio-synthesis ZnO NPs and banana peel extract, which showed the composition and quality of the product. The absorption bands at 3427, 2928, 2354, 1605, 1408, 1056 and 524 cm^{-1} in banana peel extract would be shifted into 3442, 2945, 2309, 1516, 1410, 1099 and 436 cm^{-1} of synthesized ZnO NPs sample. The strong absorption peak at 436 cm^{-1} correspond to the Zn-O bonding and confirm the presence of ZnO particles (Hong *et al.*, 2009; Umar *et al.*, 2009). The band observed at the region of 3442 cm^{-1} may be due to O-H stretching and deforming, probably due to atmospheric moisture. The other bands at 582 and 765 cm^{-1} were probably due to the carbonate

moieties that are generally observed when FTIR samples are measured in air (Padmavathy and Vijayaraghavan, 2008). The absorption band near 1410-1516 cm^{-1} were due to C=O stretching mode and the band near 2309 cm^{-1} was due to absorption of atmospheric CO_2 on the metallic cations.

Determination of Minimum inhibitory concentration and minimum bactericidal concentration (MIC/MBC) as antibacterial activity of ZnO nanoparticle:

In this study, the relative antibacterial activities of ZnO NPs suspensions against pathogenic isolates (*Staphylococcus aureus*, *Pseudomonas aeruginosa* and *Escherichia coli*) were studied in nutrient broth

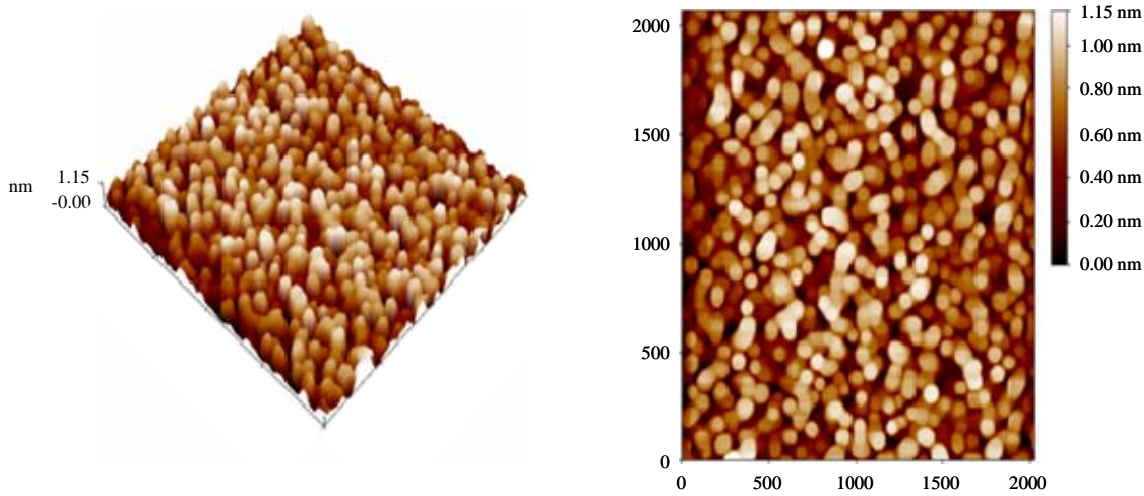


Fig. 6: Atomic force microscopy images show the particle size distribution of ZnO nanoparticles

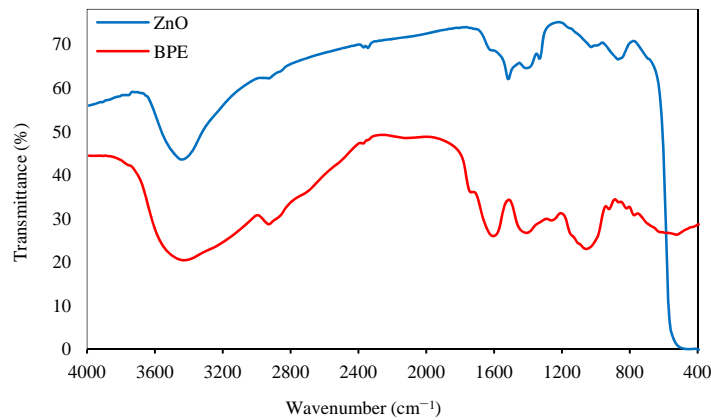


Fig. 7: FT-IR spectra of peels extract of banana and green synthesized ZnO nanoparticles

Table 3: Antibacterial activity MIC/MBC ($\mu\text{g mL}^{-1}$) of ZnO against different type from bacteria

Antibacterial activity of ZnO NPs	<i>Staphylococcus aureus</i>	<i>Escherichia coli</i>	<i>Pseudomonas aeruginosa</i>
MIC	$\geq 6.2 \mu\text{g mL}^{-1}$	$\geq 12.5 \mu\text{g mL}^{-1}$	
MBC	$\geq 6.2 \mu\text{g mL}^{-1}$	$\geq 12.5 \mu\text{g mL}^{-1}$	

quantitatively by determination of the MIC and MBC. Here, nine ZnO NPs suspensions with different concentrations were tested of 200, 100, 50, 25, 12.5, 6.2, 3.1, 1.5 and $0.7 \mu\text{g mL}^{-1}$ and the results are given in Table 3. The result showed that the Gram-negative bacterial isolates (*Pseudomonas aeruginosa* and *Escherichia coli*) were completely inhibited at the concentration about ($12.5 \mu\text{g mL}^{-1}$) of ZnO NPs (Minimum inhibitory concentration MIC) but no significant antibacterial activity was observed at concentrations less than ($6.2 \mu\text{g mL}^{-1}$) of ZnO NPs, while that the Gram-positive bacterial isolates (*Staphylococcus aureus*) were completely inhibited at the concentration about ($6.2 \mu\text{g mL}^{-1}$) of ZnO NPs but no

significant antibacterial activity was observed at concentrations less than ($3.1 \mu\text{g mL}^{-1}$) of ZnO NPs. The result also showed that the minimum bactericidal concentration (MBC) was same as MIC for all isolates. Previously it has been reported that the antibacterial mechanism of nanoparticles against Gram-positive and Gram-negative bacteria relies on the difference in the cell-membrane structural composition, most distinctively peptidoglycan layer thickness (Shrivastava *et al.*, 2007). Gram-positive bacteria possess thick peptidoglycan layer composed of linear polysaccharide chain cross-linked with small peptides, forming a rigid cell membrane to penetrate ZnO NPs, thus no inhibition zone was formed, whereas, the cell wall Gram-negative bacteria has thinner

Table 4: LSD test to show the differences between control group and different treatment group

(I) group	(J) group	Mean difference (I-J)	Std. Error	p-value	95% Confidence interval	
					Lower bound	Upper bound
Control	6.25 μg	84.17325*	1.30837	0.000	81.3671	86.9794
	12.5 μg	87.30726*	1.30837	0.000	84.5011	90.1134
	25.0 μg	92.57240*	1.30837	0.000	89.7662	95.3786
	50.0 μg	93.10518*	1.30837	0.000	90.2990	95.9114
	100.0 μg	93.19920*	1.30837	0.000	90.3930	96.0054
	200.0 μg	96.55259*	1.30837	0.000	93.7464	99.3588

*The mean difference is significant at the 0.05 level

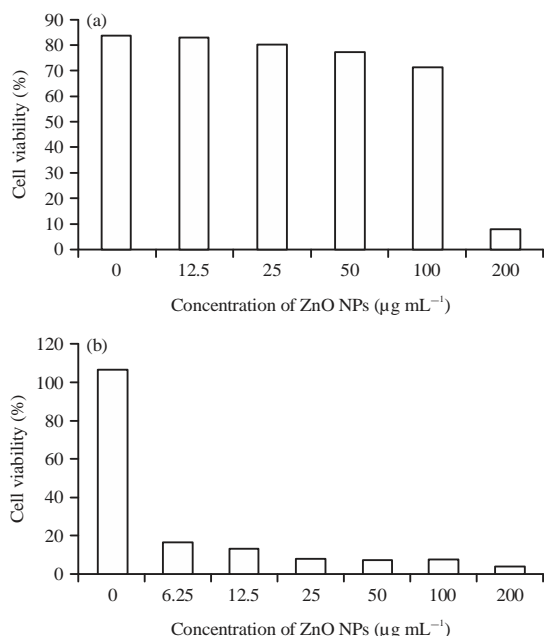


Fig. 8(a-b): Cytotoxic effect of ZnO nanoparticles against (a) Vero101 normal cell lines and (b) Skin A431 cancer cell lines. Cells were treated with various concentrations (200, 100, 50, 25, 12.5 and 6.2 $\mu\text{g mL}^{-1}$) of ZnO NPs for 72 h grown in a serum free media. The percentage of cell death induced was determined using the CV assay

polysaccharide layer, showed significant bactericidal effect. These results identical to the results of Padmavathy and Vijayaraghavan (2008) that ZnO nanoparticles have bactericidal activity in addition they interpreted in their study that once hydrogen peroxide is generated by ZnO nanoparticles, the nanoparticles remains in contact with the deadly bacteria to prevent further bacterial action and continue to generate and discharge hydrogen peroxide to the medium.

Assessment of cytotoxicity: The cytotoxicity of the zinc oxide nanoparticles was evaluated against Vero101 normal cell lines and Skin A431 cancer cell lines at

various concentrations 200, 100, 50, 25, 12.5 and 6.2 $\mu\text{g mL}^{-1}$. Toxicity of ZnO NPs depends on multiple factors such as surface oxidation and the bioactivity of the outer coating, resulting in release of zinc ions and oxygen to the system leading to toxicity (Hoshino *et al.*, 2004). Figure 8 shows the cell viability evaluated after 72 h exposure to ZnO NPs of various concentrations 200, 100, 50, 25, 12.5 and 6.2 $\mu\text{g mL}^{-1}$. Vero101 normal cells exposed to 12.5-100 $\mu\text{g mL}^{-1}$ ZnO showed no evidence to the toxicity more than 72 h (Fig. 8a) and these results indicate that even at 100 $\mu\text{g mL}^{-1}$ ZnO the nanoparticles are non-toxic *in vitro*.

The ZnO NPs were selectively induced cytotoxicity on Skin A431 cancer cell lines in dose depended manner of ZnO NPs with a significant p value 0.05 (Table 4). Maximum concentration of zinc oxide nanoparticles (200 $\mu\text{g mL}^{-1}$) effectively inhibited the growth of cell by more than 98% and these results indicate that even at 6.2 $\mu\text{g mL}^{-1}$ ZnO the nanoparticles are toxic *in vitro*.

The toxicity mechanisms of ZnO NPs may be depend on the interaction between nanoparticles and biomolecules and toxicity mainly involves protein unfolding, (Chatterjee *et al.*, 2010) fibrillation, thiol cross-linking and loss enzymatic activity. There are three mechanisms to explain why ZnO NPs exert toxic effects: oxidative stress, coordination effects and non-homeostasis effects (Chang *et al.*, 2012). According to the previous report Guo *et al.* (2016) ZnO NPs induced increasing the level of hydrogen peroxide and hydroxyl radicals, decreased the level of molecular oxygen and glutathione and reduced interleukin-8 (IL-8) release (a signal for proinflammatory mediator release). This report can be explain our results which indicated that the bio-synthesized ZnO nanoparticles are non-toxic on human healthy cells at the highest concentration with $\text{IC}_{50} = 63.615 \mu\text{g mL}^{-1}$ while it has toxicity on human cancer cells with least concentration with $\text{IC}_{50} = 31.122 \mu\text{g mL}^{-1}$ since the cancer cells already have high level of hydrogen peroxide and hydroxyl radicals (Guo *et al.*, 2016). Therefore, bio-synthesized ZnO nanoparticles allowing them to be used as an alternative agent to chemical treatment that cause human cells damage.

CONCLUSION

This study has reported the bio-synthesized of zinc oxide nanoparticles by using banana peels for the first time. It was cheap, simpler and better choice than physical and chemical methods as it is fast, clean and eco-friendly method. The XRD results indicated that the synthesized ZnO NPs have hexagonal wurtzite structure with the crystallite size of 11.98 nm. The diffuse reflectance spectrum showed a sharp increase at 373 nm with the band gap energy value of 3.33 eV. The FTIR spectrum indicated the involvement of functional activities of peels extract in the reduction of ZnO NPs. The final preparation showed that zinc oxide nanoparticles had strong antibacterial activity with no cytotoxic effect on normal cell, whereas it showed anticancer activity in dose dependent manner. Therefore a major conclusion of this study which suggests that biologically synthesized ZnO NPs might be used as novel anticancer agents for the treatment of skin cancer.

ACKNOWLEDGMENTS

The authors wish to thank MSc Sarah Lafta Hamad, Department of Biotechnology, College of Science, University of Baghdad, Baghdad, Iraq, for providing the bacterial isolates. Authors are thankful to the Cancer Research Lab., Department of Pharmacology, College of Medical, University of Babylon, Babylon, Iraq, for providing the cell lines.

REFERENCES

- Ambika, S. and M. Sundrarajan, 2015. Antibacterial behaviour of *Vitex negundo* extract assisted ZnO nanoparticles against pathogenic bacteria. J. Photochem. Photobiol. B: Biol., 146: 52-57.
- Ann, L.C., S. Mahmud, S.K.M. Bakhori, A. Sirelkhatim and D. Mohamad *et al.*, 2014. Antibacterial responses of zinc oxide structures against *Staphylococcus aureus*, *Pseudomonas aeruginosa* and *Streptococcus pyogenes*. Ceramics Int., 40: 2993-3001.
- Azizi, S., M. Ahmad, M. Mahdavi and S. Abdolmohammadi, 2013. Preparation, characterization and antimicrobial activities of ZnO nanoparticles/cellulose nanocrystal nanocomposites. BioResources, 8: 1841-1851.
- Bai, Z., X. Yan, X. Chen, K. Zhao, P. Lin and Y. Zhang, 2014. High sensitivity, fast speed and self-powered ultraviolet photodetectors based on ZnO micro/nanowire networks. Progress Nat. Sci.: Mater. Int., 24: 1-5.
- Bar, H., D.K. Bhui, G.P. Sahoo, P. Sarkar, S. Pyne and A. Misra, 2009. Green synthesis of silver nanoparticles using seed extract of *Jatropha curcas*. Colloids Surf. Physicochem. Eng. Aspects, 348: 212-216.
- Bhuyan, T., K. Mishra, M. Khanuja, R. Prasad and A. Varma, 2015. Biosynthesis of Zinc oxide nanoparticles from *Azadirachta indica* for antibacterial and photocatalytic applications. Mater. Sci. Semicond. Process., 32: 55-61.
- Castro-Garza, J., H.B. Barrios-García, D.E. Cruz-Vega, S. Said-Fernández, P. Carranza-Rosales, C.A. Molina-Torres and L. Vera-Cabrera, 2007. Use of a colorimetric assay to measure differences in cytotoxicity of *Mycobacterium tuberculosis* strains. J. Med. Microbiol., 56: 733-737.
- Chang, Y.N., M. Zhang, L. Xia, J. Zhang and G. Xing, 2012. The toxic effects and mechanisms of CuO and ZnO nanoparticles. Materials, 5: 2850-2871.
- Chatterjee, T., S. Chakraborti, P. Joshi, S.P. Singh, V. Gupta and P. Chakrabarti, 2010. The effect of Zinc oxide nanoparticles on the structure of the periplasmic domain of the *Vibrio cholerae* ToxR protein. FEBS. J., 277: 4184-4194.
- Chitra, K. and G. Annadurai, 2013. Antimicrobial activity of wet chemically engineered spherical shaped ZnO nanoparticles on food borne pathogen. Int. Food Res. J., 20: 59-64.
- Cullity, B.D., 1967. Elements of X-Ray Diffraction. 3rd Edn., Addison-Wesley, Boston, Massachusetts, USA.
- Delay, M., T. Dolt, A. Woellhaf, R. Sembritzki and F.H. Frimmel, 2011. Interactions and stability of silver nanoparticles in the aqueous phase: Influence of Natural Organic Matter (NOM) and ionic strength. J. Chromatogr. A., 1218: 4206-4212.
- Dobrucka, R. and J. Długaszewska, 2016. Biosynthesis and antibacterial activity of ZnO nanoparticles using *Trifolium pratense* flower extract. Saudi J. Biol. Sci., 23: 517-523.
- Elumalai, K., S. Velmurugan, S. Ravi, V. Kathiravan and S. Ashokkumar, 2015a. Bio-fabrication of Zinc oxide nanoparticles using leaf extract of curry leaf (*Murraya koenigii*) and its antimicrobial activities. Mater. Sci. Semicond. Process., 34: 365-372.
- Elumalai, K., S. Velmurugan, S. Ravi, V. Kathiravan and S. Ashokkumar, 2015b. RETRACTED: Facile, eco-friendly and template free photosynthesis of cauliflower like ZnO nanoparticles using leaf extract of *Tamarindus indica* (L.) and its biological evolution of antibacterial and antifungal activities. Spectrochim. Acta Part A: Mol. Biomol. Spectrosc., 136: 1052-1057.

- Elumalai, K., S. Velmurugan, S. Ravi, V. Kathiravan and S. Ashokkumar, 2015c. RETRACTED: Green synthesis of Zinc oxide nanoparticles using *Moringa oleifera* leaf extract and evaluation of its antimicrobial activity. Spectrochim. Acta Part A: Mol. Biomol. Spectrosc., 143: 158-164.
- Freshney, R.I., 1993. Culture of Animal Cells. 3rd Edn., Wiley, Hoboken, New Jersey, USA., ISBN: 9780471589662, Pages: 510.
- Gopinath, S.M., T.B. Suneetha, V.D. Mruganka and S. Ananda, 2011. Evaluation of antibacterial activity of *Tabernaemontana divaricata* (L.) leaves against the causative organisms of bovine mastitis. Int. J. Res. Phytochem. Pharmacol., 1: 211-213.
- Guo, D.D., Q. Li, H.Y. Tang, J. Su and H.S. Bi, 2016. Zinc oxide nanoparticles inhibit expression of manganese superoxide dismutase *via* amplification of oxidative stress, in murine photoreceptor cells. Cell Proliferation, 49: 386-394.
- Harborne, J.B., 1998. Phytochemical Methods: A Guide to Modern Techniques of Plant Analysis. 3rd Edn., Chapman and Hall, London, UK., ISBN: 9780412572609, Pages: 302.
- Hong, R.Y., J.H. Li, L.L. Chen, D.Q. Liu, H.Z. Li, Y. Zheng and J. Ding, 2009. Synthesis, surface modification and photocatalytic property of ZnO nanoparticles. Powder Technol., 189: 426-432.
- Hoshino, A., K. Fujioka, T. Oku, M. Suga and Y.F. Sasaki *et al.*, 2004. Physicochemical properties and cellular toxicity of nanocrystal quantum dots depend on their surface modification. Nano Lett., 4: 2163-2169.
- Ibrahim, H.M.M., 2015. Green synthesis and characterization of silver nanoparticles using banana peel extract and their antimicrobial activity against representative microorganisms. J. Radiat. Res. Applied Sci., 8: 265-275.
- Jayaseelan, C., A.A. Rahuman, A.V. Kirthi, S. Marimuthu and T. Santhoshkumar *et al.*, 2012. Novel microbial route to synthesize ZnO nanoparticles using *Aeromonas hydrophila* and their activity against pathogenic bacteria and fungi. Spectrochim. Acta Part A: Mol. Biomol. Spectrosc., 90: 78-84.
- Lakshmeesha, T.R., M.K. Sateesh, B.D. Prasad, S.C. Sharma, D. Kavyashree, M. Chandrasekhar and H. Nagabhushana, 2014. Reactivity of crystalline ZnO superstructures against fungi and bacterial pathogens: Synthesized using *Nerium oleander* leaf extract. Crystal Growth Design, 14: 4068-4079.
- Li, R., S. Yabe, M. Yamashita, S. Momose, S. Yoshida, S. Yin and T. Sato, 2002. Synthesis and UV-shielding properties of ZnO- and CaO-doped CeO₂ via soft solution chemical process. Solid State Ionics, 151: 235-241.
- Mashrai, A., H. Khanam and R.N. Aljawfi, 2017. Biological synthesis of ZnO nanoparticles using *C. albicans* and studying their catalytic performance in the synthesis of steroidal pyrazolines. Arabian J. Chem., 10: S1530-S1536.
- Moosa, A.A., A.M. Ridha and M.H. Allawi, 2015. Green synthesis of silver nanoparticles using spent tea leaves extract with atomic force microscopy. Int. J. Curr. Eng. Technol., 5: 3233-3241.
- Nagarajan, S. and K.A. Kuppusamy, 2013. Extracellular synthesis of zinc oxide nanoparticle using seaweeds of gulf of Mannar, India. J. Nanobiotechnol., Vol. 11. 10.1186/1477-3155-11-39.
- Padmavathy, N. and R. Vijayaraghavan, 2008. Enhanced bioactivity of ZnO nanoparticles-an antimicrobial study. Sci. Technol. Adv. Mater., Vol. 9, No. 3. 10.1088/1468-6996/9/3/035004.
- Pangnakorn, U., 2006. Valuable added the agricultural waste for farmers using in organic farming groups in Phitsanulok, Thailand. Proceedings of the Tropentag 2006 International Conference on Prosperity and Poverty in a Globalized World-Challenges for Agricultural Research, October, 11-13, 2006, University of Born, Bonn, Germany, pp: 275-278.
- Parthibana, C. and N. Sundaramurthy, 2015. Biosynthesis, characterization of ZnO nanoparticles by using *Pyrus pyrifolia* leaf extract and their photocatalytic activity. Int. J. Innovative Res. Sci. Eng. Technol., 4: 9710-9718.
- Patil, S.K., S.S. Shinde and K.Y. Rajpure, 2013. Physical properties of spray deposited Ni-doped Zinc oxide thin films. Ceram. Int., 39: 3901-3907.
- Podrezova, L.V., S. Porro, V. Cauda, M. Fontana and G. Cicero, 2013. Comparison between ZnO nanowires grown by chemical vapor deposition and hydrothermal synthesis. Applied Phys. A, 113: 623-632.
- Prasad, K. and A.K. Jha, 2009. ZnO nanoparticles: Synthesis and adsorption study. Nat. Sci., 1: 129-135.
- Prachayasakul, W., A. Pongchaidecha, N. Chattipakorn and S. Chattipakorn, 2008. Ethnobotany and ethnopharmacology of *Tabernaemontana divaricata*. Indian J. Med. Res., 127: 317-335.
- Ramesh, M., M. Anbuvaran and G. Viruthagiri, 2015. Green synthesis of ZnO nanoparticles using *Solanum nigrum* leaf extract and their antibacterial activity. Spectrochim. Acta Part A: Mol. Biomol. Spectrosc., 136: 864-870.
- Rodriguez, R., A. Jimenez, J. Fernandez-Bolanos, R. Guillen and A. Heredia, 2006. Dietary fibre from vegetable products as source of functional ingredients. Trends Food Sci. Technol., 17: 3-15.
- Saadat, M., S.R. Mohammadi and M. Eskandari, 2013. Evaluation of antibacterial activity of ZnO and TiO₂ nanoparticles on planktonic and biofilm cells of *Pseudomonas aeruginosa*. Biosci. Biotechnol. Res. Asia, 10: 629-635.

- Salam, H.A., R. Sivaraj and R. Venkatesh, 2014. Green synthesis and characterization of Zinc oxide nanoparticles from *Ocimum basilicum* L. var. *purpurascens* Benth.-Lamiaceae leaf extract. *Mater. Lett.*, 131: 16-18.
- Sangeetha, G., S. Rajeshwari and R. Venkatesh, 2011. Green synthesis of zinc oxide nanoparticles by *Aloe barbadensis miller* leaf extract: Structure and optical properties. *Mater. Res. Bull.*, 46: 2560-2566.
- Sanpui, P., A. Murugadoss, P.V.D. Prasad, S.S. Ghosh and A. Chattopadhyay, 2008. The antibacterial properties of a novel chitosan-Ag-nanoparticle composite. *Int. J. Food Microbiol.*, 124: 142-146.
- Sasikumar, R., P. Balasubramanian, P. Govindaraj and T. Krishnaveni, 2014. Preliminary studies on phytochemicals and antimicrobial activity of solvent extracts of *Coriandrum sativum* L. roots (Coriander). *J. Pharmacogn. Phytochem.*, 2: 74-78.
- Shrivastava, S., T. Bera, A. Roy, G. Singh, P. Ramachandrarao and D. Dash, 2007. Characterization of enhanced antibacterial effects of novel silver nanoparticles. *Nanotechnology*, Vol. 18, No. 22. 10.1088/0957-4484/18/22/225103.
- Singh, G., E.M. Joyce, J. Beddow and T.J. Mason, 2012. Evaluation of antibacterial activity of ZnO nanoparticles coated sonochemically onto textile fabrics. *J. Microbiol. Biotechnol. Food Sci.*, 2: 106-120.
- Suresh, D., P.C. Nethravathi, H. Rajanaika, H. Nagabhushana and S.C. Sharma, 2015a. Green synthesis of multifunctional Zinc oxide (ZnO) nanoparticles using *Cassia fistula* plant extract and their photodegradative, antioxidant and antibacterial activities. *Mater. Sci. Semicond. Process.*, 31: 446-454.
- Suresh, D., R.M. Shobharani, P.C. Nethravathi, M.A.P. Kumar, H. Nagabhushana and S.C. Sharma, 2015b. Artocarpus gomezianus aided green synthesis of ZnO nanoparticles: Luminescence, photocatalytic and antioxidant properties. *Spectrochim. Acta Part A: Mol. Biomol. Spectrosc.*, 141: 128-134.
- Suwanboon, S., 2008. Structural and optical properties of nanocrystalline ZnO powder from sol-gel method. *ScienceAsia*, 34: 31-34.
- Suwanboon, S., P. Amornpitoksuk, A. Sukolrat and N. Muensit, 2013. Optical and photocatalytic properties of La-doped ZnO nanoparticles prepared via precipitation and mechanical milling method. *Ceram. Int.*, 39: 2811-2819.
- Trease, G.E. and W.C. Evans, 1989. *Pharmacognosy*. 11th Edn., Macmillan Publishers, London, UK., pp: 35-38.
- Umar, A., M.M. Rahman, M. Vaseem and Y.B. Hahn, 2009. Ultra-sensitive cholesterol biosensor based on low-temperature grown ZnO nanoparticles. *Electrochem. Commun.*, 11: 118-121.
- Van Beek, T.A., R. Verpoorte, A.B. Svendsen, A.J.M. Leeuwenberg and N.G. Bisset, 1984. *Tabernaemontana* L. (Apocynaceae): A review of its taxonomy, phytochemistry, ethnobotany and pharmacology. *J. Ethnopharmacol.*, 10: 1-156.
- Vayssieres, L., 2004. On the design of advanced metal oxide nanomaterials. *Int. J. Nanotechnol.*, 1: 1-41.
- Vimala, K., S. Shenbagamoorthy, P. Manickam, V. Srinivasan and K. Soundarapandian, 2014. Green synthesized doxorubicin loaded zinc oxide nanoparticles regulates the Bax and Bcl-2 expression in breast and colon carcinoma. *Process Biochem.*, 49: 160-172.
- Yuvakkumar, R., J. Suresh, A.J. Nathanael, M. Sundrarajan and S.I. Hong, 2014. Novel green synthetic strategy to prepare ZnO nanocrystals using rambutan (*Nephelium lappaceum* L.) peel extract and its antibacterial applications. *Mater. Sci. Eng.: C*, 41: 17-27.
- Zak, A.K., W.H. Majid, H.Z. Wang, R. Yousefi, A.M. Golsheikh and Z.F. Ren, 2013. Sonochemical synthesis of hierarchical ZnO nanostructures. *Ultrason. Sonochem.*, 20: 395-400.
- Zhou, H., H. Alves, D.M. Hofmann, W. Kriegseis, B.K. Meyer, G. Kaczmarczyk and A. Hoffmann, 2002. Behind the weak excitonic emission of ZnO quantum dots: ZnO/Zn(OH)₂ core-shell structure. *Applied Phys. Lett.*, 80: 210-212.